

~~ISO/TC156 N769~~

ISO/FDIS 16701

~~ISO/TC-156/WG 7~~

Secretariat: SAC

Date: ~~2024-12-05~~ 2025-02-24

**Corrosion of metals and alloys — Corrosion in artificial atmosphere
— Accelerated corrosion test involving exposure under controlled
conditions of humidity cycling and intermittent spraying of a salt
solution**

*Corrosion des métaux et alliages — Corrosion en atmosphère artificielle — Essai de corrosion accélérée
comprenant des expositions sous conditions contrôlées à des cycles d'humidité et à des vaporisations
intermittentes de solution saline*

iteh Standards
Document Preview

ISO/FDIS 16701

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ee-4901-a0ea-01cd9a36065e/iso-fdis-16701>

FDIS stage

Edited DIS - MUST BE USED FOR FINAL DRAFT

ISO/FDIS 16701:2025(en)

© ISO 2023/2025

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO/FDIS 16701

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ee-4901-a0ea-01cd9a36065e/iso-fdis-16701>

ii

© ISO 2024 — All rights reserved

© ISO 2025 — All rights reserved

Edited DIS - MUST BE USED FOR FINAL DRAFT

Contents —

Foreword	v
Introduction	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Apparatus	3
4.1 General	3
4.2 Basic properties of the climate test chamber	3
4.3 Supporting requisites and accessories	3
5 Test method	4
5.1 Test exposure conditions	4
5.2 Requirements on salt solution	15
5.3 Precipitation rate of salt solution	16
5.4 Start and end time of test	16
5.5 Duration of test	16
6 Test object conditions	16
6.1 Requirements on geometry and distribution	16
6.2 Test object preparation	19
7 Requirements on quality control and calibration	19
7.1 Overview	19
7.2 Climate control and calibration procedures	20
7.3 Control of salt solution precipitation	23
7.4 Recommended schedule for quality control	25
7.5 Deviation handling	26
8 Evaluation of results	28
9 Test report	28
Annex A (normative) Requirements on test equipment	29
Annex B (informative) Example of a device for spraying a precipitation of salt solution	34
Annex C (informative) Guidelines on devices for independent, stand-alone temperature and humidity monitoring	36
Annex D (normative) Temperature/humidity control procedures	38
Annex E (informative) Guiding information about the test method	44
Bibliography	53
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2

ISO/FDIS 16701:2025(en)

4	Apparatus	2
4.1	Basic properties of the climate test chamber	3
4.2	Supporting requisites and accessories	3
5	Test method	4
5.1	Test exposure conditions	4
5.2	Requirements on salt solution	11
5.3	Precipitation rate of salt solution	12
5.4	Start and end time of test	12
5.5	Duration of test	12
6	Test object conditions	12
6.1	Requirements on geometry and distribution	12
6.2	Test object preparation	14
7	Requirements on quality control and calibration	15
7.1	Orientation	15
7.2	Climate control and calibration procedures	15
7.3	Control of salt solution precipitation	17
7.4	Recommended schedule for quality control	19
7.5	Deviation handling	20
8	Evaluation of results	21
9	Test report	21
Annex A (normative)	Requirements on test equipment	22
Annex B (informative)	Application of salt containing solution	26
Annex C (informative)	Requirements on devices for independent, stand-alone temperature and humidity monitoring	27
Annex D (normative)	Temperature/humidity control procedures	28
Annex E (informative)	Guiding information about the test method	31
Bibliography		39

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ce-4901-a0ea-01cd9a36065e/iso-fdis-16701>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 262, *Metallic and other inorganic coatings, including for corrosion protection and corrosion testing of metals and alloys*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 16701:2015), which has been technically revised.

The main changes are as follows:

- The test cycle has been revised with the same intended acceptance criteria to improve field correlation and reproducibility, when performed in various exposure chambers.
- An alternative cycle with alternating temperature in the climate cycling (constant dew point instead of constant temperature) is introduced. It is a modification of the so called ACT1 (originally Volvo Standard 423-0014), however within the same scope and intended acceptance criteria.
- Extensive requirements and guidelines on quality assurance of test equipment and control procedures have been incorporated, mainly as normative and informative annexes.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Atmospheric corrosion of metallic materials, with or without corrosion protection, is influenced by many environmental factors, ~~the importance of which can vary. Their corrosion impact varies~~ with the type of ~~metallie~~~~exposed~~ material ~~and with the type of environment~~~~system~~. It is therefore not possible to design a laboratory corrosion test in such a way that the complexity and variations of real, in-service conditions are fully represented. Acceleration (forced conditions) as such can also have a negative impact on the correlation ~~to~~~~field~~ performance. Nevertheless, tests with humidity cycling and only intermittent exposure to a salt solution provide a better correlation ~~to~~~~field~~ performance than tests using continuous salt spray.

This document was developed in the automotive context, where the major contributor to corrosion is the use of wintertime de-icing road salt in cool/cold temperate areas ~~around the world, here represented by, most often as~~ sodium chloride depositions ~~acting that act~~ in cyclic humidity conditions. The test procedure is moderately forced by humidity and salt ~~and, It is~~ intended to be applicable for quality assurance of the metals and corrosion protections typically encountered in motor vehicles:^{[4]-[4], [11]-[11]} The method ~~can have relevance is~~ also ~~relevant~~ in other areas of application, provided ~~representing they have~~ similar climatic conditions with an influence of sodium chloride depositions:^{[5]-[5], [5]-[5]}

iTeh Standards (<https://standards.iteh.ai>) Document Preview

ISO/FDIS 16701

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ee-4901-a0ea-01cd9a36065e/iso-fdis-16701>

Corrosion of metals and alloys — Corrosion in artificial atmosphere — Accelerated corrosion test involving exposure under controlled conditions of humidity cycling and intermittent spraying of a salt solution

1 Scope

This document specifies an atmospheric accelerated test procedure in two closely related variants, ~~A and B, containing that contain~~ intermittent salt exposure combined with dynamic humidity patterns; variant A at constant dew point, ~~and~~ variant B at constant temperature. ~~They~~ These variants are used in assessing the corrosion resistance of metals in environments where there is a significant influence of chloride ions, mainly as sodium chloride from ~~e.g., for example,~~ winter road de-icing salt. The results obtained do not permit far-reaching conclusions on the corrosion resistance of the tested metallic material under the whole range of environmental conditions in which it ~~may~~ can be used. Nevertheless, the method provides information on the relative corrosion resistance of a material exposed to a salt-contaminated environment with varying humidity conditions.

The two accelerated laboratory corrosion test variants are applicable to:

- ~~metals and their alloys (ferrous and non-ferrous);~~
- ~~metallic coatings;~~
- ~~chemical conversion coatings;~~
- ~~organic coating on metals;~~
- ~~a combination of materials and coatings that include galvanic interactions and/or crevice conditions~~

NOTE 1 If testing low-alloy stainless steels according to this document, especially austenitic grades, there is a risk of ~~receiving~~ exaggerated pitting, ~~which is~~ not representative ~~for~~ most service environments.

NOTE 2 This document is not suitable for testing of wax and oil-based rust protection agents, due to the constantly elevated temperature condition of the test.

This document also specifies requirements on the test equipment and contains detailed procedures for quality control, including recommended instrumentation.

This document does not specify the dimensions of the tests specimens, the exposure period to be used for a particular product, or the interpretation of the results. Such details are provided in the appropriate product specifications.

2 Normative references

There are no ~~documents referred to in the text in such a way that some or all of their content constitutes requirements of~~ normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1 3.1

step
individual test climate operation, such as a linear climate ramp between two temperatures/humidities, constant conditions during a defined time period or spraying with salt solution

3.2 3.2

sequence
series of *steps* (3.1)(3.1)

Note_1_to_entry:- Sequences can be handled as subroutines when programming the test.

3.3 3.3

sub-cycle
sequence (3.2)(3.2) when run in a repeated mode

3.4 3.4

test cycle
full weekly (168 h) series of different *sub-cycles* (3.3)(3.3), to be repeated for a stipulated number of weeks

3.5 3.5

test area
area within a test chamber (usually horizontal and designed as a structure open to air circulation) onto which test objects and their possible fixtures are supported

3.6 3.6

approved test area
part of the test area where the test conditions are fulfilled regarding climate and downfall of salt solution

3.7 3.7

test space
volume defined by the *test area* (3.5)(3.5) times the permissible height to which the test object can extend without compromising the stipulated uniformity of the test conditions

3.8 3.8

approved test space
approved test area (3.6)(3.6) times the height where the test conditions are fulfilled regarding climate and downfall of salt solution

3.9 3.9

tolerance span
permissible deviation ranges for the achieved momentaneous value of set temperature and relative humidity relative to the programmed set value at any time increment

3.10 ~~3.10~~ macro wetness

droplets or an aqueous film visible to the eye, e.g. from spray application or by dew formation

4 Apparatus

4.1 General

The climate test chamber shall offer a design so that the requirements on the test conditions in ~~Clause 5~~ Clause 5 can be obtained and controlled within the permissible range according to the procedures in ~~Clause 7~~ Clause 7. The chamber test area and test space where these conditions are fulfilled are hence defined as the approved test area and approved test space, respectively. The test chamber design, applicable for manufacturing and at purchasing, shall be in accordance with ~~Annex A~~ Annex A.

4.2 Basic properties of the climate test chamber

For a fully automated procedure, the chamber shall be equipped with a spray device capable of producing a uniformly distributed spray of salt solution falling onto the test objects at a rate defined in ~~5.3.5.3~~ 5.3.5.3. This can be performed by installing a swaying rail or tube equipped with flat-spraying nozzles as depicted in ~~Annex B~~ Annex B. Other technical solutions are permissible, provided ~~meeting they meet~~ the downfall requirements.

4.3 Supporting requisites and accessories

The following requisites and accessories are necessary to perform the test method:

- ~~Compressed, oil-free, clean air for humidification (if supplied by spray humidifiers), for cleaning salt solution from spray nozzles and as a source for the renewal of chamber air. The supplier of the equipment shall stipulate the specific requirements of the compressed air supply and may additionally include special requirements, such as that it should meet ISO 8573-1, class 4 or better.~~⁷⁾
- ~~A low-conductivity water supply for humidification or evaporative spray humidifiers and for the preparation of salt solutions. The requirement on water quality for the equipment shall be set by the supplier of the equipment. From corrosion testing standpoint, it is sufficient to be below 20 µS/cm. If the humidification of the test chamber is supplied by high-pressure nozzle(s), the acceptable conductivity of the water can be as low as 5 µS/cm to secure the long-term performance of nozzles and heaters.~~
- ~~A tank for preparation and storage of salt solution or, alternatively, a system for direct in-line mixing of water, saturated NaCl solution and, if applicable, diluted sulphuric acid to be contained within the stipulated concentration and tolerances.~~
- ~~A conductivity meter with built-in temperature compensation for preparation and control of the salt solution.~~
- ~~A standard pH-meter, with a glass-electrode for weak electrolytes, to be regularly calibrated at pH = 7 and pH = 4.~~
- ~~Sodium chloride of min 99,9 % purity without sodium iodide addition, either as a vacuum salt supplied as grain salt or in accordance with the specification in ISO 9227.~~¹⁾

- ~~Sulphuric~~Sulfuric acid of reagent grade.

WARNING — Sulfuric Acid¹⁾ (CAS Registry Number[®] 7664-93-9) solution causes severe skin burns and eye damage. Refer to safety data sheet for details. Handling of sulfuric acid solution shall be restricted to skilled personnel or conducted under their control.

For accuracy, safety and convenience, it is recommended to use commercially available ampoules of diluted sulfuric acid (titration reagent) as a source for the preparation of the solution. One litre of a 0,5 M ~~sulphuric~~sulfuric acid solution prepared this way is sufficient for the acidification of 10 m³ of ready salt solution. In the unlikely need to adjust up the pH of the ready salt solution, ~~then~~ use diluted sodium hydroxide. For safety reasons, it is recommended to prepare the solution from commercially available titration ampoules. A 0,01 M solution is convenient.

- ~~—~~A device for independent monitoring of temperature and relative humidity (RH) shall be accessible. ~~Annex C~~Annex C provides information on suitable devices. This instrument shall on stipulated intervals be used for independent monitoring and calibration of the climate in the test space of the exposure chamber in accordance with ~~Annex D~~Annex D.
- ~~—~~Racks of inert material for support and aligned fixation of test object, which shall not hamper a free airflow around the test objects, nor collect standing wetness. Further requirements are found in ~~Clause 6~~Clause 6.
- ~~—~~Funnels, beakers/measuring glasses and a balance with at least 0,1 g accuracy for monitoring and calibration of salt solution downfall throughout the test plane of the exposure chamber.

5 Test method

5.1 Test exposure conditions

There are two variants of the test procedure, ~~here denoted: variant~~ variant A and ~~variant~~ variant B. ~~Figure 1 shows overviews~~Figure 1 gives an overview of the weekly patterns of temperature and ~~relative humidity~~RH for the variants.


In variant A, the humidity cycling is run with a counter temperature cycling to receive approximately constant absolute humidity/dew point. This is in line with outdoor day and night conditions. Variant B runs with constant temperature during the humidity cycling and is recommended when heavy test objects are exposed. ~~It~~

~~Biweekly in~~ both test variants, a ~~sequence~~3-h wet period of intermittent spray with salt solution ~~is~~ followed by a ~~slow~~controlled gradual drying-up for several hours ~~is applied twice weekly~~ (see ~~Figure 2~~Figure 2). This 24-h sequence is identical for variant A and B, ~~except for the last 2 h, connecting to a and is followed by a~~ series of repeated 12-h climate cycles, ~~which are~~ different for variants A and B (see ~~Figure 3~~Figure 3), ~~followed by a new 24-h sequence with spray, and so on. A chosen~~Figure 3). ~~The sequence of spraying followed by climate cycling is repeated once to reach a one-week (168 h) test cycle. This~~ cycle is then repeated for a stipulated number of weeks (typically six weeks) to form a complete atmospheric corrosion test. The background and rationales

¹⁾ Chemical Abstracts Service (CAS) Registry Number[®] is a trademark of the American Chemical Society (ACS). This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

¹⁾ Chemical Abstracts Service (CAS) Registry Number[®] is a trademark of the American Chemical Society (ACS). This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.


behind the two test variants and guidelines when to use which are found in Annex E, Tables 1 and 2. Annex E, Table 1 and Table 2 list the detailed exposure conditions step by step for each test variant independently.

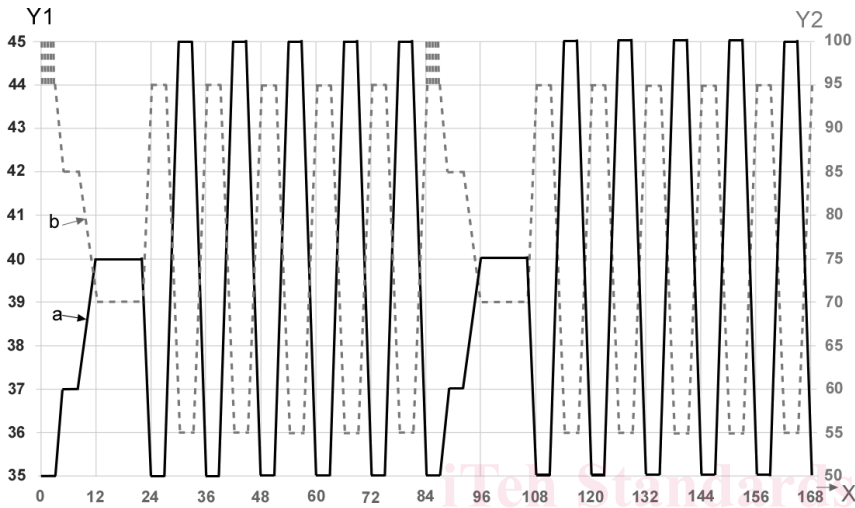

(<https://standards.iteh.ai>)
Document Preview

ISO/FDIS 16701

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ce-4901-a0ea-01cd9a36065e/iso-fdis-16701>

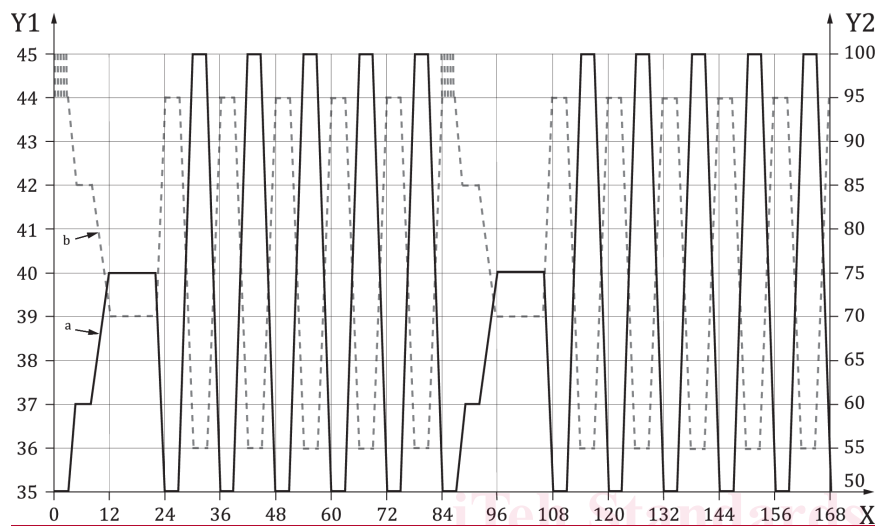


a) Weekly overview of test variant A

(<https://standards.iteh.ai>)

Document Preview

[ISO/FDIS 16701](https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ce-4901-a0ea-01cd9a36065e/iso-fdis-16701)

<https://standards.iteh.ai/catalog/standards/iso/0a1fec04-45ce-4901-a0ea-01cd9a36065e/iso-fdis-16701>

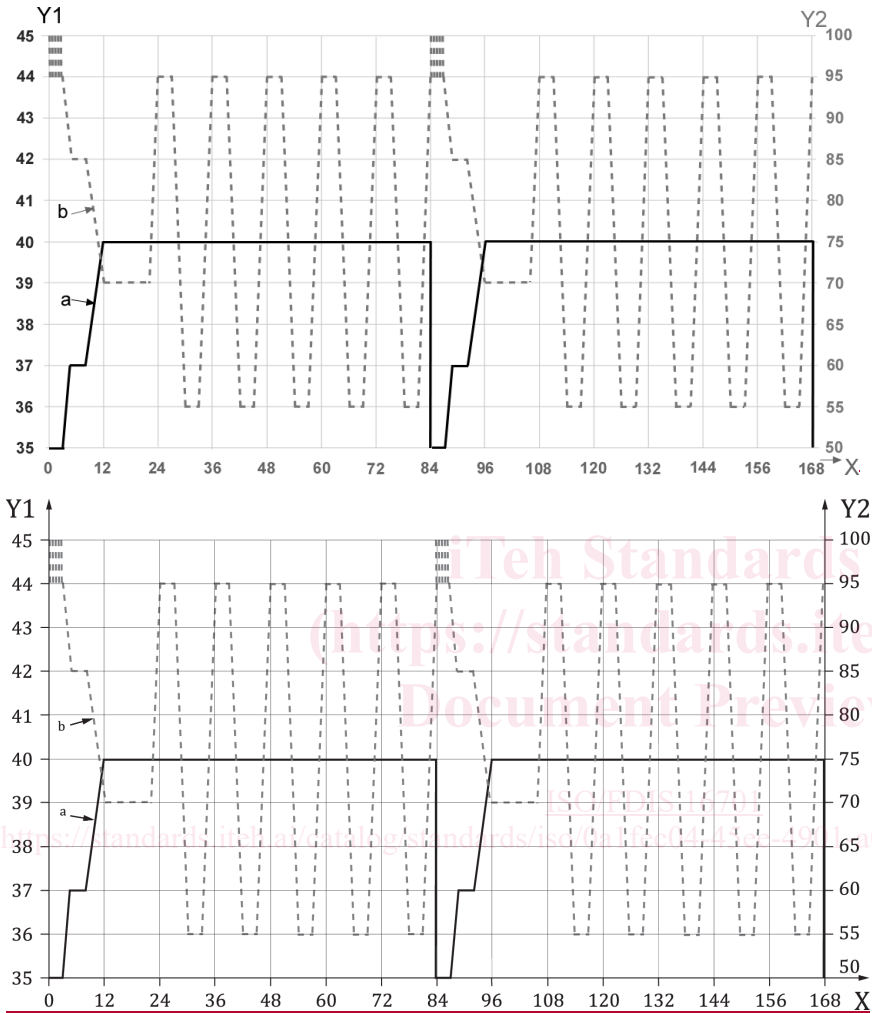



b) Weekly overview of test variant B

Key

- | | | | |
|----|-------------------|---|--|
| X | elapsed time (h) | a | temperatureTemperature, expressed in solid line. |
| Y1 | temperature (°C) | b | relativeRelative humidity, expressed in dotted line. |
| Y2 | relative humidity | | |

Figure 1.— Complete one-week cycles of the test variants A and B

ISO/FDIS 16701:2024(E)2025(en)

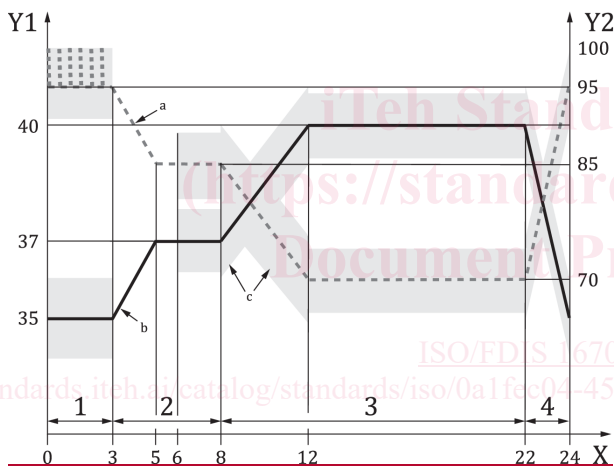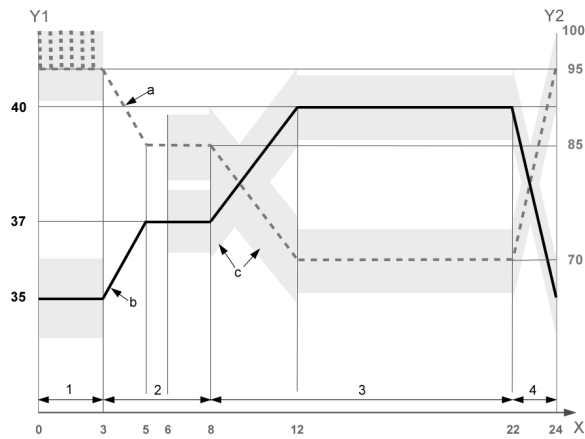

a) Test variant A