

~~DRAFT INTERNATIONAL STANDARD~~

ISO/~~DIS~~ **FDIS** 21068-2:2023(E)

ISO/TC 33

Secretariat: BSI

~~draft edition~~

~~2023-08~~

Date: 2024-02-13

**Chemical analysis of raw materials and refractory products containing silicon-carbide, silicon-nitride, silicon-oxynitride and sialon. —**

iTeh Standards  
(<https://standards.itih.ai>)

Document Preview

**Part 2:  
Determination of volatile components, total carbon, free carbon, silicon carbide, total and free silicon, free and surface silica**

Analyse chimique des matières premières et des produits réfractaires contenant du carbure de silicium, du nitrure de silicium, ~~oxynitride~~ de l'oxynitride de silicium et ~~sialon~~ du SiAlON. —

Partie 2: ~~Détermination~~ Dosage des ~~composants~~ composés volatils, du carbone total, du carbone libre, du carbure de silicium, du silicium ~~total~~ total et libre et de la silice libre et ~~superficiel~~ superficielle

**FDIS stage**

© ISO ~~2023~~2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
~~Email~~E-mail: [copyright@iso.org](mailto:copyright@iso.org)  
Website: ~~www.iso.org~~[www.iso.org](http://www.iso.org)

Published in Switzerland

iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

ISO/FDIS 21068-2

<https://standards.iteh.ai/catalog/standards/iso/1634748e-e9b2-46df-896d-9d4bdaddf73b/iso-fdis-21068-2>

**Contents—Page**

Foreword .....	vi
Introduction .....	viii
1 Scope .....	1
2 Normative references .....	1
3 Terms and definitions .....	2
4 Determination of volatile components by gravimetric methods .....	2
4.1 General .....	2
4.2 Determination of the loss on drying at 250 °C ( $W_{LOD250}$ ) .....	3
4.2.1 Principle .....	3
4.2.2 Apparatus .....	3
4.2.3 Procedure .....	3
4.2.4 Calculation .....	3
4.3 Determination of the loss on ignition in argon ( $W_{LOIAr}$ ) .....	3
4.3.1 Principle .....	3
4.3.2 Apparatus .....	4
4.3.3 Test assembly .....	4
4.3.4 Reagents .....	5
4.3.5 Procedure .....	5
4.3.6 Calculation .....	6
5 Determination of the total carbon content .....	6
5.1 Scope .....	6
5.2 Combustion techniques .....	6
5.2.1 Combustion in a resistance furnace with lead borate or tin as decomposing agent .....	6
5.2.2 Combustion in an induction furnace (IF) with metallic powder as decomposing agent .....	7
5.3 Detection techniques .....	8
5.3.1 Coulometry .....	8
5.3.2 Detection of the released carbon dioxide, CO <sub>2</sub> , by infrared absorption (IR) .....	9
5.3.3 Thermal conductivity (TC) method .....	9
5.4 Expression of results .....	9
6 Determination of free carbon content .....	9
6.1 General .....	9
6.1.1 Direct methods .....	10
6.1.2 Indirect methods .....	17
7 Determination of silicon carbide content .....	20
7.1 General .....	20

7.2	Determination of silicon carbide, SiC, by indirect method .....	20
7.2.1	Principle.....	20
7.2.2	Calculation.....	20
7.2.3	Precision .....	21
7.3	Determination of silicon carbide, SiC, by combustion methods .....	21
7.3.1	Procedure.....	21
7.3.2	Calculation.....	21
7.4	Determination of silicon carbide, SiC, by combustion at 750 °C .....	21
7.4.1	Principle.....	21
7.4.2	Residue production .....	22
7.4.3	Determination of the total carbon content of the residue.....	22
7.4.4	Calculation.....	22
8	Determination of total silicon content .....	23
9	Determination of free silicon content.....	23
9.1	Principle.....	23
9.2	Pretreatment with hydrochloric acid.....	24
9.3	Determination of free silicon by hydrogen evolution.....	24
9.3.1	Reagents.....	24
9.3.2	Apparatus.....	24
9.3.3	Mass of test portion.....	25
9.3.4	Procedure.....	26
9.3.5	Blank test.....	27
9.3.6	Calculation.....	27
10	Determination of free silica content.....	28
10.1	Principle.....	28
10.2	Reagents.....	28
10.3	Apparatus.....	28
10.4	Sample preparation.....	29
10.5	Procedure.....	29
10.5.1	Determination .....	31
10.5.2	Calculation and expression of SiO <sub>2</sub> content .....	31
11	Determination of surface silica content.....	31
12	Expression of results .....	31
13	Test report .....	32
Annex A	(informative) Precision data .....	33
A.1	Precision data obtained for the analysis of refractories containing carbon and/or silicon carbide.....	33
A.1.1	Samples .....	33

A.1.2 Precision data for the determination of total carbon content..... 33

A.1.3 Precision data for the determination of free carbon content ..... 34

A.1.4 Precision data for the determination of silicon carbide content..... 36

A.1.5 Precision data for the determination of free silicon content ..... 37

A.2 Precision data obtained in an interlaboratory study for the certification of the certified reference material BAM-S008 silicon carbide powder ..... 38

A.2.1 Precision data for the determination of total carbon content..... 38

Annex B (informative) Examples of certified reference materials for calibration of carbon analyser..... 40

Annex C (normative) Correction of the free carbon content in case of oxidation of SiC ..... 41

C.1 General ..... 41

C.2 Procedure ..... 41

C.3 Calculation ..... 41

Bibliography ..... 43

Foreword — iii

Introduction — iv

1 Scope — 1

2 Normative references — 1

3 Terms and definitions — 2

4 Determination of volatile components by gravimetric methods — 2

5 Determination of the total carbon content — 4

6 Determination of free carbon content — 7

7 Determination of silicon carbide content — 15

8 Determination of total silicon content — 17

9 Determination of free silicon content — 18

10 Determination of free silica content — 21

11 Determination of surface silica content — 24

12 Expression of results — 24

13 Test report — 24

Annex A (informative) Precision data for the determination of total carbon, free carbon, silicon carbide and free silicon — XX

Annex B (informative) Examples of CRMs for calibration of carbon analyser — 25

Annex C (normative) Correction of the free carbon content in case of oxidation of SiC — 26

Bibliography — 27

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 33, *Refractories*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 187, *Refractory products and materials*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 21068-2:2008), which has been **editorially and technically revised**.

The main changes are as follows:

- ~~The~~ methods described in ISO 12698-1:2007 for the determination of free carbon, silicon carbide and free silica ~~were inserted into~~ have been included in this document;
- ~~Methods~~ methods that are no longer used in practice have been removed;
  - ~~The list of documents in Normative References has been adjusted;~~
  - ~~Bibliography was adjusted to this document;~~
- ~~The entire normative references and bibliography have been updated;~~
- document has been comprehensively editorially revised ~~with respect to~~.

[A list of all parts in the ISO Form&Style requirements21068 series can be found on the ISO website.](#)

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html)![www.iso.org/members.html](http://www.iso.org/members.html).

iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

[ISO/FDIS 21068-2](#)

<https://standards.iteh.ai/catalog/standards/iso/1634748e-e9b2-46df-896d-9d4bdaddf73b/iso-fdis-21068-2>

## Introduction

The ISO 21068 series has been developed from the combination of EN 12698-1:2007-<sup>[11]</sup> and EN 12698-2:2007-<sup>[12]</sup> and ISO 21068-1:2008-<sup>[3]</sup>,<sup>[31]</sup> ISO 21068-2:2008-<sup>[4]</sup> and ISO 21068-3:2008-<sup>[5]</sup>,<sup>[51]</sup>. The latter has been originally developed from the combination of Japanese standard JIS R 2011:2007-<sup>[6]</sup>,<sup>[61]</sup> and work items developed within CEN. Because there is a wide variety of laboratory equipment in use, the most commonly used methods are described.

ISO 21068-4 is derived from EN 12698-2:2007-<sup>[2]</sup>,<sup>[21]</sup> describing XRD methods for the determination of mineralogical phases typically apparent in nitride and oxy-nitride bonded silicon carbide refractory products using a Bragg-Brentano diffractometer.

The ISO 21068 series is applicable to the analysis of all refractory products as classified in ~~the~~ ISO 10081-1-<sup>[7]</sup>,<sup>[71]</sup> ISO 10081-2-<sup>[8]</sup>,<sup>[81]</sup> ISO 10081-3-<sup>[9]</sup>,<sup>[91]</sup> and ISO 10081-4-<sup>[10]</sup>,<sup>[101]</sup> (shaped) and ISO 1927-1-<sup>[11]</sup>,<sup>[111]</sup> (unshaped) and for raw materials containing carbon and/or silicon carbide. Therefore, the ISO 21068 series covers the full range of analysis from pure silicon carbide to oxide refractory composition with low-content silicon carbide and/or nitrides. Primarily, the ISO 21068 series provides methods to distinguish between different carbon bound types like total carbon ( $C_{\text{total}}$ ) and free carbon ( $C_{\text{free}}$ ) and derives from these two the silicon carbide content. ISO 21068-4 includes details of sample preparation and general principles for qualitative and quantitative analysis of mineralogical phase composition. Quantitative determination of  $\alpha$ -Si<sub>3</sub>N<sub>4</sub>,  $\beta$ -Si<sub>3</sub>N<sub>4</sub>, Si<sub>2</sub>ON<sub>2</sub>, AlN, and sialon are described.

If free carbon is present, ISO 21068-2 includes different temperature treatments to determine the mass changes gravimetrically. Frequently, the resulting residue is used for other determinations.

The determination of other groups of analytes described in the ISO 21068 series are free metals, free silicon ( $Si_{\text{free}}$ ), free aluminium ( $Al_{\text{free}}$ ), free magnesium ( $Mg_{\text{free}}$ ), free iron ( $Fe_{\text{free}}$ ) and the group of oxides from main to trace components.

The ISO 21068 series also describes the determination of silicon dioxide, total silicon, oxygen and nitrogen and other oxide bound metals that typically occur in the materials.

It represents a listing of analytical methods which is generally structured according to material composition. However, it is still the user who should prove the applicability of the method depending on the material and analytical requirements.

The most broadly used analytical techniques such as X-ray fluorescence spectroscopy (XRF) and inductively coupled plasma-optical emission spectrometry (ICP-OES) suffer from the disadvantage that the analytical results are chemical species independent. For carbon-containing ceramic raw materials and compositions, the ISO 21068 series provides analytical methods for the determination of free carbon, and SiC in the presence of oxide compounds in particular SiO<sub>2</sub>.

Due to the diversity of laboratory equipment, the ISO 21068 series summarizes broadly used analytical techniques which lead to equivalent results. For example, the determination of carbon is based on all described methods on the reaction of carbon with oxygen at elevated temperatures to CO<sub>2</sub>. Thus, carbon is analysed as CO<sub>2</sub>.

As well as carbon and carbide compounds, metallic silicon, aluminium and magnesium are considered. While metallic silicon is mainly a precursor material which remains after the production process of SiC in the raw material, metallic aluminium is added as an antioxidant in carbon-containing refractory formulations.

Mostly oxide bound components, such as Al<sub>2</sub>O<sub>3</sub>, CaO, MgO, TiO<sub>2</sub>, Cr<sub>2</sub>O<sub>3</sub>, ZrO<sub>2</sub> and alkalis, can be determined by XRF, ICP-OES or wet chemical methods (see ISO 12677, ISO 26845, ISO 21587-1, ISO 21587-2 and ISO



21587-3). These results can be corrected by formulae provided by the ISO 21068 series, in consideration of the values obtained by the determination of carbon, SiC, and metallic components.

The ISO 21068 series also provides methods for qualitative and quantitative determinations of the nitrogen content and the determination of oxygen. Thereby only the total content of nitrogen and oxygen is given; a precise determination of non-carbide components (oxides and nitrides) is not possible in this way.

The ISO 21068 series also provides methods to distinguish quantitatively between different varieties of nitrides like silicon nitride, silicon oxy-nitride and sialon.

iTeh Standards  
(<https://standards.itih.ai>)  
Document Preview

ISO/FDIS 21068-2

<https://standards.itih.ai/catalog/standards/iso/1634748e-e9b2-46df-896d-9d4bdaddf73b/iso-fdis-21068-2>



~~Chemical analysis of raw materials and refractory products containing silicon-carbide, silicon-nitride, silicon-oxynitride and sialon — Part 2: Determination of volatile components, total carbon, free carbon, silicon carbide, total and free silicon, free and surface silica~~

Chemical analysis of raw materials and refractory products containing silicon-carbide, silicon-nitride, silicon-oxynitride and sialon — Part 2: Determination of volatile components, total carbon, free carbon, silicon carbide, total and free silicon, free and surface silica

## 1 Scope

This document specifies analytical techniques for the determination of volatile components by thermal treatment at specified temperatures, and methods for the determination of the total carbon content, free carbon, silicon carbide, total and free silicon and free and surface silica content of silicon-carbide, silicon-nitride and silicon-oxynitride containing raw materials and refractory products.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3310-1, *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

ISO 9286:2021, *Abrasive grains and crude — Chemical analysis of silicon carbide*

ISO 12677, *Chemical analysis of refractory products by X-ray fluorescence (XRF) — Fused cast bead method*

~~ISO 20565-1, *Chemical analysis of chrome-bearing refractory products and chrome-bearing raw materials (alternative to the X-ray fluorescence method) — Part 1: Apparatus, reagents, dissolution and determination of gravimetric silica*~~

~~ISO 20565-2, *Chemical analysis of chrome-bearing refractory products and chrome-bearing raw materials (alternative to the X-ray fluorescence method) — Part 2: Wet chemical analysis*~~

~~ISO 20565-3, *Chemical analysis of chrome-bearing refractory products and chrome-bearing raw materials (alternative to the X-ray fluorescence method) — Part 3: Flame atomic absorption spectrometry (FAAS) and inductively coupled plasma atomic emission spectrometry (ICP-AES)*~~

ISO 21068-1, *Chemical analysis of raw materials and refractory products containing silicon-carbide, silicon-nitride, silicon-oxynitride and sialon — Part 1: General information, terminology and sample preparation*

~~ISO 21079-1, Chemical analysis of refractories containing alumina, zirconia and silica — Refractories containing 5 percent to 45 percent of ZrO<sub>2</sub> (alternative to the X-ray fluorescence method) — Part 1: Apparatus, reagents and dissolution~~

~~ISO 21079-2, Chemical analysis of refractories containing alumina, zirconia, and silica — Refractories containing 5 percent to 45 percent of ZrO<sub>2</sub> (alternative to the X-ray fluorescence method) — Part 2: Wet chemical analysis~~

~~ISO 21079-3, Chemical analysis of refractories containing alumina, zirconia, and silica — Refractories containing 5 percent to 45 percent of ZrO<sub>2</sub> (alternative to the X-ray fluorescence method) — Part 3: Flame atomic absorption spectrophotometry (FAAS) and inductively coupled plasma emission spectrometry (ICP-AES)~~

~~ISO 21587-1, Chemical analysis of aluminosilicate refractory products (alternative to the X-ray fluorescence method) — Part 1: Apparatus, reagents, dissolution and gravimetric silica~~

~~ISO 21587-2, Chemical analysis of aluminosilicate refractory products (alternative to the X-ray fluorescence method) — Part 2: Wet chemical analysis~~

~~ISO 21587-3, Chemical analysis of aluminosilicate refractory products (alternative to the X-ray fluorescence method) — Part 3: Inductively coupled plasma and atomic absorption spectrometry methods~~

~~ISO 26845, Chemical analysis of refractories — General requirements for wet chemical analysis, atomic absorption spectrometry (AAS) and inductively coupled plasma atomic emission spectrometry (ICP-AES) methods~~

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 21068-1 apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <https://www.iso.org/obp>

— IEC Electropedia: available at <https://www.electropedia.org/>

## 4 Determination of volatile components by gravimetric methods

### 4.1 General

The determination of volatile components is defined as change in mass caused by heat treatment of the sample at a defined temperature. The change in mass is measured by weighing.

Table 1 gives an overview of methods for determination of volatile components.

Table 1 — Methods for determination of volatile components

Title of method	Temperature	Subclause	Application
Loss on drying (LOD <sub>250</sub> /WLOD <sub>250</sub> )	250 °C	4.24.2	Attached water and chemically combined water are removed, for example, in clay containing plastic formulations.
Loss on ignition in argon (LOI <sub>Ar</sub> /WLOI <sub>Ar</sub> )	750 °C	4.34.3	All volatile compounds from pitch- or resin-bonded formulations are removed.

#### 4.3.4.2 Determination of the loss on drying at 250 °C (~~LOD<sub>250</sub>~~ $w_{LOD250}$ )

##### 4.3.14.2.1 Principle

The test sample is heated at 250 °C ± 10 °C and the change in mass is determined gravimetrically.

##### 4.3.24.2.2 Apparatus

**4.2.2.1 Heat-resistant container**, for example, with dimensions 200 mm × 150 mm × 30 mm and made from stainless steel.

**4.2.2.2 Analytical balance**, capable of measuring to the nearest 0,01-g.

##### 4.3.34.2.3 Procedure

Heat the heat-resistant container at 250 °C ± 10 °C for 30 min. Cool in a desiccator, weigh and record its empty mass,  $m_0$ , to the nearest 0,01 g.

Transfer 100 g to 600 g of the sample into the container and spread it out evenly. Then weigh and record the mass,  $m_1$ , of the container and sample to the nearest 0,01 g.

Place the container without a lid in air and heat it at 250 °C ± 10 °C for 16 h. Allow to cool in a desiccator. Weigh and record the mass,  $m_2$ , of the container plus the dried sample to the nearest 0,01 g.

##### 4.3.44.2.4 Calculation

Calculate the loss on drying at 250 °C,  $w_{LOD250}$ , as a percentage by mass, using ~~Formula (1)~~ Formula (1).

$$w_{LOD250} = \frac{m_1 - m_2}{m_1 - m_0} \times 100 \quad (1)$$

$$w_{LOD250} = \frac{m_1 - m_2}{m_1 - m_0} \times 100 \quad (1)$$

where

- $w_{LOD250}$  is the loss on drying at 250 °C, in mass percent;
- $m_0$  is the mass of the empty container, in grams;
- $m_1$  is the mass of the container plus the sample before heating, in grams;
- $m_2$  is the mass of the container plus the sample after heating, in grams.

#### 4.4.4.3 Determination of the loss on ignition in argon (~~LOI<sub>Ar</sub>~~ $w_{LOIAr}$ )

##### 4.4.14.3.1 Principle

The sample is heated in an argon atmosphere at 750 °C to remove volatile matter. The change in mass is determined gravimetrically.

NOTE The residue can be used for determination of  $C_{total}$ , SiC and  $C_{free}$  in organic matter containing materials.

The change in mass during heating in argon must be considered for the calculation of  $C_{total}$ , SiC and  $C_{free}$ .

4.4.24.3.2 Apparatus


Ordinary laboratory apparatus and the following.

- 4.3.2.1 **Analytical balance**, capable of measuring to the nearest 0,001-g.
- 4.3.2.2 **U-tube**, with ground stoppers and filled with magnesium perchlorate.
- 4.3.2.3 **Resistance furnace**, capable of reaching  $(750 \pm 25) \text{ }^\circ\text{C}$ , in the centre of the heating zone.
- 4.3.2.4 **Thermocouple with display**, registering up to 1 200  $^\circ\text{C}$ .
- 4.3.2.5 **Ceramic tube**, with cones or other gastight connector, of suitable diameter, made from porcelain, sillimanite, quartz or other suitable material.
- 4.3.2.6 **Open combustion boats**, of unglazed ceramic material, the length of which matches the oven's zone of constant temperature. The boats shall be broad enough to accommodate the amount of sample required for the determination.
- 4.3.2.7 **Gas flowmeter**, with an upper scale reading of around 20 l/h.

The argon-conducting parts, such as tubes and connections, must be made of material proofed against oxygen diffusion. Preferable materials are glass and copper. Silicone is unsuitable.

4.4.34.3.3 Test assembly

The test assembly is set up as shown in [Figure 1](#).

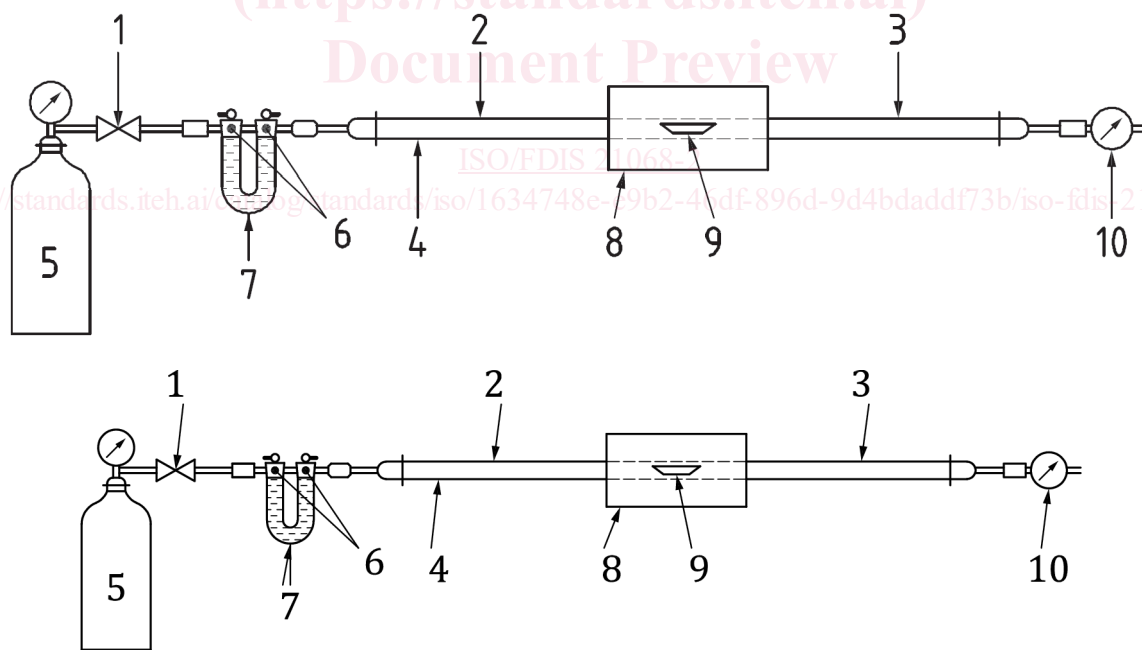

Key

- |   |                            |   |                       |    |                 |
|---|----------------------------|---|-----------------------|----|-----------------|
| 1 | valve for pressure control | 5 | argon cylinder        | 9  | combustion boat |
| 2 | cold zone B                | 6 | glass wool            | 10 | gas flowmeter   |
| 3 | cold zone A                | 7 | magnesium perchlorate | -  | -               |
| 4 | ceramic tube               | 8 | resistance furnace    | -  | -               |