

ISO/TC 20/SC 4

Secretariat: DIN

Voting begins on:
2023-08-11

Voting terminates on:
2023-10-06

Aerospace — Nuts, self-locking, with maximum operating temperature less than or equal to 425 °C — Test methods

Aéronautique et espace — Écrous à freinage interne dont la température maximale d'utilisation est inférieure ou égale à 425 °C — Méthodes de contrôle et d'essai

[iteh standards
\(https://standards.iteh.ai\)](https://standards.iteh.ai)
Document Preview

[ISO 7481](#)

<https://standards.iteh.ai/catalog/standards/sist/06ee1358-5bf2-4e15-9c5a-a24b19b505b1/iso-7481>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 7481:2023(E)

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO 7481

<https://standards.iteh.ai/catalog/standards/sist/06ee1358-5bf2-4e15-9c5a-a24b19b505b1/iso-7481>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

| | Page |
|---|----------|
| Foreword..... | iv |
| 1 Scope..... | 1 |
| 2 Normative references..... | 1 |
| 3 Terms and definitions..... | 1 |
| 4 Inspections and tests..... | 1 |
| 4.1 Hardness test..... | 1 |
| 4.1.1 Procedure..... | 1 |
| 4.1.2 Method..... | 2 |
| 4.2 Bearing surface squareness test..... | 2 |
| 4.2.1 Test device..... | 2 |
| 4.2.2 Method..... | 3 |
| 4.3 Axial load test..... | 4 |
| 4.3.1 Test device..... | 4 |
| 4.3.2 Method..... | 4 |
| 4.4 Wrenching feature test..... | 6 |
| 4.4.1 General..... | 6 |
| 4.4.2 Test device..... | 6 |
| 4.4.3 Method..... | 7 |
| 4.5 Stress embrittlement test..... | 7 |
| 4.5.1 General..... | 7 |
| 4.5.2 Test device..... | 7 |
| 4.5.3 Method..... | 7 |
| 4.6 Torque-out test..... | 8 |
| 4.6.1 General..... | 8 |
| 4.6.2 Test device..... | 9 |
| 4.6.3 Method..... | 9 |
| 4.7 Test of no rotation of the captive washer..... | 9 |
| 4.7.1 General..... | 9 |
| 4.7.2 Test device..... | 10 |
| 4.7.3 Method..... | 10 |
| 4.8 Push-out test..... | 10 |
| 4.8.1 General..... | 10 |
| 4.8.2 Test device..... | 10 |
| 4.8.3 Method..... | 11 |
| 4.9 Self-locking torque at ambient temperature..... | 12 |
| 4.9.1 Test device..... | 12 |
| 4.9.2 Method..... | 12 |
| 4.10 Self-locking torque at ambient temperature after heat soak at maximum operating temperature..... | 14 |
| 4.10.1 Test device..... | 14 |
| 4.10.2 Method..... | 14 |
| 4.11 Permanent set test..... | 15 |
| 4.11.1 General..... | 15 |
| 4.11.2 Test device..... | 15 |
| 4.11.3 Method..... | 15 |
| 4.12 Vibration test..... | 16 |
| 4.12.1 General..... | 16 |
| 4.12.2 Test device..... | 16 |
| 4.12.3 Method..... | 18 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 20, *Aircraft and space vehicles*, Subcommittee SC 4, *Aerospace fastener systems*. [ISO 7481](https://standards.iso.org/standards/sist/06ee1358-5b02-4e15-9c5a-a24b19b505b1/iso-7481)

This third edition cancels and replaces the second edition (ISO 7481:2000), which has been technically revised.

The main changes are as follows:

- normative references have been updated and changed to undated;
- [Table 4](#) title error corrected;
- [Table 5](#) has been corrected;
- the footnote in [Table 5](#) has been added;
- the document has been editorially updated.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Aerospace — Nuts, self-locking, with maximum operating temperature less than or equal to 425 °C — Test methods

1 Scope

This document specifies test methods for metric self-locking nuts with MJ threads intended for use in aerospace construction at maximum operating temperatures less than or equal to 425 °C. It describes the test device and the method for each test.

It applies to self-locking nuts as defined above, provided that the relevant documents (dimensional standard, drawing, procurement specification, etc.) refer to this document.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 691, *Assembly tools for screws and nuts — Wrench and socket openings — Tolerances for general use*

ISO 5855-2, *Aerospace — MJ threads — Part 2: Limit dimensions for bolts and nuts*

ISO 6507-1, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 6508-1, *Metallic materials — Rockwell hardness test — Part 1: Test method (scales A, B, C, D, E, F, G, H, K, N, T)*

ISO 7403, *Aerospace — Spline drives — Wrenching configuration — Metric series*

<https://standards.iteh.ai/catalog/standards/sist/06ee1358-5b12-4e15-9c5a-a24b19b505b1/iso-7481>

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Inspections and tests

4.1 Hardness test

4.1.1 Procedure

The choice depends on the configuration of the nut and available equipment. The authorized procedures shall meet the following requirements:

- Rockwell hardness in accordance with ISO 6508-1;
- Vickers hardness HV 5 to HV 100 in accordance with ISO 6507-1;
- Rockwell superficial hardness in accordance with ISO 6508-1;

— microhardness.

4.1.2 Method

This test shall be carried out at ambient temperature.

The measurement zone (bearing surface, across flats, underside of anchor nut lugs, etc.) shall correspond to the following conditions:

- a) thickness at least equal to 10 times the penetration depth;
- b) parallelism with respect to bearing surface not greater than 3°.

Should this not be possible, carry out this test on a cut section after moulding the nut into thermosetting resin.

Remove all possible coating (protection, lubrication, paint, etc.) in the measurement zone. Align the bearing surface to obtain the required relationship. These two operations shall not generate any heat liable to modify the characteristics of the material constituting the nut being tested.

Carry out the test and then check conformity with the requirements of the dimensional standard or drawing.

Nuts subjected to this test shall not be used again.

4.2 Bearing surface squareness test


4.2.1 Test device

The test device is illustrated in [Figure 1](#).

The test device shall include the following elements:

- a) a threaded mandrel with end in accordance with ISO 5855-2, with the exception of the pitch diameter, which shall be in accordance with the values specified in [Table 5](#) for the maximum mandrel;
- b) a collar sliding on the plain portion of the threaded mandrel whose external diameter B is at least equal to reference dimension A for type I, II and V nuts in [Figure 2](#) and equal to reference dimension A for type III and IV nuts in [Figure 2](#);
- c) an appropriate feeler gauge.


For clinch nuts, the sliding collar shall have a counterbore to accommodate the shank.

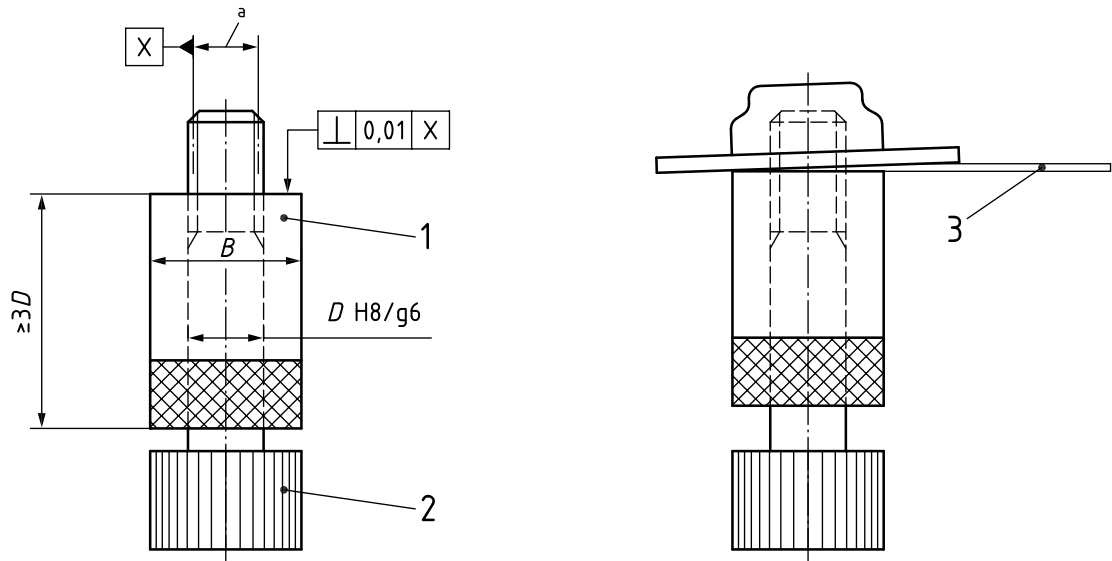

Key

- 1 sliding collar
- 2 threaded mandrel
- 3 feeler gauge
- a Pitch diameter.

Figure 1 — Test device bearing surface squareness

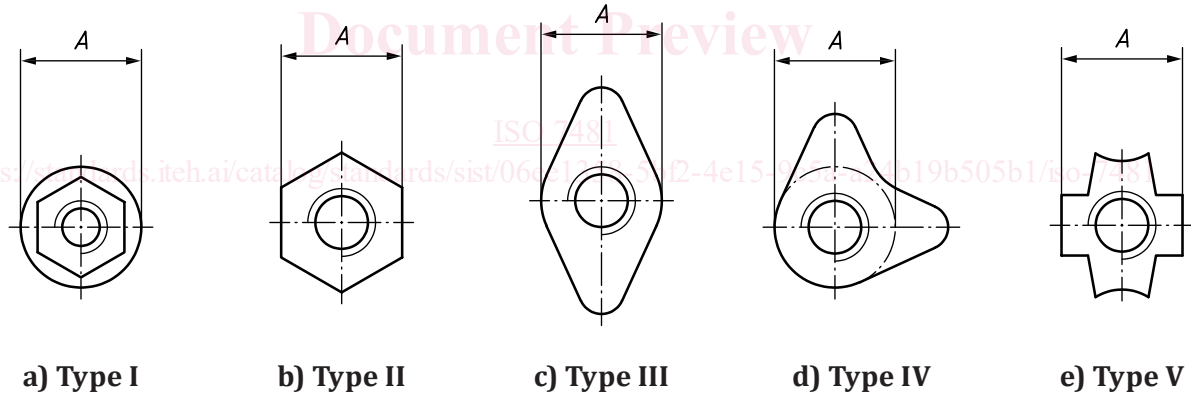

NOTE Types I and II are wrench nuts and clinch nuts. Types III and IV are fixed anchor nuts. Type V are floating anchor nuts and gang channel nuts.

Figure 2 — Types of internally threaded fasteners

4.2.2 Method

The test shall be carried out at ambient temperature.

For floating nuts, extract the nut from the cage or channel.

Lubricate the mandrel and nut (or threaded part) threads as stated in [Table 1](#) (if necessary). Screw, with or without a wrench, the threaded mandrel into the nut or threaded part up to a minimum engagement of three turns.

Move the collar into contact with the bearing surface.

Evaluate the out-of-squareness by means of a feeler gauge whose thickness corresponds to the permissible squareness error permitted by the dimensional standard, the drawing or the procurement specification.

4.3 Axial load test

4.3.1 Test device

The test device is illustrated in [Figure 3](#).

The test device includes the following elements:

- a) a bearing plate in steel, heat-treated to a hardness ≥ 40 HRC;
- b) a conical washer (for testing countersunk nuts);
- c) a bolt with characteristics as follows:
 - 1) threads: in accordance with ISO 5855-2;
 - 2) tensile strength class: greater than that of the nut under test;
 - 3) material and coating: no specific requirement.

4.3.2 Method

4.3.2.1 General

The axial load is transmitted to the nut by the bolt, the nut resting on the bearing plate. For countersunk nuts, a conical washer is interposed.

4.3.2.2 80 % test


This test shall be carried out at ambient temperature.

Lubricate the bolt and nut threads as stated in [Table 1](#) (if necessary). Assemble the bearing plate and, if used in conjunction with the nut, the conical washer onto the bolt. Assemble the nut and measure the locking torque when the protrusion is two pitches minimum (including chamfer).

Position the assembly on the tensile machine. Apply the load slowly and progressively. Reduce the load slowly and progressively when the value quoted in the procurement specification has been reached.

Remove the assembly from the tensile machine. Unscrew the nut a half-turn and cease movement, then again unscrew and measure the breakaway torque.

Remove the nut, then submit it to a visual examination and, if necessary, an examination at a magnification of $\times 10$ after sectioning, to check conformity with the requirements of the procurement specification.

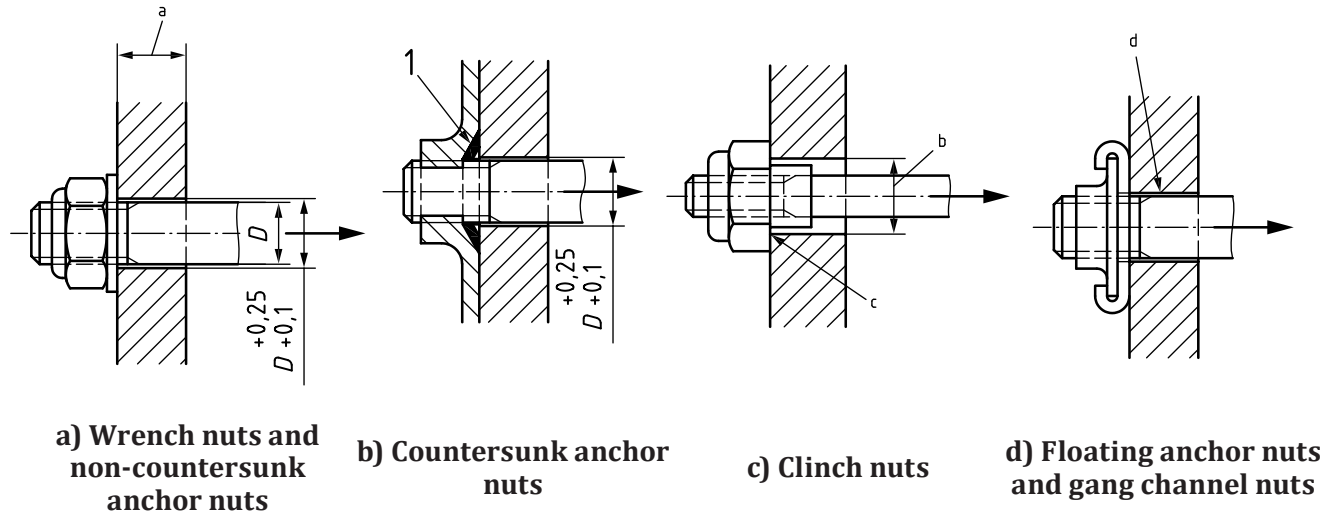**Key**

- 1 washer to fit countersink
- a Thickness $\geq D$.
- b Maximum shank diameter $\begin{matrix} +0,25 \\ +0,10 \end{matrix}$.
- c Chamfer to suit the nut radius.
- d The hole shall allow the specified float.

Figure 3 — Test set-up axial load test**Table 1 — Test bolt and lubrication, example**

| Locking | Nut to be tested | | Test bolt | | Additional lubrication |
|----------------|----------------------|----------------------------|-----------------|---------|------------------------|
| | Material | Coating | Material | Coating | |
| Plastic insert | Any | Any | Alloy steel | Cadmium | None |
| Metallic | Steel or alloy steel | Any | Alloy steel | Cadmium | None |
| | Stainless steel | Silver or MoS ₂ | Stainless steel | None | Synthetic oil |
| | | None | Stainless steel | Silver | |

4.3.2.3 100 % test

This test shall be carried out at ambient temperature.

If the test includes a heat soak, then heat the nut and maintain it at the temperature quoted in the procurement specification. Take the nut from the oven and allow it to cool slowly to ambient temperature, then proceed as follows.

Lubricate the bolt and nut threads as specified in [Table 1](#) (if necessary), assemble the bearing plate and, if required, the conical washer, onto the bolt. Assemble the nut with a protrusion of two bolt pitches minimum (including chamfer).

Position the assembly on the tensile machine and apply the load slowly and progressively. Reduce the load slowly and progressively when the value quoted in the procurement specification has been reached.

Remove the assembly from the tensile machine. Remove the nut, then submit it to a visual examination and, if necessary, an examination at a magnification of $\times 10$ after sectioning to check conformity with the requirements of the procurement specification.

Nuts subjected to this test shall not be used again.

4.4 Wrenching feature test

4.4.1 General

This test applies only to wrenchable nuts.

4.4.2 Test device

The test device is illustrated in [Figure 4](#).


The test device includes the following elements:

- a) a block of steel, heat-treated to a hardness of ≥ 40 HRC;
- b) a bolt with characteristics as follows:
 - 1) threads: in accordance with ISO 5855-2;
 - 2) tensile strength class: no specific requirement;
 - 3) material and coating: no specific requirement.

NOTE Any other device which prevents the rotation of the nut and allows the specified torque to be applied is acceptable. For instance:

- nut welded on a block of the same material, the assembly being heat-treated to the correct level;
- nuts mounted in counter-rotation on a threaded rod of strength class appropriate to hold the required torques without deformation;
- nut mounted on a bolt of strength class appropriate to hold the required torques without deformation as a spacer is placed between the nut and the bolt head.

ISO 7481
<https://standards.iteh.ai/catalog/standards/sist/06ee1358-5bf2-4e15-9c5a-d9b505b1/iso-7481>

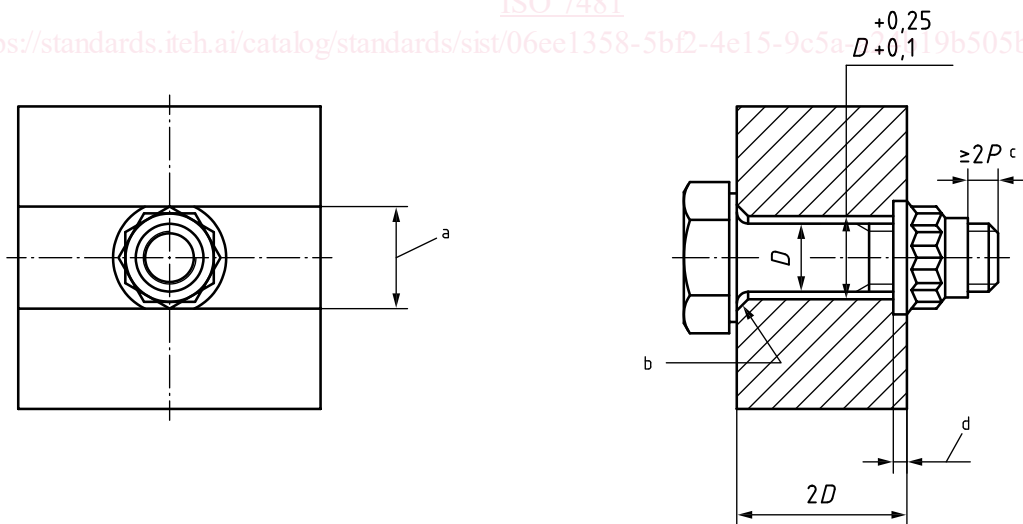

- a Width of slot equal to diameter of circle circumscribing the wrenching feature.
- b Chamfer to suit underhead radius.
- c Including chamfer, where P is the pitch.
- d Depth of slot equal to flange height of nut under test.

Figure 4 — Test set-up for wrenching feature test