



Designation: D3434 – 00 (Reapproved 2013)

Standard Test Method for Multiple-Cycle Accelerated Aging Test (Automatic Boil Test) for Exterior Wet Use Wood Adhesives¹

This standard is issued under the fixed designation D3434; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers a procedure for testing the durability of wood adhesives that may be suitable for exterior (wet use) exposure conditions. The possible use of adhesives suitable for evaluation includes, but is not limited to those used for laminating large members, manufacturing plywood, or fabricating wood joints such as finger or scarf joints. This practice is not suitable for interior type glues.^{2,3}

1.2 The test does not evaluate for any biological effects.

1.3 The test subjects specimens to a large number of alternate boil/dry cycles.

1.4 The values stated in SI units are to be regarded as the standard. The inch-pound units in parentheses are provided for information only.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*⁴

[D906 Test Method for Strength Properties of Adhesives in Plywood Type Construction in Shear by Tension Loading](#)

[D907 Terminology of Adhesives](#)

[D2339 Test Method for Strength Properties of Adhesives in Two-Ply Wood Construction in Shear by Tension Loading](#)

[D4422 Test Method for Ash in Analysis of Petroleum Coke](#)

¹ This test method is under the jurisdiction of ASTM Committee D14 on Adhesives and is the direct responsibility of Subcommittee D14.30 on Wood Adhesives.

Current edition approved May 1, 2013. Published May 2013. Originally approved in 1975. Last previous edition approved in 2006 as D3434 – 00 (2006). DOI: 10.1520/D3434-00R13.

² Walser and Colbeck, "Bond-Degrade Accelerating Machine Helps Predict Bond Life," *Adhesives Age*, Vol 10(11), November 1967, pp. 33–35.

³ Kreibich and Freeman, "Development and Design of an Accelerated Boil Machine," *Forest Products Journal*, Vol 18, No. 12, December 1968.

⁴ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process](#)

3. Terminology

3.1 *Definitions*—Definitions of terms in this test method may be found in Terminology [D907](#).

4. Summary of Test Method

4.1 The lumber is selected, adhesive obtained, and test specimens prepared.

4.2 The specimens are subjected to the required number of boil/dry cycles.

4.3 The specimens are withdrawn from the test at the required periodic intervals.

4.4 The designated number of specimens are tested in tensile shear at the end of the specified number of boil/dry cycles.

4.5 Plot shear strength, kPa (psi), or percent of wood failure, or both, versus the number of boil/dry cycles to which the specimens have been subjected.

4.6 The graph is compared for the test adhesives. Because of the variables occurring in wood, a known performance adhesive control should be run for each test set being evaluated.

5. Significance and Use

5.1 This test method is intended to differentiate between the exterior durability of two or more adhesives. At present, this is done by comparing the adhesives as described in 4.5 and 4.6 rather than by assigning absolute numerical values for durability performance.

5.2 The test method as described is for comparing potential long-term durability rather than for use as a quality control procedure. This makes it suitable for research, adhesive evaluation, process evaluation, and product design. A modification could be made, that is, shorten the number of cycles used so the test method would be suitable for quality control in production mills. The results obtained for a particular adhesive can be used to show how many cycles are required for a mill quality control test of that adhesive.

5.3 The test method assumes that boil/dry cycling is an adequate and useful accelerated aging technique. Evaluation of long-term durability of adhesives in wood joints under severe service conditions, including extended exterior exposure, is a complex field, and no entirely reliable short-term test is known to ensure that a new type of adhesive system will satisfactorily resist all of the chemical, moisture, microorganism, and solvent effects that such severe service may involve. Except for effects of microorganisms and other similar biological influences, this test method has proven very useful for comparison purposes to distinguish between adhesive systems of different degree of durability to the usual temperature, moisture, and cyclic moisture conditions. It has proven very useful to distinguish between bondlines, made with adhesives of proven chemical and biological durability, that were properly used in production to resist the mechanical and moisture effects that such joints must withstand in severe service over extended periods of exposure. It does not, in itself, assure that new types of adhesives will always withstand actual exterior or other severe service.

6. Apparatus

6.1 Due to the large number of boil/dry cycles involved, an automated piece of test equipment is required. A schematic diagram of one system found suitable is shown in Fig. 1; a photograph in Fig. 2. The equipment shown automatically boils and dries the test specimens as required.

6.2 A tensile shear tool is required such as described in Test Method D2339.

7. Test Specimens

7.1 Wood Substrate:

7.1.1 *For Lumber Laminating Adhesives*—Condition the wood at $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and a relative humidity of 50 to 70 % (preferably 65 %) until a moisture content of 8 to 14 % (preferably 9 to 12 %) has been attained. Freshly surface both sides of each lamination before bonding with $6.3 \pm 0.25\text{-mm}$ ($0.25 \pm 0.01\text{-in}$) thick lumber. Since adhesives join materials by surface attachment, care must be taken to ensure a uniform reproducible surface representative of actual construction. Typical surfaces include sawed, planed, sanded, and skived. Detailed surface preparation procedures used must be included in the report (see 10.1).

7.1.1.1 Specimen moisture content (MC) conditions called for in this test method should be checked in accordance with Test Methods D4422.

7.1.2 *For Plywood Adhesives*—Prepare the test specimen in accordance with Test Method D906.

7.1.3 *Miscellaneous Specimens*—Other wood joints, such as finger or scarf joints, or other wood-based materials, such as particleboard, hardboard, or insulating board, may also be evaluated.

7.2 *Adhesive*—Store the adhesive or its components at the manufacturer’s recommended conditions.

7.3 Bonding Procedure:

7.3.1 It has been found convenient to fabricate large two- and three-ply blocks, which are subsequently cut into a number of test specimens. A 140 by 140-mm ($5\frac{1}{2}$ by $5\frac{1}{2}$ -in) block will yield four specimens and one 140 by 200-mm ($5\frac{1}{2}$ by 8-in) block will yield eight specimens.

7.3.2 Mix and apply the adhesive(s) to the surface(s) to be bonded in accordance with the manufacturer’s instructions. If the processes are being evaluated, prepare specimens reflecting the limits of the typical process conditions.

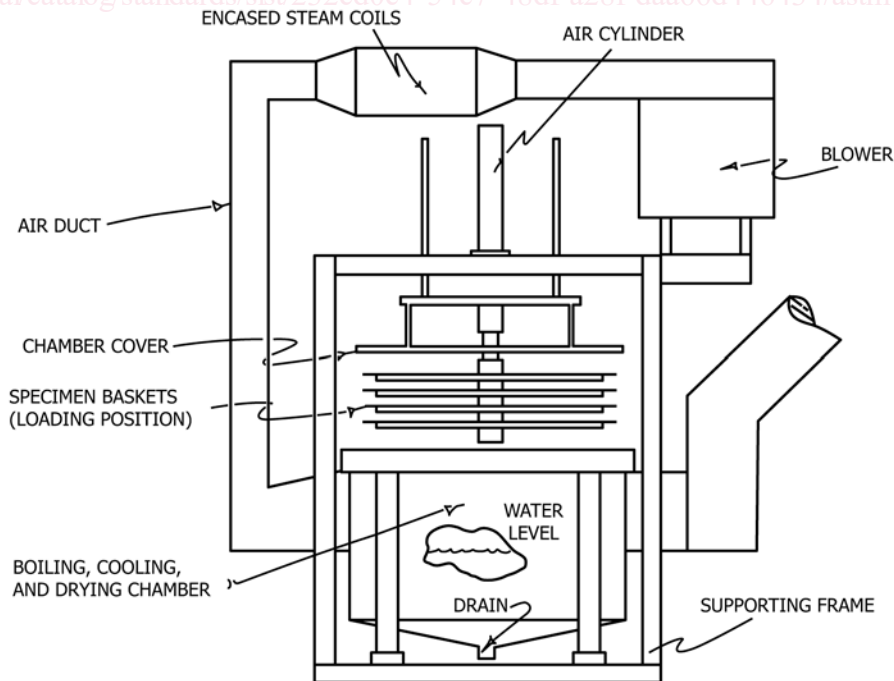


FIG. 1 Automatic Boil Machine