



**SLOVENSKI STANDARD**  
**SIST EN ISO 9856:1997**

**01-marec-1997**

---

**Trakovi tračnih transporterjev - Določitev modula elastičnosti (ISO 9856:1989)**

Conveyor belts - Determination of elastic modulus (ISO 9856:1989)

Fördergurte - Bestimmung des Elastizitätsmoduls (ISO 9856:1989)

Courroies transporteuses - Détermination du module d'élasticité (ISO 9856:1989)

**Ta slovenski standard je istoveten z: EN ISO 9856:1995**

[SIST EN ISO 9856:1997](https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997)

<https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997>

**ICS:**

53.040.20      Deli za transporterje      Components for conveyors

**SIST EN ISO 9856:1997**

**en**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 9856:1997

<https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997>

EUROPEAN STANDARD

EN ISO 9856

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 1995

ICS 53.040.20

Descriptors: Conveyors, belt conveyors, conveyor belts, tests, mechanical tests, tension tests, determination, modulus of elasticity.

English version

## Conveyor belts - Determination of elastic modulus (ISO 9856:1989)

Courroies transporteuses Détermination du module d'élasticité (ISO 9856:1989) Fördergurte - Bestimmung des Elastizitätsmoduls (ISO 9856:1989)

**ITeH STANDARD PREVIEW**  
(standards.iteh.ai)

SIST EN ISO 9856:1997

<https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997>

This European Standard was approved by CEN on 1995-03-22. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

# CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Page 2  
EN ISO 9856:1995

## Foreword

The text of the International Standard from ISO/TC 41 "Pulleys and belts (including veebelts)" of the International Organization for Standardization (ISO) has been taken over as a European Standard by the Technical Committee CEN/TC 188 "Conveyor belts".

This European Standard is not applicable for light conveyor belts as in EN 873 "Light conveyor belts - Principal characteristics and applications".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 1996, and conflicting national standards shall be withdrawn at the latest by April 1996.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EC Directive(s).

According to the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

**(standards.iteh.ai)**

### Endorsement notice

[SIST EN ISO 9856:1997](https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997)

[https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-](https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997)

[94e74d0c7c3b/sist-en-iso-9856-1997](https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997)

The text of the International Standard ISO 9856:1989 has been approved by CEN as a European Standard without any modification.



# INTERNATIONAL STANDARD

**ISO  
9856**

First edition  
1989-07-01

---

---

## Conveyor belts — Determination of elastic modulus

*Courroies transporteuses — Détermination du module d'élasticité*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN ISO 9856:1997

<https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997>



Reference number  
ISO 9856 : 1989 (E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 9856 was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*.

[SIST EN ISO 9856:1997](https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997)

Annex A of this International Standard is for information only.

© ISO 1989

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

# Conveyor belts — Determination of elastic modulus

## 1 Scope

This International Standard specifies a method for determining the elastic modulus of a conveyor belt.

NOTE — The elastic modulus is notably used in the calculation of transition distances in accordance with ISO 5293.

## 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards listed below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 282 : 1975, *Conveyor belts — Sampling*.

ISO 283 : 1980, *Full thickness tensile strength and elongation of conveyor belts — Specifications and method of test*.

ISO 471 : 1983, *Rubber — Standard temperatures, humidities and times for the conditioning and testing of test pieces*.

## 3 Principle

Application of a sinusoidal stress between 2 % and 10 % of the minimum breaking load on a test piece cut from the full thickness of the belt in the longitudinal direction, then recording of at least 200 load cycles of the graph giving the load as a function of elongation, and, from this graph, determination by calculation of the elastic modulus.

## 4 Apparatus

**4.1 Dynamic tensile testing machine**, capable of applying stress of up to 10 % of the minimum breaking load determined in accordance with ISO 283. The machine shall be capable of applying a cyclic load to the test pieces between 2 % and 10 % of the minimum breaking load.

**4.2 Extensometer**, with a measuring length of at least 100 mm and accurate to at least 0,1 mm.

**4.3 Recording device**, to record the curve of tensile stress as a function of elongation.

## 5 Test pieces

### 5.1 Shape and dimensions

The test piece cut from the full thickness of the belt in the longitudinal direction shall be rectangular. Its width shall be 50 mm and its length at least 300 mm plus twice the necessary clamping zone length.

### 5.2 Number and conditioning of test pieces

From the same sample obtained in accordance with ISO 282, take the three following test pieces according to the requirements of 5.1:

- two test pieces taken at least 50 mm from the edge of the belt;
- one test piece taken in the middle of the belt.

They shall be taken at least five days after manufacture.

### 5.3 Preparation and conditioning

Remove the covers from the test piece so that the thickness of the remaining cover is between 0,5 mm and 1 mm (see ISO 283 : 1980, 3.3.4).

Unless specified otherwise (to be noted in the test report), condition the test piece for three days at  $23\text{ °C} \pm 2\text{ °C}$  and a relative humidity of  $50\% \pm 5\%$ , in accordance with ISO 471.

## 6 Procedure

Carry out the test on each test piece defined in 5.2. Place the ends of the test piece between the jaws of the dynamic tensile testing machine (4.1). The free length between the jaws shall be at least 300 mm.

**ISO 9856 : 1989 (E)**

Stress the test piece with an initial tensile stress (dead load) of 0,5 % of the specified minimum breaking strength of the belt in accordance with the method specified in ISO 283.

Position the two grids of the extensometer (4.2) on the axis of the test piece with a separation of at least 100 mm. Then set the recorder (4.3) to zero elongation.

Load the test piece approximately sinusoidally with a force between 2 % and 10 % of the specified minimum breaking strength of the belt and at a frequency of 0,1 Hz.

Record at least the first and the 200th load cycle (see figure 1).

From the graphs obtained (see figure 1), record the value  $\Delta F$  in newtons per millimetre of test piece width and read the value  $\Delta l$  in millimetres.

**7 Expression of results**

The elastic modulus,  $M$ , of the belt, expressed in newtons per millimetre of test piece width, is given by the formula

$$M = \frac{\Delta F}{\varepsilon}$$

where

$\Delta F$  is the variation of the amplitude of the load between 2 % and 10 % of the minimum breaking strength of the test piece, expressed in newtons per millimetre of width;

$\varepsilon$  is the relative elongation.

The relative elongation,  $\varepsilon$ , is given by the formula

$$\varepsilon = \frac{\Delta l}{l_0}$$

where

$\Delta l$  is the elastic elongation, expressed in millimetres;

$l_0$  is the initial length, expressed in millimetres, of the test piece.

Calculate the arithmetic mean of the values found and take as the result the number rounded to the first decimal place.

**8 Test report**

The test report shall contain the following information :

- a) identification of the belt tested;
- b) reference to this International Standard;
- c) results of the test, individual values and mean values;
- d) conditioning period;
- e) temperature and relative humidity during the test;
- f) any deviation from this International Standard or from the International Standards to which reference is made, or regarded as optional.

<https://standards.iteh.ai/catalog/standards/sist/e65d01f9-f804-4536-a481-94e74d0c7c3b/sist-en-iso-9856-1997>



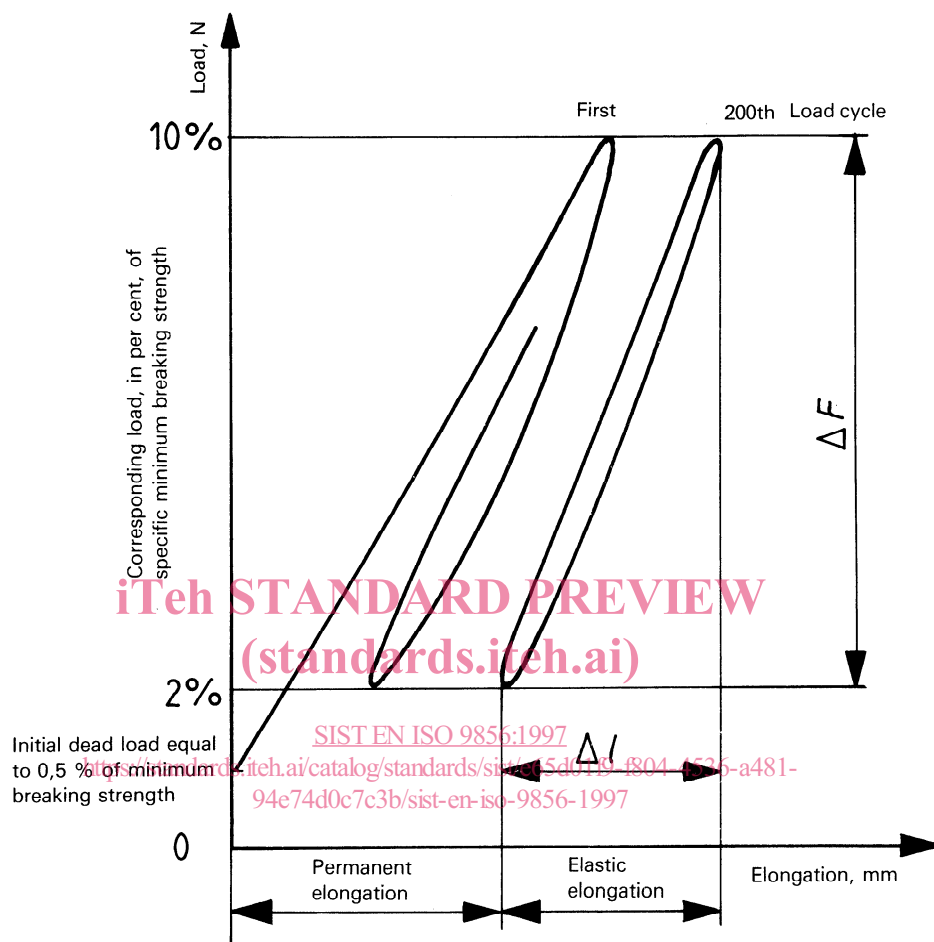


Figure 1 — Graph of the variation of amplitude of the load as a function of elongation