



SLOVENSKI STANDARD
SIST EN 1723:1999

01-december-1999

BUdfUj Y'nU_cbljbi jfbj'fUbgdcfh!'@A _j'fU_cj j'fU b] \ 'fUbgdcfHf'Yj '!DcglcdY_
nUi [cHj `Ub'Yi gH'YbY[U'YUgh] bY[Ua cXi `U

Light conveyor belts - Method of test for the determination of the relaxed elastic modulus

Leichte Fördergurte - Prüfverfahren zur Bestimmung des relaxierten Elastizitätsmoduls

Courroies transporteuses légères - Méthode d'essai pour la détermination du module
d'élasticité relaxé

ITeH STANDARD PREVIEW
(standards.iteh.ai)

Ta slovenski standard je istoveten z: ^{SIST EN 1723:1999} **EN 1723:1999**

<https://standards.iteh.ai/catalog/standards/sist/91b9d838-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999>

ICS:

53.040.20 Deli za transporterje Components for conveyors

SIST EN 1723:1999 en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 1723:1999

<https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 1723

August 1999

ICS 53.040.20

English version

Light conveyor belts - Method of test for the determination of the relaxed elastic modulus

Courroies transporteuses légères - Méthode d'essai pour la détermination du module d'élasticité relaxé

Leichte Fördergurte - Prüfverfahren zur Bestimmung des relaxierten Elastizitätsmoduls

This European Standard was approved by CEN on 8 January 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN 1723:1999](https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999)

<https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999>



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents

	Page
Foreword	3
Introduction	3
1 Scope	4
2 Normative references	4
3 Definitions and symbols	4
4 Principle	5
5 Apparatus	5
6 Test piece	5
7 Procedure	7
8 Calculation and expression of results	8
9 Test report	10
Annex A (informative) Bibliography	11

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 1723:1999

<https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999>



REPUBLIKA SLOVENIJA
MINISTRSTVO ZA VEŠTOVARSTVO IN TEHNOLOGIJO
Uradno prečiščeno besedilo
ANALIZA

1999 - 01 -

.....7018
KRAJINA ZA VEŠTOVARSTVO IN TEHNOLOGIJO

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 188 "Conveyor belts", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by February 2000, and conflicting national standards shall be withdrawn at the latest by February 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Introduction

Many applications for light conveyor belts require that the belt is initially tensioned and there is no subsequent change in belt length by adjustment of any rollers. In such cases the tensioning force in the belt changes throughout the life of the belt because of two effects: both permanent stretch and relaxation of the belt changing its real elastic modulus. It is vital to have a means of establishing the way in which the tensioning forces will change and this test applies a cyclic stretching between two defined states of elongation over a large number of cycles. It has been found experimentally that the tensioning force drops in an exponential way. It is possible to measure the tensioning force and then to calculate what is herein defined as the 'relaxed elastic modulus'. It is important to note that this is not a true elastic modulus, because it includes an element of permanent stretch but, except in cases where the permanent stretch is relatively large, it is a measure of great practical value in determining final tensioning forces. This standard is designed to meet the requirements for such applications.

1 Scope

This European Standard specifies a test method for the determination of the relaxed elastic modulus of light conveyor belts as defined by EN 873 or other conveyor belts where ISO 9856 is unsuitable.

2 Normative references

This European Standard incorporates by dated or undated references, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 873	Light conveyor belts - Principal characteristics and applications
EN 10002-2	Metallic materials - Tensile testing - Part 2: Verification of the force measuring system of the tensile testing machines
ISO 471	Rubber - Temperatures, humidities and times for conditioning and testing
ISO 554 Specifications	Standard atmospheres for conditioning and/or testing -
ISO 7500-1	Metallic materials - Verification of static uniaxial testing machines - Part 1: Tensile testing machines
ISO 9856	Conveyor belts - Determination of elastic modulus

3 Definitions and symbols

For the purposes of this standard the following apply :

3.1 elastic modulus.

1) (in conveyor belt technology). A force per unit of width of a conveyor belt . It is expressed in newtons per millimetre width of belt and is represented in ISO 9856 by the symbol *M*.

Note : This definition of the term deviates from that normally used in engineering which is expressed in units of stress, i.e. a force per unit of cross section and is represented by the symbol *E* ; (see for example ISO 527-4).

2) (in light conveyor belt technology). The force in newtons per unit of width required to extend a representative test piece of light conveyor belting by 1% of its original length. The force is represented by the symbol *k* and consequently the **elastic modulus** is represented by the symbol *k*_{1%}. This value is also called the 'tensile force for 1 % elongation per unit of width' or '*k*_{1%} value'. It is expressed in newtons per millimeter.

Note : In EN 10002-1:1991, the symbol *k* is used to represent the coefficient of

proportionality.

3.2 relaxed elastic modulus. Used in light conveyor belt technology to describe the elastic modulus of a light conveyor belt after being cycled between predetermined limits of extension for 500 cycles.

Note : The $k_{1\%}$ value of a new conveyor belt is higher than that of a used conveyor belt in which relaxation has taken place in service. The relaxation takes place following an exponential function.

The following symbols are also used in this standard:

F_A , F_B are the maximum and minimum tensile forces respectively in the test piece in newtons;

F'_A , F'_B are the specific values of F_A , F_B referred to the width of the test piece in newtons per millimetre;

a is the value in newtons per millimetre of $k_{1\%}$ for $z = 1$;

b is the manufactured width of the conveyor belt in millimetres;
[in equations (4) and (5), b is the slope of the straight line];

r is the correlation coefficient ;
iTeh STANDARD PREVIEW
(standards.iteh.ai)

x is the variable in the equation of the straight line ;

y is the value of the equation of the straight line ;
SIST EN 1723:1999
<https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67f593754/sist-en-1723-1999>

z is the number of cyclic elongations.

4 Principle

A test piece, cut from the full thickness of the conveyor belt in the longitudinal direction, is exposed to a cyclic elongation between two defined limits and the tensile force is recorded as a function of the number of cycles. From that graph, the relaxed elastic modulus is determined by calculation through a logarithmic regression.

5 Apparatus


Tensile testing machine, capable of applying load suitable for the strength of the test piece and with a force measuring system in accordance with EN 10002-2, Class of machine 3 or better (e.g. Class of machine 2) as well as capable of applying the load in displacement-controlled cycles of ± 5 mm and with a frequency of 0.5 Hz (this frequency being realizable also with older, mechanically controlled dynamometers).

6 Test piece

6.1 Shape, dimensions, number and selection

Cut from the full thickness of the conveyor belt in the longitudinal direction five rectangular test pieces each ($50 \pm 0,5$) mm wide \times (500 plus twice the length

necessary for clamping in the jaws) mm long. Select the test pieces from the conveyor belt at places as shown in figure 1.

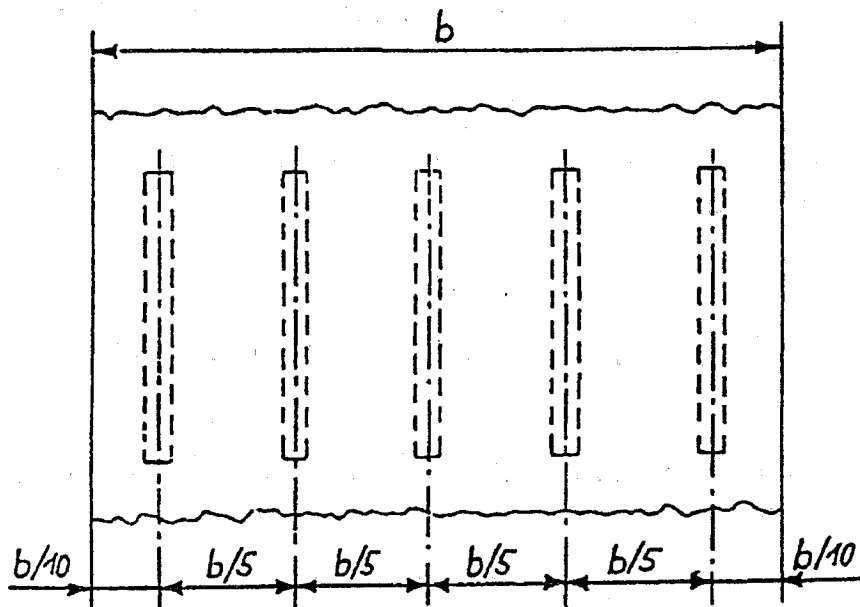

b = manufactured width of the conveyor belt

Figure 1 - Distribution of test piece selection

SIST EN 1723:1999

6.2 Conditioning

<https://standards.iteh.ai/catalog/standards/sist/91b9d858-d0c9-47ac-a7f6-cd67ff593754/sist-en-1723-1999>

The test pieces shall be conditioned at $(23 \pm 2)^\circ \text{C}$ and a relative humidity of $(50 \pm 5) \%$ in accordance with ISO 471 and ISO 554.

The climatizing time shall be:

For light conveyor belts containing materials with a low absorption of moisture, e.g. polyester, 24 h.

For light conveyor belts containing materials with a high absorption of moisture e.g. cotton or polyamide, 48 h.

7 Procedure

The test pieces shall not be tested earlier than five days after manufacture of the conveyor belt.

The test shall be carried out with each of the test pieces defined in 6.1

Place the ends of the test piece between the jaws of the tensile testing machine in such a way that the test piece is straight without using force. The free length between the jaws shall be $500 \text{ mm} \pm 1 \text{ mm}$. There shall be no slippage of the test piece in the jaws during the test.

NOTE 1: Slippage can be minimized by rubbing rosin on the portion of the test piece that will be in the jaws, removing any excess rosin and enclosing both sides of the rosin-coated test piece with coarse emery cloth. The emery cloth should be folded over the ends of the test piece with the coarse side of the cloth next to the rosin-coated surfaces.

Elongate the test piece cyclically between 1 % and 2 % (5 mm and 10 mm) at a frequency of 0,5 Hz.

NOTE 2: The same effect will be realized if the test piece is given an initial elongation of 1,5 %, corresponding to 7,5 mm, and a cyclic alteration of the elongation of $\pm 0,5 \%$, corresponding to $\pm 2,5 \text{ mm}$, is superposed at the same frequency. In both cases the average speed of deformation in the test piece will be 5 mm/s (= 300 mm/min).

In cases of conveyor belts containing reinforcing elements with a high elastic modulus, (e.g. with reinforcing elements of Aramid threads), the cyclic elongation of the test piece shall take place between 0,5 % and 1 % (2,5 mm and 5 mm) at the same frequency of 0,5 Hz.

Record the tensile force during 500 cyclic elongations as a function of the number of cycles. At the end of the test measure the permanent elongation by reducing the tensioning force to zero, and measuring the distance between the jaws. If this elongation is equal to or exceeds 1 % of the initial length then this test is unsuitable for such a belt type and ISO 9856 shall be used instead.