



**SLOVENSKI STANDARD**  
**SIST EN ISO 15236-4:2004**  
**01-september-2004**

---

Steel cord conveyor belts - Part 4: Vulcanized belt joints (ISO 15236-4:2004)

Stahlseil-Fördergurte - Teil 4: Vulkanisierte Gurtverbindungen (ISO 15236-4:2004)

Courroies transporteuses à câbles d'acier - Partie 4: Jonctions vulcanisées des courroies (ISO 15236-4:2004)

**STANDARD PREVIEW**  
**(standards.iteh.ai)**

Ta slovenski standard je istoveten z: **EN ISO 15236-4:2004**

SIST EN ISO 15236-4:2004  
<https://standards.iteh.ai/catalog/standards/sist/2c019abd-b8d6-488a-ad4f-af293cb2049/sist-en-iso-15236-4-2004>

---

**ICS:**

53.040.20      Deli za transporterje      Components for conveyors

**SIST EN ISO 15236-4:2004**      en

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN ISO 15236-4:2004](https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004)

<https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

EN ISO 15236-4

June 2004

ICS 53.040.20

English version

Steel cord conveyor belts - Part 4: Vulcanized belt joints (ISO  
15236-4:2004)

Courroies transporteuses à câbles d'acier - Partie 4:  
Jonctions vulcanisées des courroies (ISO 15236-4:2004)

Stahlseil-Fördergurte - Teil 4: Vulkanisierte  
Gurtverbindungen (ISO 15236-4:2004)

This European Standard was approved by CEN on 2 February 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

[SIST EN ISO 15236-4:2004](https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004)

<https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## EN ISO 15236-4:2004 (E)

<b>Contents</b>		<b>Page</b>
	Foreword .....	3
1	Scope.....	4
2	Terms and definitions .....	4
3	Symbols and units .....	4
4	Types of joints .....	4
5	Joint material .....	9
6	Making the joint.....	9
7	Marking the joint.....	10

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN ISO 15236-4:2004](https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004)  
<https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004>

## Foreword

This document (EN ISO 15236-4:2004) has been prepared by Technical Committee CEN/TC 188 "Conveyor belts", the secretariat of which is held by BSI, in collaboration with Technical Committee ISO/TC 41 "Pulleys and belts (including veebelts)".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2004, and conflicting national standards shall be withdrawn at the latest by December 2004.

EN ISO 15236 will consist of the following parts, under the general title *Steel cord conveyor belts*:

- *Part 1: Design, dimensions and mechanical requirements for conveyor belts for general use*
- *Part 2: Preferred belt types*
- *Part 3: Special safety requirements for belts for use in underground applications*
- *Part 4: Vulcanized belt joints*
- *Part 5: Marking*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

**iTeh STANDARD PREVIEW**  
Standards Ireland  
<https://standards.iee.ie/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004>

## EN ISO 15236-4:2004 (E)

## 1 Scope

This part of EN ISO 15236 specifies design, dimensions, requirements and marking of vulcanized joints for steel cord conveyor belts.

## 2 Terms and definitions

For the purposes of this European Standard, the following term and definition applies.

### vulcanized joint

area within which the cords from two belt lengths are joined and vulcanized through the surrounding rubber

## 3 Symbols and units

For the purposes of this European Standard, the symbols and units given in Table 1 apply.

Table 1 — Symbols and units

Symbol	Explanation	Unit
$d$	Cord diameter	mm
$K_N$	Nominal breaking strength of the belt	N/mm
$K_{Nred}$	Reduced breaking strength of the joint	N/mm
$l_p$	Length of cord end staggering area	mm
$l_q$	Length of the cord transition area	mm
$l_s$	Butt end clearance of the cord ends	mm
$n_{st}$	Number of steps	-
$SG$	Thickness of rubber between the cords in the joint	mm
$SG_{min}$	Minimum thickness of rubber between the cords in the joint	mm
$t$	Pitch	mm
$t_{min}$	Minimum spacing of the cord in the belt	mm

## 4 Types of joints

### 4.1 General

There are two types of joints differing in the way that forces are transferred from one belt length to the other:

- a) stepped joints;
  - where the forces are transferred by the rubber surrounding the cords.
- b) finger joints;

- where the forces are transferred by the rubber surrounding the cords and by the transverse reinforcements. For this type of joint, transverse reinforcement is required.

NOTE 1 Stepped joints offer the highest possible dynamic performance but require a high amount of time, knowledge, and care in their fabrication.

NOTE 2 For both types of joint, the physical properties of the rubber, especially the adhesion to the cords, are of utmost importance for the quality of the joint.

## 4.2 Stepped joints

### 4.2.1 Design principles

The cords of the belt ends to be joined are cut free from the cover rubber in the joint area. According to an agreed joint pattern, the cords are cut or separated in steps and cut free from the core rubber where necessary. The cords of both ends are merged into each other, embedded in bonding rubber and covered with cover rubber. After vulcanizing the joint will be able to transmit forces from one belt length to the other.

Unlike joints in conveyor belts with textile reinforcements for which the belt ends are generally cut in a bias, the ends of steel cord belts are cut either in a bias or perpendicular to the belt edge or in a bias for joining.

The number of steps, the length of the joint, the length of the steps and the joint pattern, i.e. the sequence of cuts of the cords, is either specified by the belt manufacturers or is given in company standards or national standards.

In addition to practical experience, the quality of a stepped joint can be evaluated by the calculation of the stresses of the rubber and the cords within the joint or by static and dynamic testing methods.

### 4.2.2 Rubber gap in the joint

The rubber filling the gap between two adjacent cords from different lengths is strained most and receives the highest stresses. A minimum distance  $SG_{\min}$  of the cords within the joint therefore has to be kept, as follows.

$$SG_{\min} \geq 1,2 + (0,1 \times d)$$

### 4.2.3 Butt end clearance

For cords meeting in the joint, the distance of the butt ends,  $l_s$ , shall be approximately  $4 \times d$  but not less than  $3 \times d$ .

### 4.2.4 Steps

Joints shall be carried out as 1-step, 2-step, 3-step, or 4-step joints, although higher numbers of steps are permitted.

According to the number of steps determined, the cords shall be cut in a sequence repeated throughout the belt width.

### 4.2.5 Interlaced stepped joint

It is characteristic of this type of joint that it contains a larger number of cords than the belt itself.

## EN ISO 15236-4:2004 (E)

On both sides of the joint, a length,  $l_q$ , shall be allowed for transition of the cords,  $l_q$  being a function of the cord diameter. Preferred transition lengths of the cords are given in Table 2. Transition lengths shall be not less than 16 x the cord diameter.

Table 2 — Transition length of cords

$D$ (mm)	$l_q$ (mm)
$\geq 6,0$	100
$>6,0 - \leq 8,5$	150
$>8,5 - \leq 10,0$	200
$>10,0 - \leq 11,5$	250

NOTE Cord end staggering where  $l_p$  is 50 mm is beneficial.


Part of a 2-step interlaced joint rectangular cut and cut on bias is shown in Figure 1.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

[SIST EN ISO 15236-4:2004](https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004)


<https://standards.iteh.ai/catalog/standards/sist/2c6f5abd-b8d6-488a-ad4f-afe293cb2049/sist-en-iso-15236-4-2004>



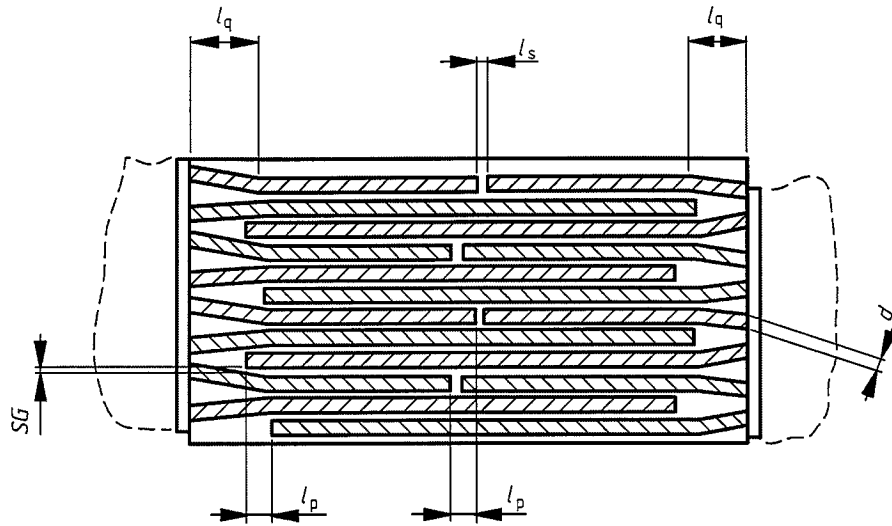

a) Rectangular cut

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

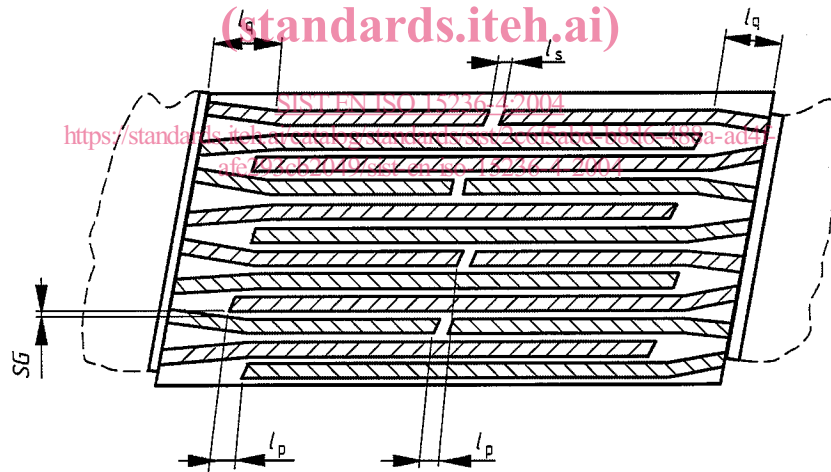

b) Cut on a bias

**Key**

See Table 1 for explanation of symbols

Figure 1 — Part of 2-step interlaced joint rectangular cut and cut on a bias