



International
Standard

ISO 21561-2

**Styrene-butadiene rubber
(SBR) — Determination of the
microstructure of solution-
polymerized SBR —**

Part 2:

**Fourier transform infrared
spectrometry (FTIR) with attenuated
total reflection (ATR) method**

Caoutchouc styrène-butadiène (SBR) — Détermination de la microstructure du SBR polymérisé en solution —

Partie 2: Méthode par spectrométrie infrarouge à transformée de Fourier (FTIR) à réflexion totale atténuée (RTA)

**Second edition
2024-08**

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO 21561-2:2024](https://standards.iteh.ai/catalog/standards/iso/820cf1b5-b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024)

<https://standards.iteh.ai/catalog/standards/iso/820cf1b5-b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
6 Calibration	2
6.1 FTIR.....	2
6.2 ATR.....	2
7 Sampling	2
8 Procedure for measuring ATR spectrum	3
9 Determination of the microstructure of butadiene and the styrene content	3
9.1 Measurement of the absorbance for each microstructure component.....	3
9.2 Calculation of microstructures.....	4
9.2.1 General.....	4
9.2.2 Base line correction of each absorbance peak.....	4
9.2.3 Ratio of absorbance.....	5
9.2.4 Second order terms.....	5
9.2.5 Styrene content and contents of three microstructure types of butadiene portion by regression formulae.....	5
9.2.6 Contents of three microstructure types relative to butadiene portion in the S-SBR.....	6
10 Precision	6
11 Test report	6
Annex A (informative) Precision results from an interlaboratory test programme	7
Annex B (informative) Acquisition of regression formulae for microstructure	10
Annex C (informative) Determination of microstructure by NMR spectrometry	12
Bibliography	15

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 3, *Raw materials (including latex) for use in the rubber industry*.

This second edition cancels and replaces the first edition (ISO 21561-2:2016), which has been technically revised.

The main changes are as follows:

- [ISO 21561-2:2024](https://standards.iteh.ai/catalog/standards/iso/820cflb5-b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024)
<https://standards.iteh.ai/catalog/standards/iso/820cflb5-b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024>
— [Clause 3](#) has been added;
- the units of styrene content and microstructure content of butadiene have been changed to SI units;
- the conditions of FTIR spectrum have been moved to [8.1](#);
- a description of regression formulae has been added in [9.2.5](#) and [9.2.6](#);
- in [Table A.1](#), one cell has been replaced by the correct value;
- in [C.3.1](#), the measurement conditions for ¹³C-NMR have been corrected.

A list of all parts in the ISO 21561 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Styrene-butadiene rubber (SBR) — Determination of the microstructure of solution-polymerized SBR —

Part 2: Fourier transform infrared spectrometry (FTIR) with attenuated total reflection (ATR) method

WARNING 1 — Persons using this document should be familiar with normal laboratory practice. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to determine the applicability of any other restrictions.

WARNING 2 — Certain procedures specified in this document can involve the use or generation of substances, or the generation of waste, that can constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.

1 Scope

This document specifies procedures for the quantitative determination of the microstructure of the butadiene portion and the content of styrene in solution-polymerized SBR (S-SBR) by Fourier transform infrared spectrometry (FTIR) with attenuated total reflection (ATR) method. The styrene content is expressed in mass fraction relative to the S-SBR. The contents of three microstructure types, i.e. vinyl, trans and cis, are expressed in mol fraction relative to the butadiene portion in the S-SBR. This method is only applicable to raw rubbers.

NOTE 1 Precision as shown in [Annex A](#) is not always possible to obtain for S-SBRs containing polystyrene block or styrene content more than 45 %.

NOTE 2 Only “vinyl”, “trans” and “cis”, are used in this document. However, the expression of vinyl, trans and cis mean as follows in general:

- vinyl: vinyl unit, vinyl bond, 1,2-unit, 1,2-bond, 1,2-vinyl-unit or 1,2-vinyl-bond;
- trans: 1,4-trans unit, 1,4-trans bond, trans-1,4 unit or trans1,4 bond;
- cis: 1,4-cis unit, 1,4-cis bond, cis-1,4 unit or cis-1,4 bond.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1382, *Rubber — Vocabulary*

ISO 1795, *Rubber, raw natural and raw synthetic — Sampling and further preparative procedures*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1382 apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Principle

The IR spectrum of the S-SBR sample is measured by FTIR with ATR. The absorbances that are characteristic of each microstructure component and styrene at the specified wave number are used to determine the content of each component by using the specific formulae presented in this document.

5 Apparatus

5.1 FTIR, of the following specifications:

- detector: deuterium tri-glycine sulfate (DTGS) or tri-glycine sulfate (TGS);
- resolution: 2 cm⁻¹.

5.2 ATR, of the following specifications:

- type: single bounce ATR;
- crystal: diamond;
- angle of incidence: 45°;
- sample pressure clamp: a concave or a flat-shaped clamp which is capable of maintaining a constant pressure on the sample. The use of a torque wrench is recommended.

6 Calibration

6.1 FTIR standards.iteh.ai/catalog/standards/iso/820c1b5-b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024

Adjust the optical bench alignment of FTIR spectrometer according to the manufacturer's instruction manual.

6.2 ATR

Set ATR in the sample chamber of FTIR and adjust the optical alignment of ATR according to the manufacturer's instruction manual.

7 Sampling

7.1 Prepare the test sample in accordance with ISO 1795.

NOTE The extraction of ordinary extender oils by solvent is not necessary.

7.2 Cut out a test piece from the test sample. The test piece shall have a flat surface to give good contact with the ATR crystal and be approximately the same size as the crystal, usually a few square millimetres.

8 Procedure for measuring ATR spectrum

8.1 Set up FTIR according to the manufacturer's instruction manual and set up the measurement conditions as follows:

- resolution: 2 cm⁻¹;
- number of scans: 32;
- range of wave number: 600 cm⁻¹ to 1 800 cm⁻¹.

8.2 Set ATR with the specification in a sample chamber of FTIR.

8.3 Measure the background spectrum without sample on the ATR crystal with the conditions shown in [8.1](#).

8.4 Put the test piece on the ATR crystal and contact it as completely as possible to the crystal surface, preferably using the clamp specified in [5.2](#). The contact between the test piece and the crystal affects the absorbance of ATR spectra.

8.5 Measure the sample spectrum with the conditions shown in [8.1](#).

8.6 The atmosphere of the sample chamber for FTIR shall be kept consistent during the background and test piece measurements in order to avoid the influences of absorbance at 668 cm⁻¹ and 723 cm⁻¹ by CO₂.

9 Determination of the microstructure of butadiene and the styrene content

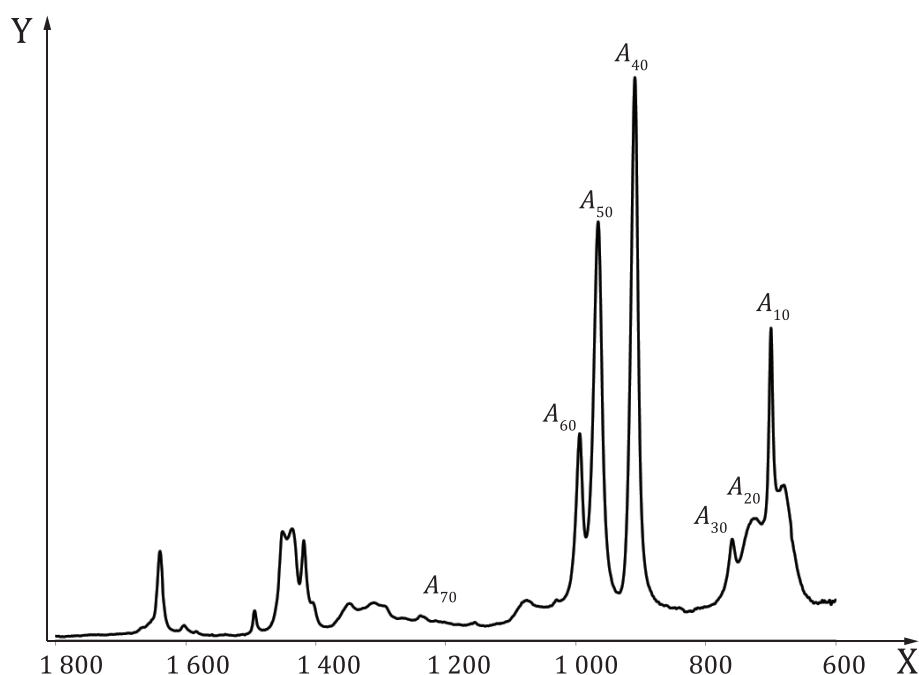
9.1 Measurement of the absorbance for each microstructure component

Measure the absorbance values at the wave numbers corresponding to the microstructure components as specified in [Table 1](#). For cis, the absorption peaks are weak and the wave number of the peaks is affected by the styrene content of the polymer.

[Figure 1](#) provides an example of an ATR spectrum of a typical S-SBR.

Table 1 — Measurement of absorbances for each microstructure component of S-SBR

Notation for absorbance	Microstructure Component	Remarks
A ₁₀	Styrene	Measure the absorbance at the peak maximum from 695 cm ⁻¹ to 700 cm ⁻¹ .
A ₂₀	Cis	The wave number at this peak maximum is affected by the nature of the polymer, such as the styrene content. When the peak maximum is visible, read off the absorbance at the peak maximum from 720 cm ⁻¹ to 730 cm ⁻¹ . If the styrene content is over 30 %, the peak of the cis bond is hidden between the two large styrene absorptions at around 758 cm ⁻¹ and around 698 cm ⁻¹ . In this case, measure the absorbance value at 726 cm ⁻¹ .
A ₃₀	Styrene	Measure the absorbance at the peak maximum from 755 cm ⁻¹ to 761 cm ⁻¹ .
A ₄₀	Vinyl	Measure the absorbance at the peak maximum from 905 cm ⁻¹ to 912 cm ⁻¹ .
A ₅₀	Trans	Measure the absorbance at the peak maximum from 962 cm ⁻¹ to 967 cm ⁻¹ .
A ₆₀	Vinyl	Measure the absorbance at the peak maximum from 991 cm ⁻¹ to 996 cm ⁻¹ .
A ₇₀	Base line	Measure the absorbance at 1 200 cm ⁻¹ as zero point of each absorbance.

**Key**X wave number (cm⁻¹)

Y absorbance

Figure 1 — ATR spectrum of a typical S-SBR**9.2 Calculation of microstructures****9.2.1 General**

The microstructure of S-SBR is calculated by using regression formulae and the measured absorbance values of the ATR spectra of each sample. The regression formulae were derived from a statistical study on the ATR spectra of various S-SBR samples with known microstructures. After adjusting the baseline of the ATR spectra, the absorbance ratio values of respective absorptions are obtained as the parameter value for microstructure calculation. The microstructure results are calculated by substituting these parameter values in the regression formulae.

9.2.2 Base line correction of each absorbance peak

Obtain the absorbance of each of the peaks A_{11} to A_{61} with corrected base lines by using [Formulae \(1\) to \(6\)](#):

$$A_{11} = A_{10} - A_{70} \quad (1)$$

$$A_{21} = A_{20} - A_{70} \quad (2)$$

$$A_{31} = A_{30} - A_{70} \quad (3)$$

$$A_{41} = A_{40} - A_{70} \quad (4)$$

$$A_{51} = A_{50} - A_{70} \quad (5)$$

$$A_{61} = A_{60} - A_{70} \quad (6)$$

9.2.3 Ratio of absorbance

Obtain the ratios of the absorbances A_{12} to A_{62} by using [Formulae \(7\)](#) to [\(12\)](#):

$$A_{12} = A_{11}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (7)$$

$$A_{22} = A_{21}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (8)$$

$$A_{32} = A_{31}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (9)$$

$$A_{42} = A_{41}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (10)$$

$$A_{52} = A_{51}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (11)$$

$$A_{62} = A_{61}/(A_{11} + A_{21} + A_{31} + A_{41} + A_{51} + A_{61}) \quad (12)$$

9.2.4 Second order terms

Calculate the second order terms which are the squares of A_{12} to A_{62} . The second order terms are expressed as A_{12}^2 to A_{62}^2 for the square of A_{12} to A_{62} .

9.2.5 Styrene content and contents of three microstructure types of butadiene portion by regression formulae

Styrene content relative to the S-SBR and the contents of three microstructure types of butadiene portion relative to the S-SBR are expressed by the regression Formulae [\(13\)](#) to [\(16\)](#).

These four regression formulae are obtained by the method shown in [Annex B](#).

$$S_m = 9,0 + 12,9 \times A_{12} + 25,9 \times A_{12}^2 - 111,2 \times A_{22} + 412,5 \times A_{22}^2 + 105,0 \times A_{32} + 891,9 \times A_{32}^2 - 0,5 \times A_{42} - 21,5 \times A_{42}^2 - 30,7 \times A_{52} + 28,9 \times A_{52}^2 + 24,5 \times A_{62} - 47,2 \times A_{62}^2 \quad (13)$$

$$V_m = 32,9 + 5,3 \times A_{12} - 12,9 \times A_{12}^2 - 183,6 \times A_{22} + 1\,168,4 \times A_{22}^2 + 13,2 \times A_{32} - 572,5 \times A_{32}^2 + 33,7 \times A_{42} + 3,5 \times A_{42}^2 - 90,5 \times A_{52} + 33,5 \times A_{52}^2 + 129,6 \times A_{62} + 168,9 \times A_{62}^2 \quad (14)$$

$$T_m = 42,5 - 16,3 \times A_{12} - 18,8 \times A_{12}^2 + 61,4 \times A_{22} - 1\,368,2 \times A_{22}^2 - 65,1 \times A_{32} - 127,7 \times A_{32}^2 - 19,6 \times A_{42} + 14,9 \times A_{42}^2 + 93,3 \times A_{52} - 13,9 \times A_{52}^2 - 129,8 \times A_{62} - 116,6 \times A_{62}^2 \quad (15)$$

$$C_m = 15,6 - 1,9 \times A_{12} + 5,8 \times A_{12}^2 + 233,5 \times A_{22} - 212,6 \times A_{22}^2 - 53,1 \times A_{32} - 191,7 \times A_{32}^2 - 13,6 \times A_{42} + 3,1 \times A_{42}^2 + 27,9 \times A_{52} - 48,5 \times A_{52}^2 - 24,3 \times A_{62} - 5,1 \times A_{62}^2 \quad (16)$$

where

S_m is the mass fraction of styrene relative to the S-SBR, expressed in per cent;

V_m is the mass fraction of vinyl relative to the S-SBR, expressed in per cent;

T_m is the mass fraction of trans relative to S-SBR, expressed in per cent;

C_m is the mass fraction of cis relative to the S-SBR, expressed in per cent.

The styrene content is the mass fraction of styrene relative to the S-SBR.

9.2.6 Contents of three microstructure types relative to butadiene portion in the S-SBR

Contents of three microstructure types of the butadiene portion in the S-SBR are expressed by [Formulae \(17\)](#) to [\(19\)](#):

$$V = V_m / (V_m + T_m + C_m) \times 100 \quad (17)$$

$$T = T_m / (V_m + T_m + C_m) \times 100 \quad (18)$$

$$C = C_m / (V_m + T_m + C_m) \times 100 \quad (19)$$

where

V is the mol fraction of vinyl relative to the butadiene portion in the S-SBR, expressed in per cent;

T is the mol fraction of trans relative to the butadiene portion in the S-SBR, expressed in per cent;

C is the mol fraction of cis relative to the butadiene portion in the S-SBR, expressed in per cent.

10 Precision

See [Annex A](#).

11 Test report

The test report shall include at least the following information:

- a) sample details:
 - 1) a full description of the sample and its origin;
 - 2) method of preparation of test piece from the sample;
- b) a reference to this document, i.e. ISO 21561-2:2024; -b36a-4744-a84b-214bfe6a2022/iso-21561-2-2024
- c) test details including any details of any procedures not specified in this document;
- d) test results:
 - 1) the number of test pieces used;
 - 2) the results of the determination, expressed in % and rounded to one place of decimals;
- e) date(s) of test.