



Designation: F 112 – 00

Standard Test Method for Sealability of Enveloped Gaskets¹

This standard is issued under the fixed designation F 112; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the evaluation of the sealing properties of enveloped gaskets for use with corrosion-resistant process equipment.² Enveloped gaskets are described as gaskets having some corrosion-resistant covering over the internal area normally exposed to the corrosive environment. The shield material may be plastic (such as polytetrafluoroethylene) or metal (such as tantalum). A resilient conformable filler is usually used inside the envelope. The design and construction of nonmetallic gaskets is covered in Practice F 336.

1.2 The values stated in SI units are to be regarded as the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For specific precautionary statements, see Section 6.

2. Referenced Documents

2.1 ASTM Standards:

F 336 Design and Construction of Nonmetallic Enveloped Gaskets for Corrosive Service³

3. Summary of Method

3.1 An enveloped gasket is compressed between two bolted flanges in a special test fixture⁴. After the specified load is

applied to the gasket, air at the specified pressure is introduced into the test chamber and then the test chamber is sealed. Pressure and temperature readings are taken and recorded at specified intervals. The leakage rate is measured by the change in the test chamber pressure over time. The flange load on the gasket is increased and the process is repeated.

3.2 Results of the sealability test are expressed as a graph of the remaining test chamber pressure versus time for the specified conditions.

4. Significance and Use

4.1 This test method is designed to evaluate all types of enveloped gaskets under controlled conditions with respect to leakage and to provide measurable leakage rates.

4.2 Determining torque required to seal a given gasket is also part of this test method. By converting the torque at sealing to total bolt load, useful design information may be obtained for other standard and nonstandard openings.

4.3 This test method may be used as an incoming quality control test to evaluate similar gaskets from different suppliers. This test method may also be used as a quality control test when parameters are agreed upon between the producer and the user.

4.4 Leakage through the gasket or over the gasket, or both, is determined by this test method.

5. Apparatus

5.1 *Leakage Test Unit*—The unit⁴ shall contain a suitable pressure gage to read from 0 to 2.1 MPa (0 to 300 psig) and mounted as shown in Fig. 1.

5.2 *Compressed Air Supply*, capable of supplying 621 kPa (90 psig) to the test unit.

5.3 *Temperature Indicating Device*—A thermometer capable of reading in increments of 1°C in the ambient temperature range.

6. Hazards

6.1 Use only a unit suitable for a minimum of 1034 kPa (150 psig).

6.2 A metal shield box with access doors is suggested as an added safety factor.

¹ This test method is under the jurisdiction of ASTM Committee F03 on Gaskets and is the direct responsibility of Subcommittee F03.10 on Composite Gaskets.

Current edition approved Oct. 10, 2000. Published November 2000. Originally published as F 112 – 70. Last previous edition F 112 - 95.

² This test method is to be used in place of ASTM Test Methods F 37, for Sealability of Gasket Materials (*Annual Book of ASTM Standards*, Vol 09.02), which applies only to single-component gasket materials and is not applicable to envelope-style gaskets. This fixture may also be used for other gasket materials or designs, with or without modification.

Supporting data are available from ASTM Headquarters. Request RR: F03-1000.

³ *Annual Book of ASTM Standards*, Vol 09.02.

⁴ Detailed drawing of the test fixture is available at a nominal cost from ASTM Headquarters, 100 Barr Harbor Drive, West Conshohocken, PA 19428. Request Adjunct No. ADJF0112. A suitable test unit can be obtained from the Pfaudler Co., 1000 West Ave., Rochester, NY 14603.


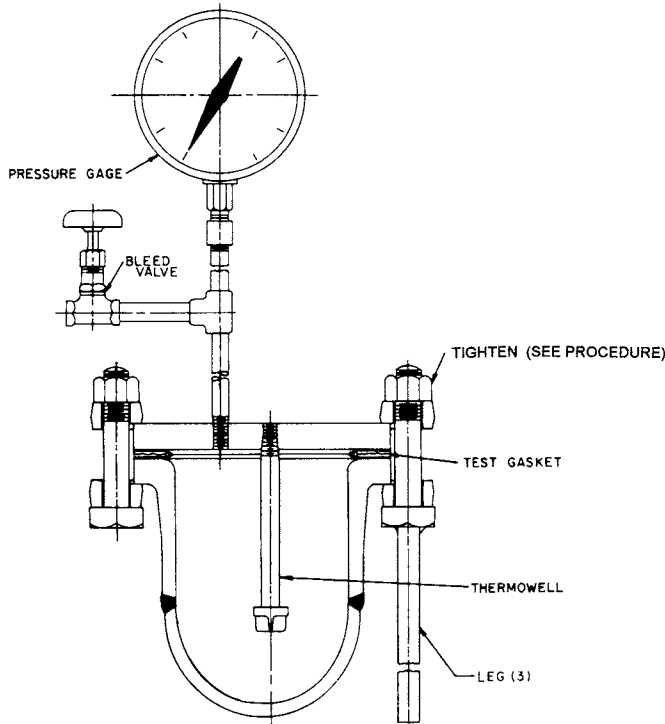


FIG. 1 Test Unit

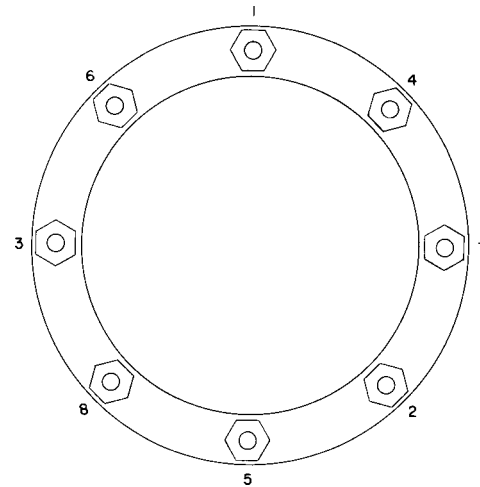

NOTE 1—Tighten bolts evenly; follow numerical sequence.

FIG. 2 Bolt Tightening Progression

6.3 Prior to performing any tests, inspect the unit for damage, corrosion, and also for metal fatigue cracks that may have developed.

7. Test Specimen

7.1 Commercial 102-mm (4-in.) nominal size enveloped gasket with a shield 102 mm (4 in.) in inside diameter (minimum) and inserts 114 mm (4.5 in.) in inside diameter by 175 mm (6.88 in.) in outside diameter. The thickness of the test gasket will depend upon its expected usage and must be specified in the report as results will vary accordingly.

8. Conditioning

8.1 Conditioning of the test gasket is not necessary since this test method is designed for shelf stock. Assembled enveloped gaskets and the components used in their construction would not be affected by aging under normal storage conditions.

9. Procedure

9.1 The temperature for this test is normally ambient room temperature.

9.2 Assemble the gasket in the test unit.

9.3 Lubricate the bolt threads well using molydisulfide dry film or grease. Sanding the bottom of the bolt heads and the washers will minimize torque variables and ensure duplication of results.

9.4 Gradually and evenly tighten the bolts to 39 N·m (29 lbf·ft) following the sequence indicated by the numbers in Fig. 2. Progression of the tightening on each bolt should be in approximately 7-N·m (5-lbf·ft) increments.

9.5 Apply 621 kPa (90 psig) of air pressure into the test unit and seal. Record the pressure readings every hour for 4 h and then at the end of 20 h, but since the readings are temperature dependent, take and record the temperature within the oil-filled thermowell to coincide with the time of the pressure readings. Apply corrections if required.

9.6 Fill the test fixture thermowell three-quarters full with a light oil.⁵ Allow 15 minutes for the temperature to stabilize, and insert the temperature sensor.

9.7 Retighten the bolts to 57 N·m (42 lbf·ft) in accordance with 9.4 and proceed as in 9.5.

9.8 Continue testing using bolt tensions of 85 N·m (63 lbf·ft), 102 N·m (75 lbf·ft), and 122 N·m (90 lbf·ft) in accordance with 9.4 and proceed as in 9.5.

9.9 Repeat 9.2-9.8 using another gasket from the same lot.

10. Report

10.1 Report the following information:

10.1.1 Identification of the enveloped gasket,

10.1.2 Gasket thickness,

10.1.3 Pressure readings versus time, and

10.1.4 Plot of remaining pressure versus time, h, for each torque level.

11. Precision and Bias

11.1 *Precision:*

11.1.1 The condition and the lubrication of the bolts have a direct bearing on the precision and bias of this test method.

11.1.2 A variation of 5 % between laboratories may be expected using this procedure.

11.2 *Bias*—since there is no accepted reference material suitable for determining the bias of the procedure in this test method for measuring sealability of gasket materials, no statement on bias is available.

⁵ Mineral oil or commercially available heat transfer oil has been found satisfactory.