



Designation: **D3108—07 D3108/D3108M – 13**

Standard Test Method for Coefficient of Friction, Yarn to Solid Material¹

This standard is issued under the fixed designation ~~D3108~~D3108/D3108M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope

1.1 This test method covers the measurement of the kinetic frictional properties of a moving yarn in contact with a solid material.

NOTE 1—For determining yarn-to-yarn friction, refer to Test Method [D3412](#).

1.2 This test method specifies a relative speed of 100 m/min. The test method may be used at other speeds, although with a possible change in precision and coefficient of friction.

1.3 This test method covers the measurement of the coefficient of kinetic friction between yarn and solid surface or surfaces of constant radius in the contact area. If a yarn of uniform value is used, comparisons of frictional properties of different solid materials can be made with relation to that yarn. If a given solid material is used, comparisons of frictional properties of different yarns, or yarns with different finishes, can be made with relation to that particular solid material.

1.4 This test method specifically recommends wrap angles of 1.57, 3.14 and 6.28 radian (~~±80~~(90, 180 and 360°), but other wrap angles may be used, again with a possible change in precision and level. The angle of wrap should not be so great, especially for yarns having high coefficients of friction, that it causes the output tension to exceed the yield value for the yarn being tested. Also, in every case the angle of wrap should not be less than 1.57 rad (90°).

1.5 This test method has been applied to yarns having linear densities ranging between ~~±0~~1.5 and 80400 tex (~~±0~~[14 and 720 denier]~~3600 denier~~) and having coefficients of friction ranging between 0.1 and 0.51.0 but may also be used with yarns outside these ranges of linear densities and coefficients of friction.

1.6 The values stated in either SI units or inch-pound units are to be regarded separately as ~~the~~ standard. The values ~~given in parentheses are for information only.~~ stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Section 7.

2. Referenced Documents

2.1 *ASTM Standards:*²

[D123 Terminology Relating to Textiles](#)

[D1776 Practice for Conditioning and Testing Textiles](#)

[D1907 Test Method for Linear Density of Yarn \(Yarn Number\) by the Skein Method](#)

[D2258 Practice for Sampling Yarn for Testing](#)

[D3412 Test Method for Coefficient of Friction, Yarn to Yarn](#)

[D4849 Terminology Related to Yarns and Fibers](#)

3. Terminology

3.1 For all terminology relating to [D13.58](#), Yarns and Fibers, refer to Terminology [D4849](#).

3.1.1 The following terms are relevant to this standard: coefficient of friction, friction, kinetic friction, radian, static friction, wrap angle.

¹ This test method is under the jurisdiction of ASTM Committee [D13](#) on Textiles and is the direct responsibility of Subcommittee [D13.58](#) on Yarns and Fibers. Current edition approved ~~Jan. 1, 2007~~July 1, 2013. Published ~~January 2007~~August 2013. Originally approved in 1972. Last previous edition approved in ~~2004~~2007 as ~~D3108—04~~D3108—07. DOI: ~~10.1520/D3108-07~~10.1520/D3108_D3108M-13.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.2 For all other terminology related to textiles, refer to Terminology **D123**.

4. Summary of Test Method

4.1 A length of yarn is run at known speeds and in contact with either single or multiple friction surfaces using a specified wrap angle. (See **Fig. 1**.) The yarn input and output tensions are measured, and the coefficient of friction is calculated by means of Amontons' law (see **11.4**). Alternatively, apparatus is used in which the ratio of output tension to input tension is measured allowing the coefficient of friction to be indicated directly.

5. Significance and Use

5.1 Test Method D3108 for the determination of kinetic friction between yarn and solid materials may be used for the acceptance testing of commercial shipments of yarn, but caution is advised since between laboratory precision is known to be poor. Comparative tests as directed in **5.1.1** may be advisable.

5.1.1 If there are differences or practical significance between reported test results for two laboratories (or more), comparative tests should be performed to determine if there is a statistical bias between them, using competent statistical assistance. As a minimum, test samples that are as homogenous as possible, drawn from the material from which the disparate test results were obtained, and randomly assigned in equal numbers to each laboratory for testing. The test results from the two laboratories should be compared using a statistical test for unpaired data, at a probability level chosen prior to the testing series. If a bias is found, either its cause must be found and corrected, or future test results for that material must be adjusted in consideration of the known bias.

5.2 The frictional properties of textile yarns and of machinery components such as yarn guides are of general interest and have many applications. Because the frictional properties of yarns will affect the performance and life of yarn guides, sewing and knitting needles, and other contact surfaces, the modifying effects of surface finishes and lubricants are of special interest. Frictional properties also affect the quality and performance properties of yarns and subsequently of products made from them. As a consequence, frictional properties are of interest in research, control, and product design.

5.3 It is stressed that there is no coefficient of friction for a single body such as a yarn or a surface. A coefficient of friction measures the interaction between two bodies or elements such as a yarn running over a surface.

5.4 Although this method lays down standardized conditions of test, nonstandard conditions may be used for research or diagnosis but should be reported as such.

5.5 This method covers determination of the mean friction over a specified length of yarn.

5.6 Additional information has been reported in the literature.^{3,4,5}

ASTM D3108/D3108M-13

<https://standards.iteh.ai/catalog/standards/sist/240649be-f1c8-4469-abb5-34cce478866c/astm-d3108-d3108m-13>

³ Olsen, J.S., "Frictional Behaviour of Textile Yarns," *Textile Research Journal*, Vol 39 No 1, 1969, pp 31-37.

⁴ Lyne, D.G., "Dynamic Friction Between Cellulose Acetate Yarn and a Metal Cylinder," *Journal of the Textile Institute*, Vol 46, 1955, p 112.

⁵ Rubenstein, C., "Review of the Factors Influencing the Friction of Fibres, Yarns and Fabrics," *Wear* Vol 2, 1958-59, p 296.

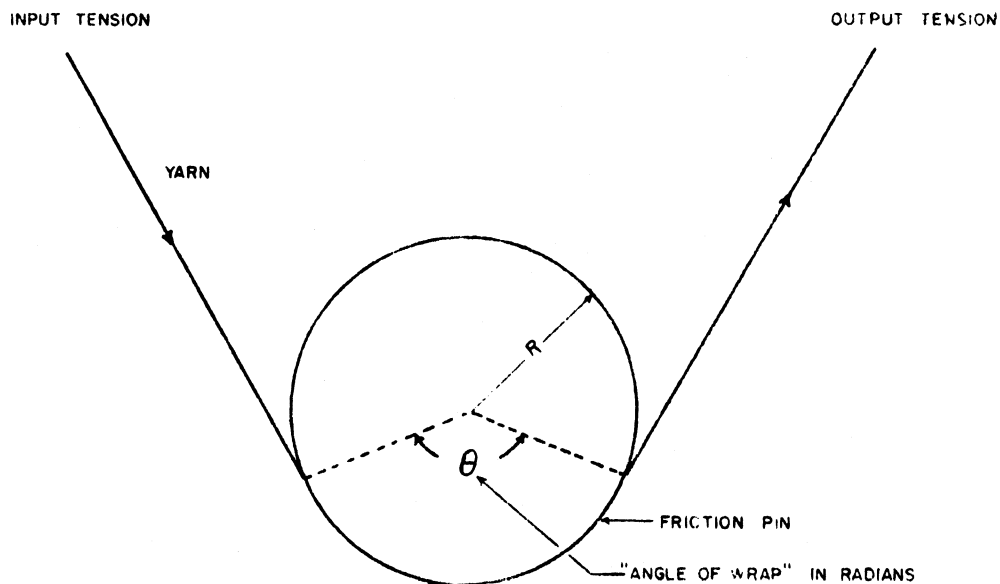


FIG. 1 Schematic Diagram of Angle of Wrap

6. Apparatus

6.1 *Friction Testing Apparatus (Indirect)*⁶ (Fig. 2)—Apparatus in which the input tension is measured or controlled to a set value, the output tension is measured, and the coefficient of friction is calculated within or outside the apparatus.

6.1.1 *Yarn Tension Input Control*—A means of controlling the yarn input tension to the nearest ± 1 mN (± 0.1 gf) [± 0.1 gf]. A demand-fed apparatus with a fixed weight is suitable.

6.1.2 *Yarn Input Tension Measurement*—The yarn input tension is measured to within ± 1 mN (± 0.1 gf) [± 0.1 gf] using a suitable tension gage producing an electrical signal. The signal is recorded as mN (gf) [gf], or is used in combination with the yarn output tension measurement to calculate the coefficient of friction.

6.1.3 *Yarn Output Tension Measurement*—The yarn output tension is measured to within ± 1 mN (± 0.1 gf) [± 0.1 gf] using a suitable tension gage producing an electrical signal. The signal is recorded as mN (gf) [gf] or is used in combination with the yarn input tension measurement to calculate the coefficient of friction. A suitable chart recorder may be used.

6.2 *Friction Testing Apparatus (Direct)* (Fig. 3)—Apparatus in which the ratio of output to input tensions is established directly and the coefficient of friction indicated on a scale or display. The comparison may be mechanical.

6.2.1 *Yarn Tension Input Control*—Since this type of apparatus automatically derives the ratio of output-to-input-tension, close control of input tension is not usually required. However, because the absolute level of input tension can affect the measured coefficient of friction for certain yarns, particularly low-twist yarns, the general level of input tension should be preset, for example with a dead weight disk tensioner.

6.2.2 *Coefficient of Friction Indicator*—The nature of this will depend on the instrument being used. Typically, a pointer or a chart recorder pen is displaced by the movement of the components that bring the system into balance and the product of the input tension and the distance from the axis equals the product of the output tension and the distance from the axis (see Fig. 3).

6.3 *Friction Surface*, may be changeable on some equipment.

6.3.1 *Standard Friction Surface*—Friction surfaces having a diameter of 0.5 in. (12.7 mm) [12.7 mm] for yarns having linear densities ranging from 1.5 to 80 tex, or 0.79 in. [20.0 mm] for yarns having linear densities ranging from 80 to 400 tex, and a chrome surface of 40.03 to 6 μ m roughness. The use of one, two, or three pins in sequence has been found satisfactory although there may be a difference in the results (theoretically only the total angle of wrap and not the number of pins should affect the results). (See 12.3.4).

6.3.2 *Other Friction Surfaces*—Unless the apparatus has a friction surface that cannot be altered, friction surfaces of different materials, sizes, and surface finish may be used but must be specified in the report (see 12.3.4).

6.4 *Drive System*, consisting of a controlled speed yarn transporting device with appropriate controls to record and adjust the linear or throughput speed. Generally, a speed of less than 300/400 m/min has been found preferable. The yarn transporting device should be constructed to eliminate yarn slippage by the use of high-friction surface.

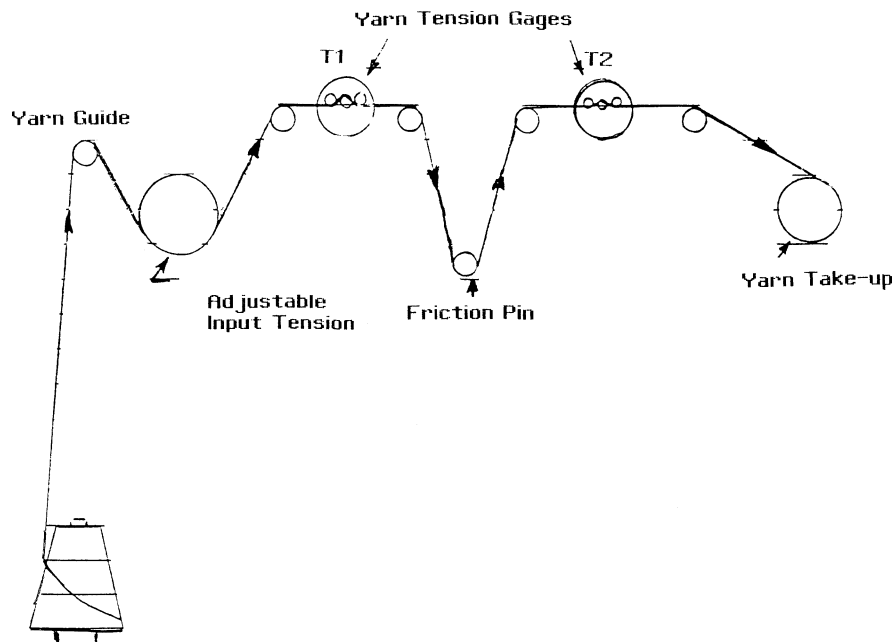


FIG. 2 Schematic Diagram of Typical Yarn Friction Measuring Apparatus, Indirect Type

⁶ Equipment meeting these requirements may be commercially obtained from Lawson Hemphill (Sales) Inc., PO Drawer 6388, Spartanburg, SC 29304.

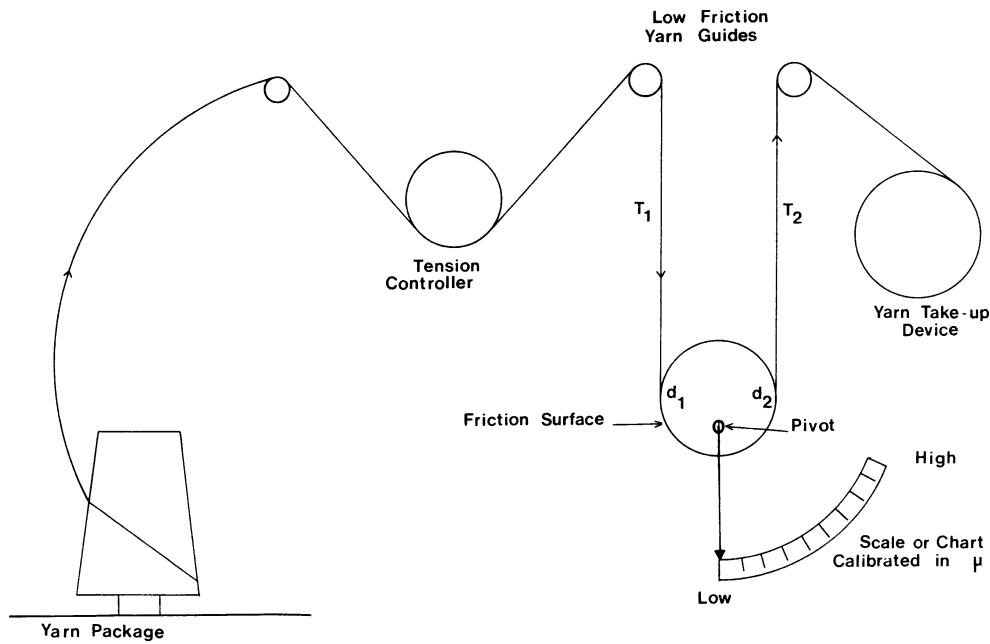


FIG. 3 Schematic Diagram of Typical Yarn Friction Measuring Apparatus, Direct Type

6.5 Cotton Yarn For Cleaning—A thoroughly scoured cotton yarn that is highly absorbent (see section 10.2.2 and Annex A1).

6.6 Solvent—See 10.2.

7. Hazard

7.1 Refer to the manufacturer's material safety data sheet for information on storage, handling, use, and disposal of chemicals used in this test method.

8. Sampling

8.1 Lot Sample—As a lot sample for acceptance testing, take at random the number of shipping units directed in an applicable material specification or other agreement between the purchaser and the supplier, such as an agreement to use Practice D2258. Consider shipping cases or other shipping units to be the primary sampling units.

NOTE 2—An adequate specification or other agreement between the purchaser and the supplier requires taking into account the variability between shipping units, between packages or ends within a shipping unit, and between specimens from a single package so as to provide a sampling plan with a meaningful producer's risk, consumer's risk, acceptable quality level, and limiting quality level.

8.2 Laboratory Sample—As a laboratory sample for acceptance testing, take at random from the each shipping unit in the lot sample the number of packages or ends directed in an applicable material specification or other agreement between the purchaser and the supplier such as an agreement to use Practice D2258. Preferably, the same number of packages should be taken from each shipping unit in the lot sample. If differing numbers of packages are to be taken from shipping units in the lot sample, determine at random which shipping units are to have each number of packages drawn.

8.3 Test Specimens—Test one specimen from each package in the laboratory sample.

9. Conditioning

9.1 Preparation of Test Packages—Remove sufficient yarn from the test packages to avoid testing nonrepresentative layers. If in doubt, remove about 10 % of the length of yarn on the package.

9.2 The strand to be tested must have a uniform moisture content along its length. Atmospheric conditions must therefore be stable and the strand must be in equilibrium with the prevailing atmosphere. To satisfy this condition, testing should be carried out after thorough conditioning in the standard atmosphere for testing textiles.

9.3 Preconditioning—Precondition packages of yarn for at least 3 h in an atmosphere with a relative humidity between 5 and 25 % and a temperature not exceeding 50°C (120°F).

9.3 Conditioning—Condition the preconditioned packages of yarn in the standard atmosphere for testing textiles (relative humidity 65 ± 2 % and temperature 21 ± 1°C (70 ± 2°F)) in moving air until it has reached moisture equilibrium for testing. Precondition and condition the specimens as directed in Practice D1776.