
**Fibre ropes for offshore
stationkeeping —**

**Part 4:
Polyarylate**

*Cordages en fibres pour le maintien en position des structures
marines —*

Partie 4: Polyarylate

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 18692-4:2023

<https://standards.iteh.ai/catalog/standards/sist/122f6af4-10d0-49b7-bf0c-cc48c6d804b4/iso-18692-4-2023>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 18692-4:2023

<https://standards.iteh.ai/catalog/standards/sist/122f6af4-10d0-49b7-bf0c-cc48c6d804b4/iso-18692-4-2023>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Materials	2
5 Requirements — Rope properties	2
5.1 Minimum breaking strength.....	2
5.2 Minimum core tenacity.....	2
5.3 Axial compression fatigue properties.....	2
5.4 Torque properties.....	2
5.5 Cyclic loading performance.....	3
5.6 Particle ingress protection.....	3
6 Requirements — Rope layout and construction	3
7 Rope testing	3
7.1 Type test.....	3
7.1.1 General.....	3
7.1.2 Sampling.....	3
7.1.3 Breaking strength, core tenacity, and stiffness tests.....	3
7.1.4 Axial compression fatigue properties test.....	3
7.1.5 Torque properties tests.....	4
7.1.6 Linear density test.....	4
7.1.7 Cyclic loading endurance test.....	4
7.1.8 Protective cover thickness.....	4
7.1.9 Particle ingress protection.....	4
7.2 Testing of current production.....	4
8 Report	4
9 Certification	4
10 Marking, labelling, and packaging	4
Annex A (normative) Fibre qualification and testing	5
Annex B (normative) Axial compression fatigue properties test	6
Annex C (informative) Additional information and guidance — Axial compression fatigue properties	8
Bibliography	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 38, *Textiles*.

This first edition of ISO 18692-4 cancels and replaces ISO/TS 19336:2015, which has been technically revised.

The main changes are as follows:

- the document previously published as a Technical Specification has been reorganized as the new ISO 18692-4, taking into account the content of ISO 18692-1:2018.

A list of all parts in the ISO 18692 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Fibre ropes for offshore stationkeeping —

Part 4: Polyarylate

1 Scope

This document specifies main characteristics and test methods of polyarylate fibre ropes used for offshore stationkeeping.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1968, *Fibre ropes and cordage — Vocabulary*

ISO 18692-1:2018, *Fibre ropes for offshore stationkeeping — Part 1: General specification*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1968, ISO 18692-1 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

polyarylate

high-modulus fibre made from thermotropic liquid crystal aromatic polyester and produced by melt spinning

Note 1 to entry: An example of polyarylate chemical structure shows in [Figure 1](#).

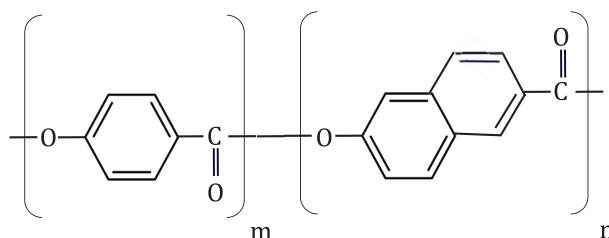


Figure 1 — Polyarylate chemical structure

3.2

axial compression fatigue

failure mode for fibre rope such as polyarylate under low tension or compression

4 Materials

The fibre used in the core of the rope shall be polyarylate fibre, with an average tenacity of not less than 1,8 N/tex, and qualified and tested in accordance with [Annex A](#).

Rope cover material and other materials employed in rope assembly shall be in accordance with ISO 18692-1.

5 Requirements — Rope properties

5.1 Minimum breaking strength

The minimum breaking strength (MBS) of the rope (spliced), when tested according to ISO 18692-1, shall conform to [Table 1](#).

Table 1 — Minimum breaking strength (MBS)

Reference number (RN) ^a	Minimum breaking strength kN
80	2 500
90	3 100
100	3 900
106	4 400
112	5 000
118	5 600
125	6 300
132	7 000
140	7 800
150	8 700
160	10 000
170	11 200
180	12 500
190	14 000
200	15 500
212	17 500
224	19 500

^a The reference number corresponds to the approximate outer diameter of the rope, in millimetres (mm). Actual diameters may vary for a given reference number.

5.2 Minimum core tenacity

The minimum tenacity of the polyarylate rope core shall be 0,90 N/tex, measured according to ISO 18692-1. All samples tested shall comply with this minimum value.

5.3 Axial compression fatigue properties

The rope shall have demonstrated a residual strength not less than 95 % of MBS, following the axial compression fatigue test method in [Annex B](#) and additional information in [Annex C](#).

5.4 Torque properties

Torque-neutral rope or torque-matched rope shall be defined according to ISO 18692-1.

5.5 Cyclic loading performance

The rope shall have demonstrated performance under cycling loading following the requirements of ISO 18692-1.

5.6 Particle ingress protection

Unless otherwise specified, the rope shall be constructed with a protection of the core against the ingress of particles in accordance with ISO 18692-1.

6 Requirements — Rope layout and construction

Rope layout and construction shall be in accordance with ISO 18692-1.

7 Rope testing

7.1 Type test

7.1.1 General

Type tests shall be performed in accordance with ISO 18692-1 and the specific requirements of this clause.

7.1.2 Sampling

The number of rope samples to be tested is given in [Table 2](#).

Table 2 — Number of samples for testing

Test	Number of samples
Breaking strength, core tenacity and stiffness ^d	3
Axial compression fatigue ^a	1
Torque properties ^b	1
Linear density	1
Cyclic loading endurance ^c	1
^a See 7.1.4 .	
^b See ISO 18692-1:2018, 7.1.4	
^c See ISO 18692-1:2018, 7.1.6	
^d See ISO 18692-1:2018, 7.1.3	

7.1.3 Breaking strength, core tenacity, and stiffness tests

The number of samples from [Table 2](#) shall be tested, and each sample shall be capable of meeting the requirements of [5.1](#) and of [5.2](#).

NOTE The measurements of the dynamic stiffness at end of bedding-in — and, when required, those of the quasi-static stiffness and the dynamic stiffness at several mean load level — are performed for design purposes only. There are no acceptance criteria on these parameters.

7.1.4 Axial compression fatigue properties test

One sample shall be tested for axial compression fatigue properties.

There is no need to perform this test when data are available from the previous qualification test of another rope with the same design, material and method of manufacture of rope core, and a size not less than reference number 90.

7.1.5 Torque properties tests

Where applicable, torque properties tests shall be performed according to the procedure specified in ISO 18692-1:2018, 7.1.4 and Annex B.

7.1.6 Linear density test

The linear density shall be calculated from the measured mass and elongation according to the method defined in ISO 18692-1:2018, 7.1.5 and Annex B.

7.1.7 Cyclic loading endurance test

The cyclic loading endurance test shall be performed according to the procedure specified in ISO 18692-1.

The residual strength of the rope shall be not less than 80 % of the MBS.

7.1.8 Protective cover thickness

The thickness of the protective cover shall be verified. See ISO 18692-1:2018, 7.1.7.

7.1.9 Particle ingress protection

See [5.6](#) and ISO 18692-1:2018, Annex B.

7.2 Testing of current production

Testing of current production shall be in accordance with ISO 18692-1:2018, 7.2.

8 Report

The report shall be in accordance with ISO 18692-1.

9 Certification

Certification shall be in accordance with ISO 18692-1.

10 Marking, labelling, and packaging

The marking, labelling, and packaging shall be in accordance with ISO 18692-1.

Annex A (normative)

Fibre qualification and testing

A.1 General

Fibre qualification and testing shall be in accordance with ISO 18692-1:2018, Annex A, and the following requirements.

A.2 Fibre testing — Hydrolysis properties of polyarylate fibres

The material shall have a residual strength of at least 90 % of its nominal value (new fibre), after immersion for two weeks in 80 °C water (alternatively 20 weeks at 60 °C).

NOTE The water for this test can be either natural or artificial seawater (e.g. ASTM D 1141).

Testing may be performed on fibres or small cords (braided or twisted).

Accelerated test based on a factor 1 000 in time over 60 °C increase of temperature, e.g. see ISO 9080, to simulate the conditions of a mooring line (20 years in seawater at 4 °C to 20 °C). Test duration may be adjusted if this can be documented by suitable test data.

<https://standards.iteh.ai>

<https://standards.iteh.ai/catalog/standards/sist/122f6af4-10d0-49b7-bf0c-cc48c6d804b4/iso-18692-4-2023>

Annex B (normative)

Axial compression fatigue properties test

B.1 General

This annex specifies a testing method for axial compression fatigue properties test of polyarylate ropes for offshore station keeping.

B.2 Testing conditions

B.2.1 Rope samples

The axial compression fatigue tests shall be performed on one sample of the full-size rope. Terminations of samples shall be identical to those used in supplied ropes.

Termination fittings shall be provided, with the same type of material and the same profile and dimensions (radius, groove shape) as the thimbles for the supplied rope.

B.2.2 Ambient conditions

The axial compression fatigue test shall be performed under ambient conditions similar to those described for cyclic loading endurance test (see ISO 18692-1:2018, B.2.2).

B.2.3 Testing machine and measurement

The testing machine and the measurement system shall be in accordance with the provisions of ISO 18692-1:2018, B.2.3 and B.2.4. The machine shall be capable of accurately controlling the trough load at 1 % of MBS.

B.3 Testing

B.3.1 Test procedure

The axial compression fatigue test shall be performed according to the steps below:

- a) sample shall be soaked for at least 4 h in fresh water;
- b) test piece shall be installed in the test machine;
- c) load of 2 % of MBS shall be applied;
- d) extensometer shall be installed in a section of the rope undisturbed by the termination;
- e) tension of 50 % of the rope MBS shall be applied at a rate of 10 % MBS/min and held for 30 min;
- f) tension shall be reduced to 20 % of the rope MBS, at a rate of 10 % MBS/min;
- g) cycling tension between 10 % and 30 % of the rope MBS shall be applied 300 times at a frequency between 0,03 Hz and 0,1 Hz;
- h) cycling tension between 1 % and 20 % of the rope MBS shall be applied 2 000 times at a frequency between 0,03 Hz and 0,1 Hz;