



FINAL DRAFT International Standard

ISO/FDIS 642

Steel — Hardenability test by end quenching (Jominy test)

Acier — Essai de trempabilité par trempe en bout (essai Jominy)

ISO/TC 17/SC 7

Secretariat: **AFNOR**

Voting begins on:
2024-06-04

Voting terminates on:
2024-07-30

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO/FDIS 642

<https://standards.iteh.ai/catalog/standards/iso/0b7827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642>

ISO/CEN PARALLEL PROCESSING

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

ISO/FDIS 642

<https://standards.iteh.ai/catalog/standards/iso/0b7827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and designations	1
5 Principle	2
6 Form of test pieces and their preparation	2
6.1 Sampling.....	2
6.2 Dimensions.....	3
6.3 Heat treatment.....	4
6.4 Machining.....	4
7 Apparatus	4
8 Heating and quenching of test piece	6
8.1 Heating.....	6
8.2 Quenching.....	6
9 Preparation for, and measurement of, hardness after quenching	7
10 Expression of results	8
10.1 Hardness at any one point.....	8
10.2 Drawing of the hardness curves.....	8
10.3 Description of the hardenability characteristics of a particular steel.....	9
10.4 Codification of test result.....	9
11 Test report	10
Annex A (informative) Specification for the hardenability of a product	11
Annex B (informative) Additional information to Clause 11	15
Annex C (informative) Computational methods for determination of hardenability	18
Bibliography	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 7, *Methods of testing (other than mechanical tests and chemical analysis)*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 459, *ECISS, European Committee for Iron and Steel Standardization*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 642:1999), which has been technically revised. [//standards.iteh.ai/catalog/standards/iso/067827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642](http://standards.iteh.ai/catalog/standards/iso/067827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642)

The main changes are as follows:

- updated the normative references;
- added a new symbol, *J_d*, in [Table 1](#);
- minimum recommended reduction ratio of 5:1, see [6.1](#);
- revised the test piece dimensions, see [6.1](#), [6.2](#) and [Figures 1](#) and [2](#);
- revised the heat treatment requirements, see [6.3](#);
- revised configuration of fixing and centring device, see [7.3](#) and [Figure 3](#);
- revised text concerning water temperature, see [7.4](#);
- revised requirement for nitric acid solution concentration, see [9.2](#);
- revised codification of test result, see [10.4](#) and [Figure 6](#);
- revised [A.2](#) and [Figures A.2](#) and [A.3](#);
- revised [Annex C](#) and Bibliography;
- editorial clarifications;

ISO/FDIS 642:2024(en)

— reduced the number of bibliographical references.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

iTeh Standards (<https://standards.itih.ai>) Document Preview

ISO/FDIS 642

<https://standards.itih.ai/catalog/standards/iso/0b7827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642>

Steel — Hardenability test by end quenching (Jominy test)

1 Scope

This document specifies a method for determining the hardenability of steel by end quenching (Jominy test) by using a test piece 25 mm in diameter and at least 100 mm long.

By agreement and for a defined field of application, the test described in this document can be replaced by the calculation of the Jominy curve according to an accepted mathematical model.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Symbols and designations

Symbols and designations used in this document are shown in [Table 1](#).

Table 1 — Symbols and designations

Symbol	Designation	Value
L	Test length of test piece	$(97 \pm 0,5)$ mm
D	Diameter of test piece	$(25^{+0,5}_0)$ mm
t	Time during which test piece is maintained at heating temperature	(30^{+5}_0) min
t_m	Maximum time lag between removal of test piece from furnace and start of quenching	5 s
T	Temperature of points on the surface, situated at certain distances from the quenched end	—
T_A	Temperature of austenitizing	—
a	Internal diameter of vertical water supply pipe	$(12,5 \pm 0,5)$ mm
h	Height of water jet without test piece in position	(65 ± 10) mm
d_w	Distance from end of water supply pipe to lower end of test piece	$(12,5 \pm 0,5)$ mm
e	Depth of flats for measurement of hardness	$(0,4 \text{ to } 0,5)$ mm
d	Distance, in millimetres, from quenched end to points where hardness is measured	—

Table 1 (continued)

Symbol	Designation	Value
Jd	Measured hardness at distance d , in HRC or HV	–
J_{xx-d}	Jominy hardenability index at distance d , in Rockwell HRC-mm	–
JHV_{xx-d}	Jominy hardenability index at distance d , in Vickers HV 30-mm	–

5 Principle

The test consists of:

- heating a cylindrical test piece to a specified temperature in the austenitic range for a specified period of time;
- quenching it by spraying water on one of its ends under specified conditions;
- measuring the hardness at certain given points (see 9.4), on flats made along the axis of the test piece, in order to determine the hardenability of the steel by variations of this hardness.

By agreement and for a defined field of application, the test described in this document can be replaced by the calculation of the Jominy curve in accordance with an accepted mathematical model (see Annex C). In case of dispute, the test shall be carried out.

6 Form of test pieces and their preparation

6.1 Sampling

In the absence of specific requirements in the product standard, and unless otherwise agreed on the order and regardless of the thickness (or diameter) of the product, the sampling of test piece from the product can be made:

- either by hot rolling or forging of test piece with 30 mm to 32 mm diameter;
- or by machining of a test piece with diameter $(25^{+0,5}_0)$ mm whose axis shall be at (20^{+5}_0) mm from one of the surfaces of the product (see Figure 1).


In case of products from continuous casting, a minimum reduction ratio 5:1 is recommended before sampling.

In all the forming processes preceding the machining of the test piece, the deformation of the product from all sides should be as uniform as possible.

In the case of a separately cast reference test piece, the original cross section before deformation shall be at least three times that corresponding to the required diameter of 30 mm to 32 mm.

By special agreement, the test piece can be obtained by a suitable casting process and tested in the as-cast condition.

The flats of the test piece shall have their axes at approximately the same distance from the product surface (see Figure 1). For this purpose, the test piece shall be marked so that its position in the round bar can be clearly recognized.

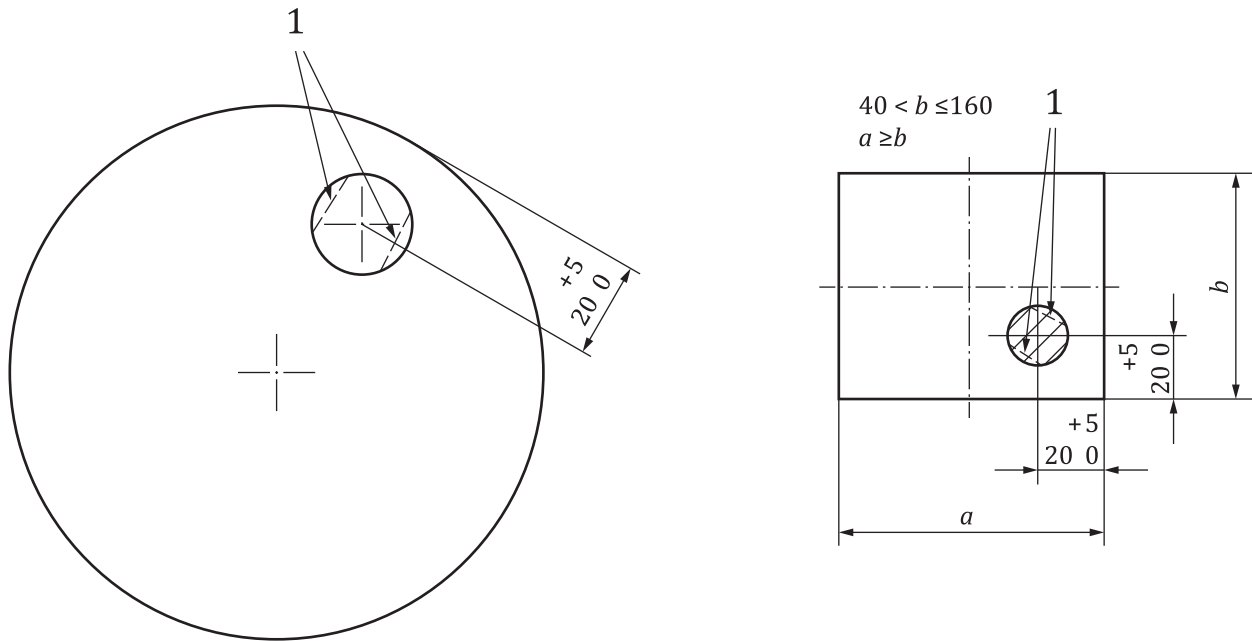

Key


1 test flats for measuring the hardness

Figure 1 — Sampling of the test piece for machining

6.2 Dimensions

6.2.1 The test piece shall consist of a round bar machined to a diameter of 25 mm and a length of at least 100 mm.

6.2.2 The end of the test piece which will not be quenched shall be 30 mm to 32 mm or 25 mm in diameter, depending upon the form of that end. Two examples, test pieces with a flange or an undercut (to permit rapid centring and fitting in position for the quenching operation by means of an appropriate support) are shown in [Figure 2](#).

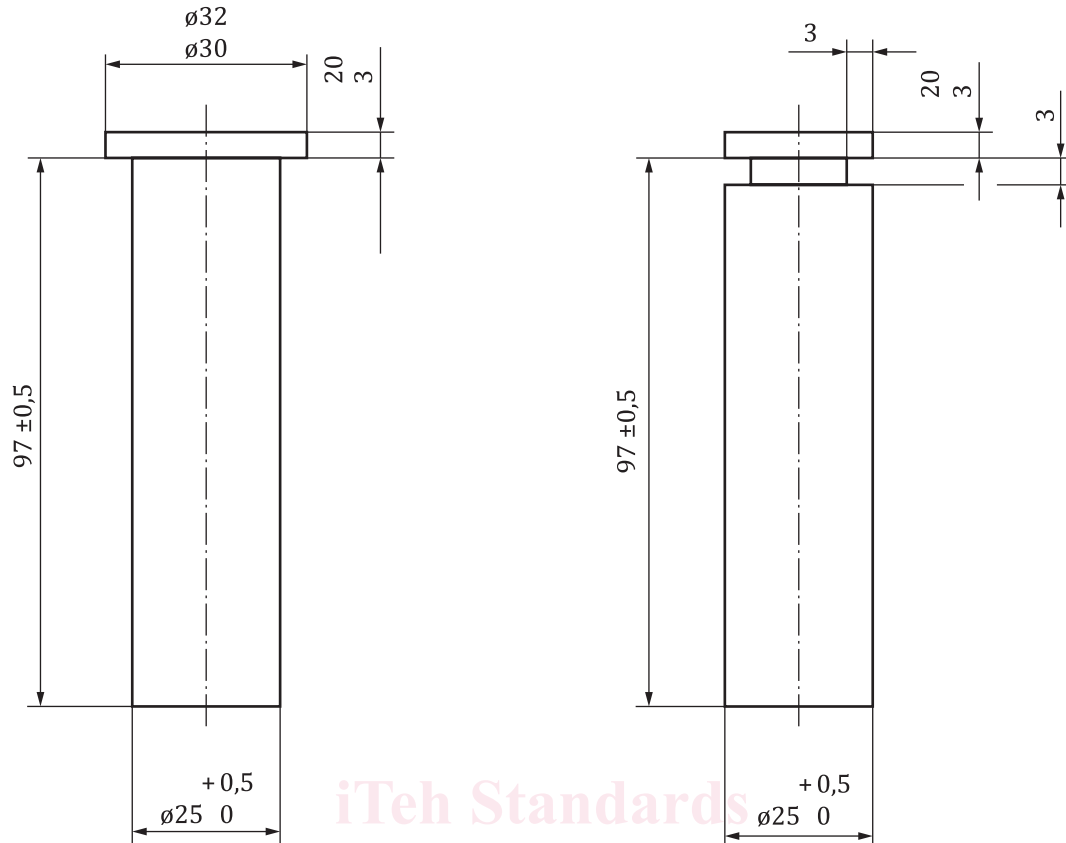

Flange thickness can be from 3 mm up to and including 20 mm. In case of dispute, reference sample flange thickness shall be 3 mm; sample length shall be $100 \pm 0,5$ mm.

Figure 2 — Dimensions of test piece

<https://standards.iteh.ai/catalog/standards/iso/0b7827a2-70ca-44a7-808a-b8124a2ed1b9/iso-fdis-642>

6.2.3 The test piece shall, if necessary, be marked (on the end opposite to the end to be quenched) to enable its position to be identified in relation to the original product.

6.3 Heat treatment

If not specified in the material standard or by mutual agreement, the heat treatment of the sample is left to the discretion of the test laboratory. Normalising (typically 30 to 60 minutes) or other heat treatment can be agreed at the time of enquiry and order. The heat treatment shall be carried out in each case in such a way that the finish-machined test piece shows no traces of decarburization.

6.4 Machining

The cylindrical surface of the test piece shall be machined by fine turning; the surface of the test piece end to be quenched shall have a reasonably fine finish, preferably obtained by fine grinding, and should be free from burrs (see [Figure 2](#)).

7 Apparatus

The apparatus consists of a device for quenching the test piece.

7.1 The quenching device consists essentially of a means of suddenly inducing the water jet to impinge on the end of the test piece to be quenched. This can be realized, for example, by a quick action tap and a system