



Designation: D5662 – 13

# Standard Test Method for Determining Automotive Gear Oil Compatibility with Typical Oil Seal Elastomers<sup>1</sup>

This standard is issued under the fixed designation D5662; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This test method<sup>2</sup> covers the determination of the compatibility of automotive gear oils with specific nitrile, polyacrylate, and fluoroelastomer oil seal materials.

1.2 Users of this test method should obtain Test Methods **D412**, **D471**, and **D2240** and become familiar with their use before proceeding with this test method.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>3</sup>

**D412** Test Methods for Vulcanized Rubber and Thermoplastic Elastomers—Tension

**D471** Test Method for Rubber Property—Effect of Liquids

**D2240** Test Method for Rubber Property—Durometer Hardness

**D5704** Test Method for Evaluation of the Thermal and Oxidative Stability of Lubricating Oils Used for Manual Transmissions and Final Drive Axles

**D5760** Specification for Performance of Manual Transmission Gear Lubricants

**E29** Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

2.2 *SAE Standard:*<sup>4</sup>

**J2360** Lubricating Oil, Gear Multipurpose (Metric) Military Use

## 3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

3.1.1 *dumbbell, n*—the specific cut shape (Die C) of an elastomer as explained in the section on dumbbell specimens in Test Methods **D412**.

3.1.2 *formulation, n*—the specific chemical composition used in manufacturing a seal elastomer or a reference oil.

3.1.3 *percent ultimate elongation, n*—the stretch length at rupture of an elastomer dumbbell oil-aged by running this procedure minus the rupture stretch length of an untested dumbbell, all divided by rupture stretch length of the untested dumbbell and then multiplied by 100.

3.1.4 *percent volume change, n*—the change in volume of a test specimen as explained in the procedure for change in volume in Test Method **D471**.

## 4. Summary of Test Method

4.1 Non-reference oils are tested using a modified version of Test Method **D471** on specific elastomer compounds. Measured quantities are percent ultimate elongation changes (further referred to as just percent elongation changes), durometer Type A hardness changes, and percent volume changes. Reference oils are run concurrently in the same oil bath to measure consistency from one test to another.

4.2 The duration of these tests is 240 h. The reference oils are available from the ASTM Test Monitoring Center (TMC).<sup>5</sup> The seal materials are available through a Central Parts Distributor (CPD).<sup>6</sup>

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee **D02** on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee **D02.B0.03** on Automotive Gear Lubricants & Fluids.

Current edition approved Oct. 1, 2013. Published October 2013. Originally approved in 1995. Last previous edition approved in 2012 as D5662 – 12a. DOI: 10.1520/D5662-13.

<sup>2</sup> Until the next revision of this test method, the ASTM Test Monitoring Center will update changes in this test method by means of Information Letters; these can be obtained from the ASTM Test Monitoring Center, 6555 Penn Ave., Pittsburgh, Pa 15206-4489. Attention: Administrator. This edition incorporates revisions in all Information Letters through No. 13-1.

<sup>3</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>4</sup> Available from Society of Automotive Engineers (SAE), 400 Commonwealth Dr., Warrendale, PA 15096-0001, http://www.sae.org.

<sup>5</sup> Reference oils are available from the ASTM Test Monitoring Center, 6555 Penn Ave., Pittsburgh, Pa 15206-4489.

<sup>6</sup> The Central Parts Distributor for this procedure is Test Engineering Inc., 12758 Cimarron Path, Suite 102, San Antonio, TX 78249.

\*A Summary of Changes section appears at the end of this standard

## 5. Significance and Use

5.1 There are several major causes of automotive lubricant-related seal failures. This test method addresses only those failures caused by excessive elastomer hardening, elongation loss, and volume swell and attempts to determine the likelihood that an oil might cause premature sealing system failures in field use. This test method may be used as a requirement of a performance specification, such as Specification **D5760** and **J2360**.

5.2 Another major cause of seal failure is the formation of carbon, varnish, and sludge-like deposits on the seal lip. The deposit-forming characteristics of automotive gear oils are evaluated in Test Method **D5704**. That procedure is intended in part to evaluate the potential for oils to cause premature seal failure in field service.

## 6. Apparatus

6.1 Specific test equipment as outlined in Test Methods **D412**, **D471**, and **D2240** is required.

6.1.1 *Hardness Durometer*—See Test Method **D2240**.

6.1.1.1 *Calibration*—Calibrate the hardness durometer annually. Use an outside source, with standards traceable to National Institute for Standards Technology (NIST) for annual calibration. Perform checks with internal standards weekly. Checks with internal standards shall be within  $\pm 3$  points. Calibrate internal standards annually, using an outside source, with standards traceable to NIST.

6.1.2 *Tension Testing Machine*—See Test Method **D412**. Set the testing machine rate of grip separation for the percent elongation change determinations at  $(8.5 \pm 0.8)$  mm/s. Calibrate the tension testing machine in accordance with **Annex A2** or **Annex A3**, as appropriate.

6.1.2.1 *Calibration*—Calibrate the tension testing machine annually. The manufacturer shall perform an annual calibration, using NIST traceable standards.

6.1.3 *Glass Tubes*, having an outside diameter of 38 mm and an overall length of 300 mm. The tube is fitted loosely with an aluminum foil-covered stopper.

6.1.4 *Balance*—Use any commercially available balance capable of weighing samples to the nearest 1.0 mg.

6.1.4.1 *Calibration*—Calibrate the balance annually. Use an outside source, with standards traceable to NIST for annual calibration. Perform checks with internal standards monthly, using NIST traceable weights. The difference between the weights and balance shall be  $< 0.5$  mg. Calibrate internal standards annually, using an outside source, with standards traceable to NIST.

## 7. Reagents and Materials

7.1 Specific reference test oils are maintained and distributed by the TMC.<sup>5</sup> To receive the test oils and seal materials, individual laboratories shall commit to furnishing the TMC with reference data developed using these reference materials.

7.2 The CPD is responsible for maintaining the numbering and tracking system for the seal elastomer batches used. The Surveillance Panel is responsible for approval of elastomer batches (see **Appendix X1**). Only approved elastomer batches are to be used for reference tests and tests run to meet industry

specifications. Certain specific information concerning these reference materials is available only to the CPD. This information is used to ensure batch-to-batch consistency.

7.2.1 Information and location of the current CPD is also available from the TMC.

7.3 Specific reference seal elastomers used are a nitrile (NI), a polyacrylate (PA), and a fluoroelastomer (FL). Notation of the numbering system is established by the TMC as follows:

[Type] Y

where:

Type = NI, PA, FL, and

Y = Batch number of the particular formulation.

7.4 The shelf life for the seal elastomers is two years from the date the batch was cured. Invalidate any test with a seal cure date older than two years. Consult the TMC for any approved exceptions to this lifespan. Place a note in the comments section of the test report where exceptions have been approved.

7.4.1 Store elastomers in a refrigerator maintained at (3 to 6) °C.

7.5 The shelf life of reference oils is typically five years unless the TMC, through their analysis, specifies otherwise.

7.6 Wetting solution of Aerosol OT—0.1 % sodium dioctyl sulfosuccinate, made by a 1.0 % dilution of a 10 % solution with reagent water.

## 8. Procedure

8.1 The testing laboratory shall conduct reference oil tests concurrently with the non-reference oil in the same oil bath. Reference oils shall perform within a specific range prescribed and evaluated by TMC for validity and updated as needed.

8.2 Prior to cutting specimens and prior to performing elongation tests for initial properties, allow 3 h for the elastomer to warm to  $(23 \pm 2)$  °C, as required by Test Method **D412**. Referring to the procedure in Test Method **D412**, use Die C to cut a set of twelve dumbbell specimens out of the elastomer sheets as required for each reference and non-reference oil tested.

8.2.1 Cut the dumbbells parallel to the grain using the same unaltered dies for the entire lot. When cutting dumbbells, only cut one thickness at a time to avoid any dimensional variations.

8.2.2 Cut all elastomer specimens, including those used for measuring initial properties, from the same elastomer batch. Use these dumbbells for measuring the percent elongation changes.

8.2.3 Next, cut twelve (25 by 50) mm by  $(2.0 \pm 0.1)$  mm rectangular specimens for the percent volume change and hardness testing.

8.2.4 Finally, cut twelve more NI, PA, and FL dumbbells for the purpose of determining initial elongation properties.

8.2.5 Randomly select sets of twelve dumbbells and twelve rectangular specimens for testing from the different sheets of test elastomers.

8.2.6 Use the water displacement procedure in accordance with Test Method **D471** to determine the initial volume measurements. Weigh the coupon in air, M1, to the nearest

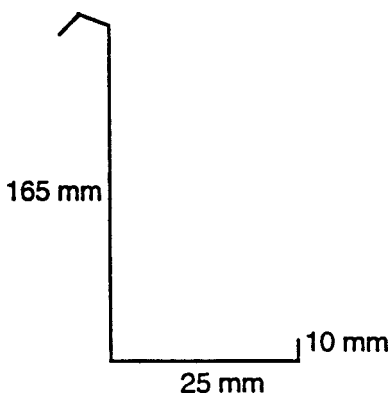


FIG. 1 Wire Hanger

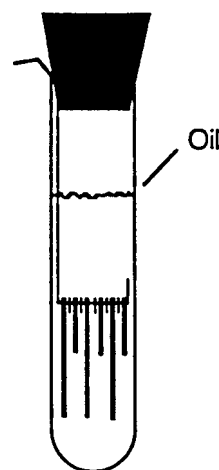


FIG. 2 Test Tube Arrangement

1 mg. For the mass in water, immerse the coupon in a 1.0 % wetting solution of aerosol OT, then place the coupon in distilled water, M2, at ambient temperature. Make sure no air bubbles are clinging to the coupon surface before recording the mass to the nearest 1 mg.

8.2.7 Ensure that initial elastomer properties of hardness and volume are determined prior to the start of testing. Initial elongation properties are determined just prior to running the end of test dumbbells because of instrument calibration.

8.3 Fill the test tubes with (150 ± 5) mL of non-reference or reference oil as appropriate.

8.4 Use four test tubes for each elastomer/oil combination. In each tube, suspend from a stainless steel wire hanger bent at a 90° angle (dimensions shown in Fig. 1) three rectangular specimens and three dumbbells in each of the four tubes. Place spacers in between the specimens to aid in the separation. The width of the spacer(s) shall be (1.7 ± 0.3) mm. The spacer material shall not affect the liquid or the rubber.

8.4.1 Fig. 2 shows the arrangement of spacers and test specimens.

8.4.2 Top the test tube with a stopper wrapped in aluminum foil.

8.4.3 Test the non-reference oil using one or more of the three different seal elastomers with the same batch of elastomers as being used for the reference oil.

8.4.4 Place the tubes randomly in an oil bath capable of maintaining a test oil temperature within ± 1 °C for a period of (240 ± 0.5) h (see Table 1).

8.4.4.1 Measure the test oil temperature with a thermocouple or resistance temperature detector (RTD) inside a dummy test tube containing bath oil within the oil bath.

8.4.4.2 Record test oil temperature at a minimum of once every minute.

8.4.4.3 Calculate the percent deviation for the elastomer material test oil temperature shown in Table 1 using the following equation. Record the results in the test report.

$$\text{percent deviation} = \sum_{i=1}^n \left( \frac{Mi}{0.5R} \times \frac{Ti}{D} \right) \times 100 \quad (1)$$

*Mi* = absolute value of the magnitude of the test parameter out of specification limit at occurrence *i*,

TABLE 1 Test Oil Temperatures

Material	Test Oil Temperature, °C	Percent Deviation Limits
Nitrile	100 ± 1	1%
Polyacrylate	150 ± 1	1%
Fluoroelastomer	150 ± 1	1%

*R* = test parameter specification range,  
*Ti* = length of time the test parameter was outside of specification range at occurrence *i*. (*Ti* is assumed to be no less than the recorded data-acquisition frequency, unless supplemental readings are documented), and  
*D* = test duration in same units as *Ti*.

8.4.4.4 Invalidate any test that exceeds the percent deviation limits in Table 1.

8.4.5 Conduct all reference and non-reference oil testing on each seal elastomer in the same oil bath. Complete reference oil and non-reference oil tests for each seal elastomer within 8 h of each other to be considered the same test.

8.5 At the end of the test period, remove the specimens from the hot oil using the wire hanger and place them on a clean absorbent towel. Allow the specimens to cool for no longer than 30 min.

8.5.1 Remove the specimens from the wire hanger, and place them on a clean absorbent towel. Remove the excess oil with a clean absorbent towel, and begin testing.

8.6 Determine type A hardness testing, percent volume in air and water, and percent elongation, as done in 8.2.6 and 8.2.7. Complete testing within 2 h of removal from the test oil.

8.7 Observe the following notes/modifications to Test Method D471.

8.7.1 Report percent change in elongation (see Test Method D412) and percent volume change (see Test Method D471) from the original using the same water displacement procedure described in 8.2.6.

8.7.1.1 When using a wire hanger to aid in the weighing of the test coupon, deduct the mass of the wire hanger from the gross mass to determine the actual mass of the test coupon.

Record the actual mass of the test coupons in the test report and use the actual masses for the percent volume change calculations.

8.7.1.2 Conduct all reference and non-reference oil testing on each seal elastomer in an oil bath capable of maintaining a test oil temperature within  $\pm 1^\circ\text{C}$  for a period of  $(240 \pm 0.5)$  h (see [Table 1](#)).

8.7.2 Report durometer Type A hardness change points from original (see Test Method [D2240](#)).

8.7.2.1 On a hard horizontal surface, stack the three rectangular specimens on top of each other to obtain the 6 mm thickness required by Test Method [D2240](#). Take hardness readings 1 s after the pin makes contact with the elastomer. Take three readings on each side of the rectangular specimen and report the average of all six readings.

8.7.2.2 After taking the first set of measurements, rotate the bottom specimen to the top of the stack and take a second set of measurements.

8.7.2.3 Rotate the bottom specimen to the top one more time to obtain the third set of measurements.

8.7.3 For each data set, calculate the average value and the sample standard deviation using the equation:

$$\sigma = \sqrt{\frac{\sum (x_i - \bar{x})^2}{n - 1}} \quad (2)$$

where:

- $\sigma$  = sample standard deviation,
- $n$  = number of data points in the set,
- $X_i$  = individual data set value,
- $\bar{x}$  = mean of the data set.

Change in volume, % =  $[(M3 - M4) - (M1 - M2)] / (M1 - M2) \times d \times 100$

where:

- $M1$  = the original mass in air,
- $M2$  = the original mass in water,
- $M3$  = the end of test mass in air,
- $M4$  = the end of test mass in water, and
- $d$  = the density of the medium in which the specimen was weighed. In this case water is used, so the multiplication is by 1.

## 9. Reference Oil Testing

9.1 Test the TMC reference oils along with each batch of non-reference oil tests. Run the reference oils simultaneously with, and in the same bath as, the non-reference oils.

NOTE 1—[Annex A1](#) discusses the involvement of the ASTM TMC with respect to the reference test-monitoring program.

9.1.1 Prior to requiring a reference oil test, procure a supply of reference oils directly from the TMC. These oils have been formulated or selected to represent specific chemistry types, or performance levels, or both. Each reference oil sample is identified using a unique set of identification codes on the container labels.

9.1.1.1 The testing laboratory tacitly agrees to use the TMC reference oils exclusively in accordance with the TMC's

published Policies for Use and Analysis of ASTM Reference Oils, and to run and report the reference oil test according to TMC guidelines.

NOTE 2—Policy for the Use and Analysis of ASTM Reference Oils is available from the TMC.

9.1.2 Request reference oil assignments from the TMC for this test method. The TMC determines the specific reference oils to be tested by the laboratory. Assignments will be made by the unique identifying codes on the reference oil container labels. Provide the TMC with the bath identification number for each test.

9.1.3 Run the TMC reference oil tests according to the test method and in the same manner as the non-reference oil test(s).

9.1.4 *Reporting of Reference Oil Test Results*—For reference oil tests, the standardized report form set and data dictionary for reporting the test results and for summarizing the operational data are required. The report forms and data dictionary are available on the ASTM Test Monitoring Center Web Page at <http://www.astmtmc.cmu.edu/> or can be obtained in hardcopy format from the TMC.

9.1.4.1 Report the reference oil test results to the TMC within five days of completion.

9.1.4.2 Report only the reference oil results to the TMC. Do not include any non-reference test data. Complete all of the required blank fields on the forms. Round test results according to Practice [E29](#).

9.1.4.3 For electronic transfer of test results, use the ASTM Data Communications Committee Test Report Transmission Model (see Section 2—Flat File Transmission Format) available from the ASTM TMC.

9.1.5 *Evaluation of Reference Test Oil Results*—Upon receipt of the transmitted TMC reference oil test results, the TMC reviews the tests for operational adherence to the published test method. If the tests are found to be operationally valid, the reference oil results are evaluated using acceptance criteria established by the governing surveillance panel. The reference oil acceptance criteria are subject to change at the discretion of the surveillance panel.

9.1.5.1 If the transmitted tests are found to be both operationally valid and statistically acceptable, the testing laboratory will be notified of the acceptable status of the reference test.

9.1.5.2 In the event that a TMC reference oil test is found to be unacceptable, an explanation of the problem relating to the failure will be provided to the testing laboratory. If there is an obvious operational reason for the failed test, the problem shall be corrected before requesting additional TMC reference oil assignments. If the reason for the failure is not obvious, all test-related equipment shall be re-checked for compliance to the test method and good laboratory practice. Following this re-check, the TMC assigns the necessary TMC reference oils for testing.

9.1.5.3 Should a reference test be determined to be statistically or operationally invalid, repeat all testing on that particular oil/elastomer pair.

9.1.6 *Status of Non-reference Oil Tests Relative to TMC Reference Oil Tests*—The batch of non-reference oil tests, that