

FINAL  
DRAFT

INTERNATIONAL  
STANDARD

ISO/FDIS  
9692-2

ISO/TC 44/SC 7

Secretariat: BSI

Voting begins on:  
2023-09-13

Voting terminates on:  
2023-12-06

---

---

## Welding and allied processes — Joint preparation —

### Part 2: Submerged arc welding of steels

*Soudage et techniques connexes — Préparation de joints —  
Partie 2: Soudage à l'arc sous flux en poudre des aciers*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/FDIS 9692-2

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>

ISO/CEN PARALLEL PROCESSING

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number  
ISO/FDIS 9692-2:2023(E)

© ISO 2023

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/FDIS 9692-2

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Materials.....	1
5 Types of joint preparation.....	1
Bibliography.....	10

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

[ISO/FDIS 9692-2](https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2)

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 7, *Representation and terms*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 121, *Welding and allied processes*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 9692-2:1998), of which it constitutes a minor revision. The changes are as follows:

- [Clause 1](#), fourth paragraph revised and moved to the Introduction;
- ISO 2553, ISO 6947 and ISO 9692-1 moved from [Clause 2](#) to the Bibliography;
- alignment in [Clause 5](#) of the note explaining the reference numbers in [Tables 1](#) and [2](#) with the corresponding text in ISO 9692-3;
- modification of the reference numbers in [Tables 1](#) and [2](#) in accordance with the latest version of ISO 2553 and reordering of the lines of the tables in ascending order of the new reference numbers.

A list of all parts in the ISO 9692 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html). Official interpretations of ISO/TC 44 documents, where they exist, are available from this page: <https://committee.iso.org/sites/tc44/home/interpretation.html>.

## Introduction

This document is intended to be used alongside ISO 9692-1. It follows similar rules and the same layout. Therefore, the introduction given in ISO 9692-1 also applies.

ISO 9692-1 specifies joint preparations for other arc welding processes (see ISO 4063), which are applicable when the root is not welded by submerged arc welding.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/FDIS 9692-2](https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2)

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>



# Welding and allied processes — Joint preparation —

## Part 2: Submerged arc welding of steels

### 1 Scope

This document applies to types of joint preparation for submerged arc welding with one wire electrode (process 121 according to ISO 4063) on steel.

This document covers only the welding positions PA and PB according to ISO 6947. If PC is used, special preparation is necessary.

This document applies to fully penetrated welds. For partly penetrated welds, types of joint preparation, shapes and dimensions can differ from the listed proposals if they are specified in the relevant application standard or agreed by the parties concerned.

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 15609-1, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 1: Arc welding* [DIS 9692-2](https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2)

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>

### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 4 Materials

Joint preparations recommended in this document are suitable for all types of weldable steel.

### 5 Types of joint preparation

The recommended types of joint preparation and dimensions are specified in [Table 1](#) and [Table 2](#).

The root gaps referred to in this document are those gaps presented after tack welding, if used.

This document gives no dimensions or type of possibly used backing materials. Root runs may also be used as backing. They may influence the quality requirements for welding (according to the relevant part of the ISO 3834 series) and the preparation as given in [Table 1](#) and [Table 2](#). They shall be part of the welding procedure specification in accordance with ISO 15609-1.

## ISO/FDIS 9692-2:2023(E)

According to the application standard or agreement between contracting parties, it can be necessary to grind the slag before welding the next run.

The reference numbers in [Tables 1](#) and [2](#) have been determined in accordance with the following scheme:

- the first digit corresponds with the number of the table (e.g. digit 1 for [Table 1](#) with joint preparation for butt welds, welded from one side);
- the second digit or numerical group corresponds with the number in ISO 2553 (e.g. digit 1 for square butt weld as given in ISO 2553:2019, Table 1);
- the third indication, expressed by a letter, covers the variants of joint preparations.

EXAMPLE Joint preparation for a butt weld, welded from one side (1), finished for single-V butt weld (2):

**1.2**

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/FDIS 9692-2](#)

<https://standards.iteh.ai/catalog/standards/sist/ee48877b-067b-4fbf-90a2-929a8faced0d/iso-fdis-9692-2>



Table 1 — Joint preparations for butt welds, welded from one side

Dimensions in millimetres




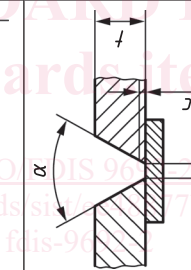

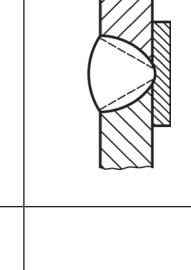

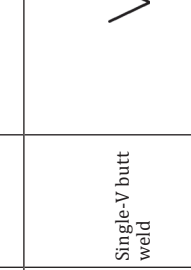
Weld		Joint preparation					Welding position (in accordance with ISO 6947)	Remarks		
Ref. no.	Work-piece thickness $t$	Designation	Symbol (in accordance with ISO 2553)	Illustration	Cross-section	Angle $\alpha, \beta$	Gap $b$ Radius $R$	Thickness of root face $c$	Depth of preparation $h$	
1.1	$3 \leq t \leq 12$	Square butt weld				—	$b \leq 0,5 t$ max. 5	—	—	With backing minimal thickness for backing: 5 mm or $0,5 t$
1.2	$10 \leq t \leq 20$	Single-V butt weld	V			$30^\circ \leq \alpha \leq 50^\circ$	$4 \leq b \leq 8$	$c \leq 2$	—	With backing minimal thickness for backing: 5 mm or $0,5 t$
1.2.2	$t > 12$	Single-V butt weld with V root	∩			$60^\circ \leq \alpha \leq 70^\circ$ $4^\circ \leq \beta \leq 10^\circ$	$1 \leq b \leq 4$	$0 \leq c \leq 3$	$4 \leq h \leq 6$	Root run welded with optional welding process
1.2.6	$t \geq 12$	Single-U butt weld with V root	∪			$60^\circ \leq \alpha \leq 70^\circ$ $4^\circ \leq \beta \leq 10^\circ$	$1 \leq b \leq 4$ $5 \leq R \leq 10$	$0 \leq c \leq 3$	$4 \leq h \leq 6$	Root run welded with optional welding process

Table 1 (continued)

Weld						Joint preparation					Welding position (in accordance with ISO 6947)	Remarks
Ref. no.	Work-piece thickness $t$	Designation	Symbol (in accordance with ISO 2553)	Illustration	Cross-section	Angle $\alpha, \beta$	Gap $b$ Radius $R$	Thickness of root face $c$	Depth of preparation $h$			
1.4	$3 \leq t \leq 16$	Single-bevel butt welded				$30^\circ \leq \beta \leq 50^\circ$	$1 \leq b \leq 4$	$c \leq 2$	—	PA PB	With backing minimal thickness for backing: 5 mm or 0,5 t	
1.6	$t \geq 30$	Single-U butt weld				$4^\circ \leq \beta \leq 10^\circ$	$1 \leq b \leq 4$ $5 \leq R \leq 10$	$2 \leq c \leq 3$	—	PA	With backing minimal thickness for backing: 5 mm or 0,5 t	