

FINAL
DRAFT

TECHNICAL
REPORT

ISO/DTR
20659-1

ISO/TC 35/SC 9

Secretariat: BSI

Voting begins on:
2023-11-17

Voting terminates on:
2024-01-12

Rheological test methods — Fundamentals and interlaboratory comparisons —

Part 1:
Determination of the yield point

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/DTR 20659-1](https://standards.iteh.ai/catalog/standards/sist/ef1c3129-f524-45ac-9ac6-3910deafa118/iso-dtr-20659-1)

<https://standards.iteh.ai/catalog/standards/sist/ef1c3129-f524-45ac-9ac6-3910deafa118/iso-dtr-20659-1>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/DTR 20659-1:2023(E)

© ISO 2023

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/DTR 20659-1](#)

<https://standards.iteh.ai/catalog/standards/sist/ef1c3129-f524-45ac-9ac6-3910deafa118/iso-dtr-20659-1>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Goal of the interlaboratory test	1
5 Metrological determination of the yield point	2
5.1 General.....	2
5.2 Shear rate-controlled rotational test.....	2
5.3 Yield point evaluation using flow curve regression models.....	2
5.4 Shear stress-controlled rotational test.....	4
5.5 Evaluation methods for yield points.....	4
5.5.1 General.....	4
5.5.2 Axis intercept for presentation of the flow curve using a linear scale.....	4
5.5.3 Plateau value for presentation of the flow curve using a logarithmic scale.....	5
5.5.4 Yield point evaluation at a reference value.....	5
5.5.5 Methods with regression lines for presentation in the $\lg \gamma / \lg \tau$ diagram.....	6
5.5.6 Rotational test: viscosity maximum method.....	7
5.5.7 Tests with constant shear rate.....	8
5.5.8 Creep test.....	9
5.5.9 Oscillatory test: amplitude sweep.....	10
6 Results of the comparative testing programme	12
6.1 Performance of the tests.....	12
6.1.1 Preliminary tests.....	12
6.1.2 Comparative testing programme.....	12
6.2 Measuring samples.....	12
6.3 Method used for determination of the yield point.....	13
7 Result	14
8 Rheometer calibration and measurement uncertainty	15
Annex A (informative) Explanatory notes	16
Bibliography	18

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

A list of all parts in the ISO 20659 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Rheological test methods — Fundamentals and interlaboratory comparisons —

Part 1: Determination of the yield point

1 Scope

This document gives information on an interlaboratory comparison for the determination of the yield point, using rheological test methods. The yield point is the shear stress τ below which a material does not flow.

This document provides examples of fields of applications, in which important material properties are characterized with the aid of the yield point. These fields of application include:

- effectiveness of rheological additives;
- shelf life (e.g. with regard to sedimentation, separation and flocculation);
- stability of the structure at rest;
- behaviour when starting to pump;
- use in scraper systems;
- wet-film thickness;
- levelling and sagging behaviour (e.g. without brushmarks or sag formation);
- orientation of effect pigments.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3219-1, *Rheology — Part 1: Vocabulary and symbols for rotational and oscillatory rheometry*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 3219-1.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Goal of the interlaboratory test

In the interlaboratory test, different possibilities for determining the yield point using the preferred methods were considered.

The samples used in the comparative testing programme consisted of different waterborne basecoats with lower yield points and dispersions with distinctly higher yield points. The samples also included the following limited cases:

- very low yield points (<1 Pa), at which the range of elastic deformation is so low that the material can also be approximately considered as a liquid at the state of rest;
- materials of which the internal structure is disintegrated only stepwise so that a transition range is occurring and a yield zone rather than a punctual yield point is determined.

Furthermore, a non-Newtonian reference sample from the the National Metrology Institute of Germany (PTB) was also included in the comparative testing programme.

Some background information on the original interlaboratory test is given in [Annex A](#).


5 Metrological determination of the yield point

5.1 General

[Clause 5](#) briefly describes all the methods in use at the time of publication. In principle, the yield point depends on the temperature, the pressure and the thermal and mechanical history of the material. A detailed specification of the measuring profile is therefore a precondition for reproducible measurements.

5.2 Shear rate-controlled rotational test

The shear rate $\dot{\gamma}$ is specified in the form of a ramp, as shown in [Figure 1](#).

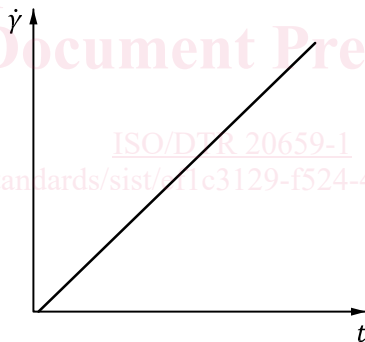

Key


$\dot{\gamma}$ shear rate

t time

Figure 1 — Shear rate/time function as a ramp

5.3 Yield point evaluation using flow curve regression models

With a linear representation of the flow curve (usually the shear stress τ as a function of the shear rate $\dot{\gamma}$), the yield point is determined as the axis intercept on the τ axis ([Figure 2](#)).

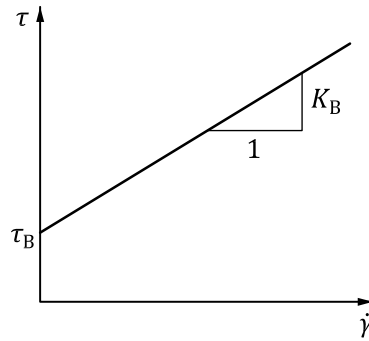**Key**

- τ shear stress
- τ_B Bingham yield point
- K_B consistency index according to Bingham
- $\dot{\gamma}$ shear rate
- 1 chosen shear rate range

Figure 2 — Flow curve regression according to Bingham

This yield point value depends not only on the specified ramp period, but also on the chosen shear rate range and the chosen regression model. In industrial laboratories, the models according to Bingham, Casson or Herschel/Bulkley are widely used.

The model function according to Bingham is given in [Formula \(1\)](#):

$$\tau = \tau_B + K_B \cdot \dot{\gamma} \quad (1)$$

where

τ is the shear stress; <https://standards.iso.org/standards/sist/ef1c3129-f524-45ac-9ac6-3910deafa118/iso-dtr-20659-1>

τ_B is the calculated Bingham yield point;

K_B is the consistency index according to Bingham;

$\dot{\gamma}$ is the shear rate.

The model function according to Casson is given in [Formula \(2\)](#):

$$\sqrt{\tau} = \sqrt{\tau_C} + \sqrt{(K_C \cdot \dot{\gamma})} \quad (2)$$

where

τ is the shear stress;

τ_C is the calculated Casson yield point;

K_C is the consistency index according to Casson;

$\dot{\gamma}$ is the shear rate.

The model function according to Herschel/Bulkley is given in [Formula \(3\)](#):


$$\tau = \tau_{HB} + K_{HB} \cdot \dot{\gamma}^p \quad (3)$$

where

- τ is the shear stress;
- τ_{HB} is the calculated yield point according to Herschel/Bulkley;
- K_{HB} is the consistency index according to Herschel/Bulkley;
- $\dot{\gamma}$ is the shear rate;
- p is an exponent; if $p < 1$, the flow behaviour is shear thinning (structural viscosity, pseudo-plastic), and if $p > 1$, the flow behaviour is shear thickening (dilatant).

5.4 Shear stress-controlled rotational test

The shear stress, τ , is specified in the form of a ramp, as shown in [Figure 3](#).

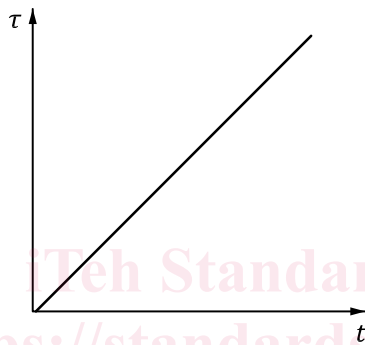

Key
 τ shear stress
 t time

Figure 3 — Specified profile: shear stress/time function as a ramp


5.5 Evaluation methods for yield points

5.5.1 General

Besides the specified ramp period, the yield point value above all depends on the resolution of the rheometer for the lowest rotational speed. At shear rates of $\dot{\gamma} < 1 \text{ s}^{-1}$, time-dependent (transient) effects are expected if the measuring point duration is too short.

5.5.2 Axis intercept for presentation of the flow curve using a linear scale

This is the “classic method” of the yield point determination. In the case of the upward ramp, the yield point τ_y is determined as the last τ value at which the rheometer does not yet detect movement of the measuring system, i.e. at which $\dot{\gamma} = 0 \text{ s}^{-1}$ is still measured. By contrast, in the case of the downward ramp, the yield point is determined as the first τ value at which the rheometer no longer detects movement, i.e. at which $\dot{\gamma} = 0 \text{ s}^{-1}$ is measured (see [Figure 4](#)).

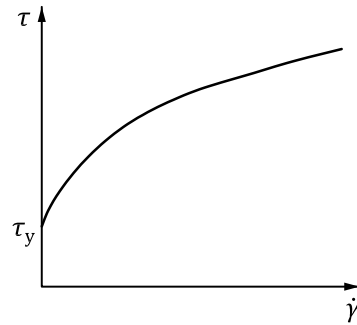
**Key**

- τ shear stress
- τ_y yield point
- $\dot{\gamma}$ shear rate

Figure 4 — Flow curve in a linear scale with the yield point as an axis intercept on the τ axis

5.5.3 Plateau value for presentation of the flow curve using a logarithmic scale

If the flow curve approaches a plateau value in the range of low shear rates, this τ value is taken as the yield point τ_y , as shown in [Figure 5](#).

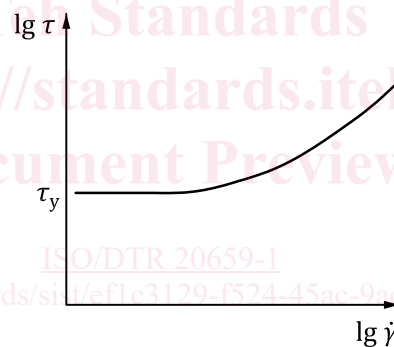
**Key**

- τ shear stress
- τ_y yield point
- $\dot{\gamma}$ shear rate

Figure 5 — Flow curve in a double-logarithmic scale with the yield point as a plateau value of the shear stress in the range of low shear rates

5.5.4 Yield point evaluation at a reference value

The flow curve specification can take the form of a $\dot{\gamma}$ ramp or a τ ramp. The yield value is determined as shown in [Figure 6](#) as the τ value at a shear rate previously defined by the user, e.g. $\dot{\gamma} = 0,01 \text{ s}^{-1}$.

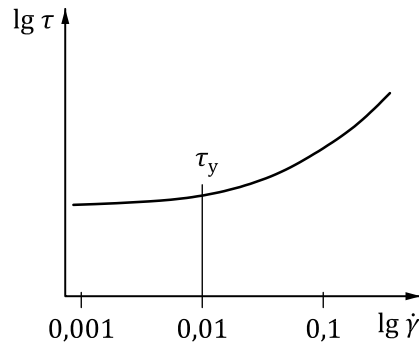


Key

- τ shear stress
- τ_y yield point
- $\dot{\gamma}$ shear rate

Figure 6 — Flow curve, determination of the yield point τ_y as the τ value with $\dot{\gamma} = 0,01 \text{ s}^{-1}$

5.5.5 Methods with regression lines for presentation in the $\lg \gamma / \lg \tau$ diagram

If a yield point is present, then a straight line becomes visible in the range of low shear load because then the shear stress τ and the shear strain γ are proportional at low values. The measured sample then demonstrates reversible linear-elastic deformation behaviour in accordance with Hooke’s law on elasticity. At higher loads the structure-at-rest disintegrates and the deformation then becomes disproportionately high, i.e. the material now demonstrates irreversible viscoelastic or viscous flow behaviour. The yield point is exceeded if the measuring points no longer lie on a straight line. If it is also possible to apply a second line through the measuring points in the flow range, i.e. when the deformation is high, the intersection point between the lines is evaluated as the yield point (see [Figure 7](#)).

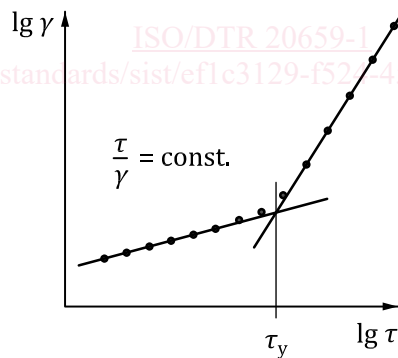

Key

- γ shear strain
- τ shear stress
- τ_y yield point

Figure 7 — Determination of the yield point using the method of the intersection point between two regression lines

If it is not easily possible to apply a second line, the regression line is only fitted in the lower range, i.e. in the linear-elastic range. The yield point is then the τ value at which the measuring curve deviates upwards from this line into the flow range (see [Figure 8](#)). If the internal structure of a material is disintegrated stepwise only so that no sharp edge but a transition range becomes visible, it is preferred to talk of a “yield transition zone” instead of a “yield point”. In this case, the evaluation method shown in [Figure 8](#) is preferred.