



Designation: B611 – 13

# Standard Test Method for Determining the High Stress Abrasion Resistance of Hard Materials<sup>1</sup>

This standard is issued under the fixed designation B611; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method was developed for ranking the high-stress abrasion resistance of cemented carbides, but it has been successfully used on ceramics, cermets, and metal matrix hardfacings with a hardness over 55 HRC. The feature of this test method that discriminates it from other abrasion tests is that the abrasive is forced against the test specimen with a steel wheel with sufficient force to cause fracture of the abrasive particles. Some abrasion tests use rubber wheels to force abrasive against test surfaces (Test Methods [G65](#), [G105](#), [G75](#)). A rubber wheel produces low-stress abrasion while a steel wheel produces high-stress abrasion.

1.2 In summary, this is a high-stress laboratory abrasion test for hard materials using a water slurry of aluminum oxide particles as the abrasive medium and a rotating steel wheel to force the abrasive across a flat test specimen in line contact with the rotating wheel immersed in the slurry.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

- [B311 Test Method for Density of Powder Metallurgy \(PM\) Materials Containing Less Than Two Percent Porosity](#)
- [G65 Test Method for Measuring Abrasion Using the Dry Sand/Rubber Wheel Apparatus](#)

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee [G02](#) on Wear and Erosion and is the direct responsibility of Subcommittee [G02.30](#) on Abrasive Wear.

Current edition approved Nov. 15, 2013. Published December 2013. Originally approved in 1976. Last previous edition approved in 2005 as B611–85 (2005). DOI: 10.1520/B0611-13.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[G75 Test Method for Determination of Slurry Abrasivity \(Miller Number\) and Slurry Abrasion Response of Materials \(SAR Number\)](#)

[G105 Test Method for Conducting Wet Sand/Rubber Wheel Abrasion Tests \(Withdrawn 2016\)<sup>3</sup>](#)

[G40 Terminology Relating to Wear and Erosion](#)

## 3. Terminology

3.1 *Definitions:* For definitions of terms found in this test method, please refer to Terminology [G40](#).

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *abrasive wear, n*—wear due to hard particles or hard protuberances forced against and moving along a solid surface.

3.2.2 *high-stress abrasion, n*—progressive material removal from a hard solid surface by the action of hard particles rolling or sliding on that surface with sufficient force to cause fracture of the particles.

3.2.3 *slurry, n*—a suspension of solid material in liquid.

## 4. Summary of Test Method

4.1 The test specimen is a flat that is held in a vertical position tangent to a rotating steel wheel immersed in water slurry of aluminum oxide particles.

4.2 The normal force holding the test specimen against the wheel is high enough to cause fracture of abrasive particles that travel through the wheel/test specimen contact. The test metric is the volume of material worn from the test specimen in specified test duration and under specified test conditions.

4.3 The test specimen is weighed to determine mass loss which is converted to a volume loss using the density of the test material.

4.4 The slurry used in the test is composed of a specified mass of 30-mesh aluminum oxide in a specified volume of water.

4.5 There may be a corrosion component to the material removal, but it is considered to be negligible since the test time is only ten or twenty minutes (600 or 1200 seconds).

<sup>3</sup> The last approved version of this historical standard is referenced on www.astm.org.

## 5. Significance and Use

5.1 The extraction of minerals from the Earth’s mantle usually requires fracturing rock with tools made from metals, but clad, overlaid, or covered in some fashion with hard materials. Drilling, crushing, and moving rock involves high-stress abrasion on the surfaces that make contact with the rock. The stresses are high enough to crush/fracture the rock. This test method simulates this condition, and it is used to screen new materials for these types of applications. It can also be used as a quality control tool for materials destined for high-stress abrasion applications: slurry pumps, comminution equipment, recycling choppers, demolition equipment, etc.

5.2 Most abrasion tests use low-stress abrasion. The abrasive stays relatively intact during testing. High-stress abrasion simulates applications where the force between an abrasive substance and a tool/component will be high enough to crush the abrasive. If this describes an application under study, then this may be an appropriate test method to use.

## 6. Apparatus


6.1 *General Description*—Fig. 1 is a schematic of the test rig. The test specimen (a) contacts a steel wheel (b) on its centerline; the water/grit slurry (c) is held in a slurry vessel; vanes, made from aluminum or steel (d) are on both sides of the steel wheel agitate the slurry. The load (force) is applied by a mass (e) that is constant throughout the test; the slurry can be replenished if needed (Note: slurry may splash out of uncovered machines) during the test, and the test duration and wheel rotational speed are fixed for the test.

6.2 *Abrading Wheel*—The wheel is made from AISI 1020 steel (80 to 95 HRB); the outside diameter is  $169 \pm 0.1$  mm when new and the wheel shall be discarded when its diameter wears below 165 mm. A burr develops during use. It should not be removed. The wheel is not dressed between uses. Four agitating vanes are attached at  $90^\circ$  increments on both sides of the wheel. The vanes must have a minimum radial clearance of 3 mm with the test sample when the wheel penetrates the test specimen to produce a wear scar (the vanes must not contact the specimen during testing). The wheel width is  $12.7 \pm 0.1$  mm.

6.3 *Test Specimen*—The test specimen dimensions are shown in Fig. 2 (from Test Method G65). It should have a surface roughness in the range of 0.1 to  $1 \mu\text{m Ra}$  on the test surfaces.


6.4 *Drive Motor*—A 1 hp motor with a gear reduction unit has been found suitable for use, but other motors (hydraulic or DC motors, etc.) could be used if they have the torque requirements to rotate the wheel with a 200 N “braking” force applied to the outside diameter. The wheel can be directly mounted to the drive or it can be mounted on a spindle which is driven by a motor. Whatever the mechanism, the radial runout of the wheel shall be less than  $\pm 0.01$  mm and widthwise runout shall be less than  $\pm 0.05$  mm. The motor speed shall be controlled to the specified rpm  $\pm 2$  rpm.

6.5 *Specimen Holder*—The centerline of the pivoting specimen holder should be aligned with the tangent point of the system with a new wheel. The sideways movement of the holder should be less than 0.2 mm and it should be designed to

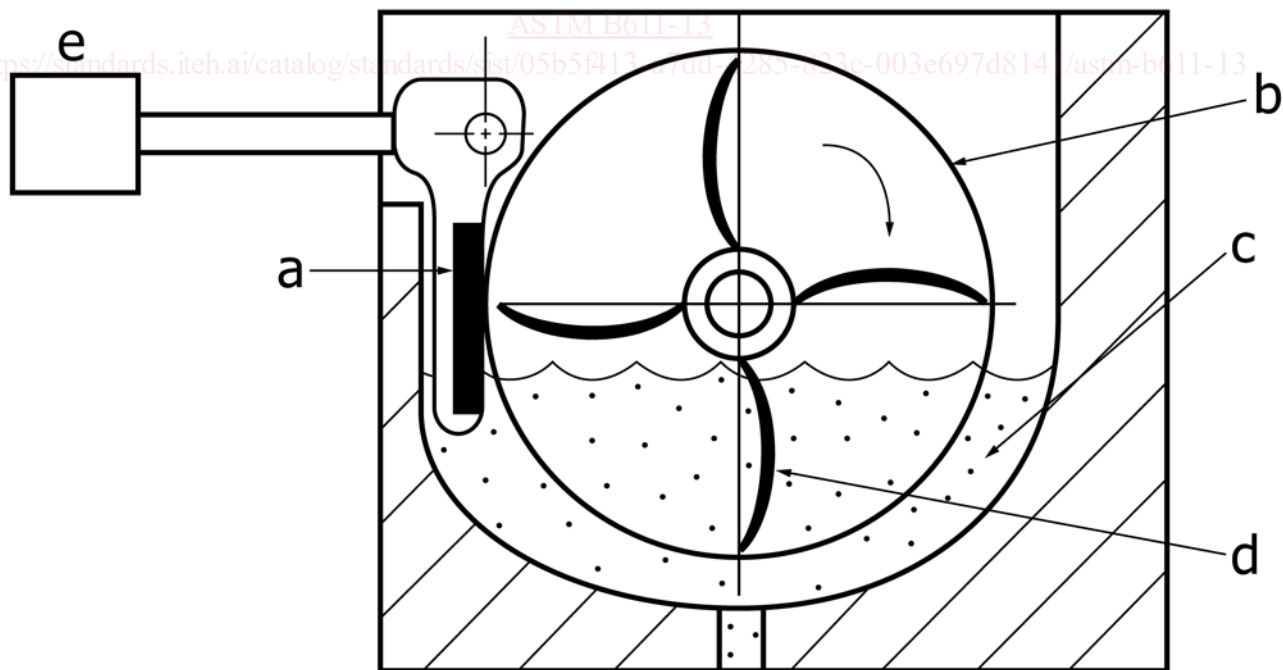

NOTE 1—“a” is the test specimen; “b” is the steel wheel; “c” is the test slurry; “d” are agitating vanes. They can have a slight curve as shown or flat. They can be from 3 to 13 mm high, but must have a minimum clearance of 3 mm on a side between the vanes and the vessel. They can be staggered so that the vanes on one side make an angle of  $45^\circ$  with the vanes on the other side. The mass producing the normal force is “e.”

FIG. 1 Schematic of Test Rig

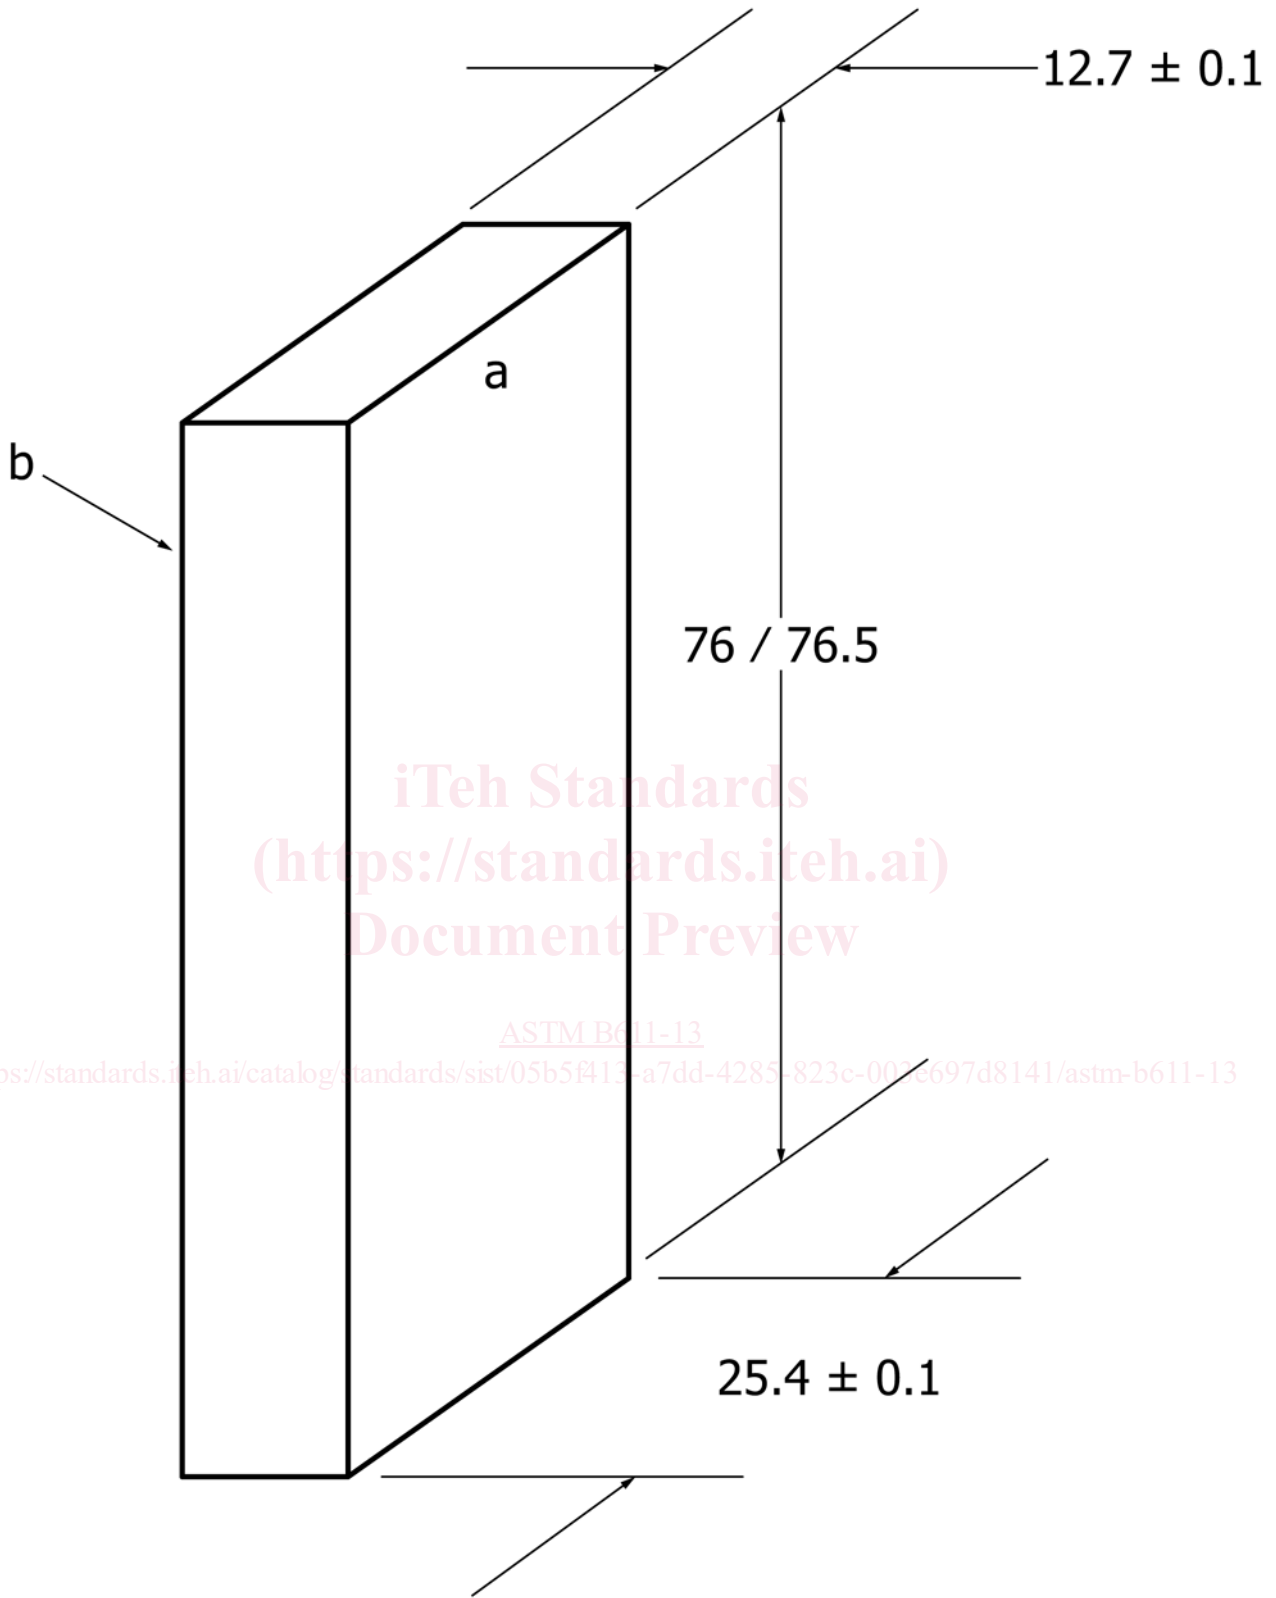

NOTE 1—Test specimen surface “a” must be flat within 0.01 mm and parallel with surface “b” within 0.01 mm. The surface roughness of the test surface/surfaces shall be less than 1  $\mu$ m Ra. All dimensions are in millimetres.

FIG. 2 Test Specimen Dimensions

place the wear scar in the center of the test specimen. Sub-sized test specimens can be held in special holders that allow the flat