



Designation: **E2256 – 03 (Reapproved 2008) E2256 – 13**

Standard Guide for Hydraulic Integrity of New, Repaired, or Reconstructed Aboveground Storage Tank Bottoms for Petroleum Service¹

This standard is issued under the fixed designation E2256; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This guide is intended to provide the reader with a knowledge of construction examination procedures and current technologies that can be used to give an owner or operator of an aboveground storage tank (AST) in petroleum service, relevant information on the hydraulic integrity of a new, repaired, or reconstructed tank bottom prior to return to service. This guide does not pertain to horizontal ASTs, manufacture of tanks using UL 142, or to tanks constructed of concrete or other non-ferrous materials.

1.2 The adoption of the methods and technologies presented in this guide are not mandatory, rather they represent options that may be selected to identify the likelihood of product leaking through a new, repaired, or reconstructed tank bottom.

1.3 This guide is not intended to suggest or treat any technology in a preferential manner.

1.4 The person responsible for applying this guide should be a knowledgeable individual with experience in the design, inspection, construction, or combination thereof, of aboveground storage tanks for use in petroleum service, and should also be certified under the requirements of API 653 when use is related to tank bottom repair.

1.5 This guide is written in metric measure units (SI Units) in accordance with requirements of Practice E621. English measure equivalents are in parentheses.

1.6 The applicability of this guide to the proposed tank configuration and service conditions should be established prior to use.

1.7 This guide complies with ASTM policy for development and subsequent use of a standard.

1.8 This guide is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this guide or for additional standards and should be addressed to ASTM International, 100 Barr Harbor Drive, W. Conshohocken, PA 19428.

1.9 This guide is not intended for use as a model code, ordinance or regulation.

1.10 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory requirements prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[A6/A6M Specification for General Requirements for Rolled Structural Steel Bars, Plates, Shapes, and Sheet Piling](#)

[A20/A20M Specification for General Requirements for Steel Plates for Pressure Vessels](#)

[A36/A36M Specification for Carbon Structural Steel](#)

[A53/A53M Specification for Pipe, Steel, Black and Hot-Dipped, Zinc-Coated, Welded and Seamless](#)

[A106/A106M Specification for Seamless Carbon Steel Pipe for High-Temperature Service](#)

[A333/A333M Specification for Seamless and Welded Steel Pipe for Low-Temperature Service and Other Applications with Required Notch Toughness](#)

[D3282 Practice for Classification of Soils and Soil-Aggregate Mixtures for Highway Construction Purposes](#)

¹ This guide is under the jurisdiction of ASTM Committee E50 on Environmental Assessment, Risk Management and Corrective Action and is the direct responsibility of Subcommittee E50.01 on Storage Tanks.

Current edition approved May 1, 2008; Oct. 1, 2013. Published June 2008; January 2014. Originally approved in 2003. Last previous edition approved in 2003 as E2256 – 03; E2256 – 03(2008). DOI: 10.1520/E2256-03R08; 10.1520/E2256-13.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

- E165 Practice for Liquid Penetrant Examination for General Industry
- E621 Practice for Use of Metric (SI) Units in Building Design and Construction(Committee E06 Supplement to E380) (Withdrawn 2008)³
- E709 Guide for Magnetic Particle Testing
- E1209 Practice for Fluorescent Liquid Penetrant Testing Using the Water-Washable Process
- E1219 Practice for Fluorescent Liquid Penetrant Testing Using the Solvent-Removable Process
- E1220 Practice for Visible Penetrant Testing Using Solvent-Removable Process

2.2 Other Documents:

- ASME Section V and IX Boiler and Pressure Vessel Code⁴
- SNT TC-1A Society for Nondestructive Testing Recommended Practice⁵
- AWS B1.10 Guide for the Nondestructive Inspection of Welds⁶
- AWS QC1-96 Standard for AWS Certification of Welding Inspectors⁶
- API Publication 322 An Engineering Evaluation of Acoustic Methods of Leak Detection in Aboveground Storage Tanks, Jan. 1994⁷
- API PBPublication 334 A Guide to Leak Detection for Aboveground Storage Tanks, Mar. 1996⁷
- API 571 Damage Mechanisms⁷
- API 575 Inspection of Atmospheric and Low-Pressure Storage Tanks⁷
- API 577 Welding, Inspection and Metallurgy⁷
- API RP 479 Fitness for Service⁷
- API RP 580 Risk Based Inspection⁷
- API 581 Base Resource Document-Risk-Based Inspection⁷
- API 650 Welded Steel Tanks for Oil Storage⁷
- API 653 Tank Inspection, Alteration, and Reconstruction⁷
- STI 1-SP001 Steel Tank Institute Standard⁸

3. Terminology

3.1 The following terms as used in this guide may differ from the more commonly accepted definitions elsewhere.

3.1.1 *aboveground storage tank (AST), n*— a vertically oriented tank (normally cylindrical), whose bottom is in contact with the soil or other solid material and whose shell to bottom joint is designed to be at the plane of grade. See Fig. 1. Many tanks are

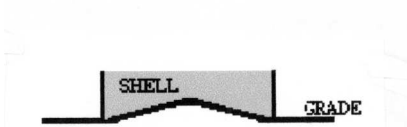


FIG. 1 Examples of ASTs per this Guide

supported on a gravel or concrete ring. Some tanks have a full concrete pad foundation.

3.1.2 *conditions and limitations, n*—the environmental and physical effects that restrict the collection of data.

3.1.3 *cut and cover or bunkered tank, n*— a field-constructed aboveground storage tank that has been cut into the soil and covered to protect it from damage either by accident or hostile intent of war.

3.1.4 *developing technology, n*—a procedure or testing method that may be used to provide additional information on a potential leak path.

3.1.5 *for petroleum service, n*—an AST that is designated for or expected to be used for petroleum product storage to include crude oil, residual, and refined petroleum products.

³ The last approved version of this historical standard is referenced on www.astm.org.

⁴ Available from American Society of Mechanical Engineers (ASME), ASME International Headquarters, Three Park Ave., New York, NY 10016-5990, <http://www.asme.org>.

⁵ Available from American Society for Nondestructive Testing (ASNT), P.O. Box 28518, 1711 Arlingate Ln., Columbus, OH 43228-0518, <http://www.asnt.org>.

⁶ Available from American Welding Society (AWS), 550 NW LeJeune Rd., Miami, FL 33126, <http://www.aws.org>.

⁷ Available from American Petroleum Institute (API), 1220 L. St., NW, Washington, DC 20005-4070, <http://www.api.org>.

⁸ Available from Steel Tank Institute / Steel Plate Fabricators Association 944 Donata Ct. Lake Zurich, IL 60047, <http://www.steel-tank.com>

3.1.6 *hydraulic integrity, n*—the actual ability of a tank bottom to prevent passage of a stored product to the external environment.

3.1.7 *leak path, n*—the route or opening through which the tank contents are released through to the exterior environment.

3.1.8 *tank, n*—a field-erected steel structure constructed of welded or riveted steel and designed for petroleum service.

3.1.9 *tank bottom, n*—the floor of a vertically oriented tank, including the shell to bottom weld, connected piping supports, column base plates, sumps, floor plates, and floor welds, but not interior or exterior coatings or cathodic protection.

3.1.10 *tank owner or operator, n*—an individual or entity that owns or operates an aboveground storage tank in accordance with and definitions of The U.S. Environmental Protection Agency Regulation 40 CFR 112.

3.1.11 *technologies, n*—systems or services that provide information that can be used to evaluate the hydraulic integrity of a tank bottom.

3.2 Abbreviations:

3.2.1 *cm*—centimetre

3.2.2 *mm*—millimetre

3.3 Acronyms:

3.3.1 *ANSI*—American National Standards Institute

3.3.2 *API*—American Petroleum Institute

3.3.3 *ASM*—American Society for Metals

3.3.4 *ASME*—American Society of Mechanical Engineers

3.3.5 *ASNT*—Society for Nondestructive Testing

3.3.6 *AST*—aboveground storage tank

3.3.7 *AWS*—American Welding Society

3.3.8 *ERW*—electric resistance weld

3.3.9 *NDE*—non-destructive evaluation

3.3.10 *OSHA*—United States Occupational, Safety and Health Administration

3.3.11 *UL*—Underwriters Laboratory

3.3.12 *UST*—underground storage tank

3.4 *Measurement Units*—This guide is written in metric measure units (SI Units) in accordance with requirements of Practice E621. English measure equivalents are in parentheses.

4. Summary of Guide <http://standards.iteh.ai/catalog/standards/sist/b5f07fe6-6ab2-4e55-b63f-c3fd62dab952/astm-e2256-13>

4.1 This guide establishes a process and provides guidance about practices and procedures that are called for in API 650 and API 653, or available as optional selections and which will lead to a better understanding about the hydraulic integrity of an AST's bottom. The information contained in the guide is set out in three formats: a flowchart of the procedures and the appropriate point for employment in order to gather the most useful information; a table of the procedures briefly describing what and how they should be used in order to gather the most useful information; and an expanded listing of the procedures to provide the guide user with procedure background and expected results in order to determine the type and validity of the information gathered.

5. Significance and Use

5.1 Inspection, repair, and construction of ASTs in petroleum service should follow at a minimum the requirements of API 650 and API 653. These standards describe methods for testing the weld quality and structural and hydraulic integrity of new or repaired ASTs. With increasing emphasis on protecting the environment and with environmental issues related to the storing of petroleum materials in ASTs, owners and operators of such tanks may want or need a guide devoted to existing and enhanced methods for evaluating the hydraulic integrity of new or repaired tank bottoms.

5.2 The consequences of a tank bottom failure include the economic loss of product, cost of repair or replacing the tank bottom, and exposure to the cost of environmental remediation and potential damage or harm to adjacent lands that may give rise to adverse public relations or regulatory action. In addition, releases of petroleum products introduce potential fire or explosive conditions.

5.3 Owners and operators of ASTs or their agents can use this guide to help choose methods of evaluating the hydraulic integrity of their repaired or new tank bottoms. Selection of the methods should be based on regulatory and economic criteria that include operational and cost/benefit considerations.

5.4 This guide is intended for use by an individual experienced in repair and construction of ASTs in petroleum service.

5.5 This guide is intended for use when repairing or building ASTs and not intended for use beyond the construction process. ASTs. This guide does not address suitability for use or imply useful life of an AST bottom.

5.6 This guide is intended to be used in conjunction with and as a supplement to standards provided for hydraulic integrity in API 650 and API 653.

5.7 Procedures or methods included here may be supported by a previously completed and documented performance evaluation(s) that may lend itself as valuable results validation.

6. Procedures

6.1 This section provides information on established practices described in API 650 and API 653. This section provides information on other practices listed in this guide as optional during a hydrostatic test, and which may be used to assess the hydraulic integrity of the tank bottom. Also identified in this section are developing technologies that may be used in conjunction with a hydro-test, and may produce supplemental information about the hydraulic integrity of the completed tank bottom construction. Some of the procedures identified here are recognized to be voluntary when used for attaining an enhanced confidence in the hydraulic integrity for a repaired or newly constructed tank bottom. For those owners and operators that already have procedures for determining the suitability of the tank bottom, this guide may serve as a reference when policy warrants a change in their methods.

6.2 **Table 1** identifies tests and procedures, and notes when application of those tests or procedures will provide the most useful information for assessing the hydraulic integrity of tank bottom.

6.3 **Table 1** supplements the flow chart by listing the accepted tests and procedures from API 650 and API 653, as a readily available reference, and also the developing technologies. These API procedures, although established chiefly to assess tank structural soundness, are also useful for determining the hydraulic soundness of tank bottom construction when it has been repaired or newly constructed. Information relating to the developing technologies may be employed by an owner and operator in order to obtain hydraulic integrity and other supplementary information during a hydrostatic test.

6.4 When using information provided in this section, considerations for schedule, operational, economic, and environmental characterizations should be reviewed. An owner and operator or the owners' and operators' representative should be familiar with conditions under which the tests and procedures can be used and in the case of the developing technologies, API 334 should be consulted.

7. Evaluation Methods

7.1 *Procedures Prior to Filling and After Filling the Tank:*

7.1.1 The owner and operator of a tank, included by definition in this guide, will find that there are numerous procedures associated with the determination of the hydraulic integrity of a tank bottom. Of this total number of procedures there can be at least nine that are conducted prior to filling the tank and can be at least another four procedures that are applied with the tank either partially or completely filled to its safe fill height.

7.2 *Evaluation of Floor Plate, Weld Construction Practices:*

7.2.1 Factors or conditions that contribute to tank bottom failure are:

7.2.1.1 Imperfections that may be included in steel plate during manufacture.

7.2.1.2 Gouging and tearing in steel plate can occur during shipment and storage, and in moving the plates into final position for welding. Such damage can be the result of improper use of equipment for moving the plate or the dragging of the plates across one another or other construction materials and rocks. The gouges and tears can compromise the structural integrity and intended service life of the tank.

7.2.1.3 Irregular surface continuities or voids in the structural fill or concrete foundation can be a significant condition causing a bottom to fail and leak. The voids and projections created by the sub-floor structural system irregularities will cause uneven stressing of the floor plates, seam welds, floor to shell weld, and sumps located in the bottom. The stress can lead to early failure of the bottom when the tank is placed back in service and under load from the stored product or the columns and legs of floating pans or roofs.

7.2.1.4 The use of incorrect welding procedures or unqualified welders can result in sub-standard welds that are more likely to fail.

TABLE 1 Tests and Procedures

Procedure	General Description of Procedure	General Application	Thresholds, Results, and Limitations
<u>7.2 Evaluation of Floor Plate, Weld Construction</u>	Good practices, procedures, record keeping, and oversight of plate manufacturing process, shipment, and storage at site. Compliance with design requirements, welding procedures, certifications and plate preparation prior to completing welds. Experience requirements for construction personnel and inspectors. Performance of work in proposed hydrogen sulfide uses or other environments that may cause cracking. Review structural fill and concrete sub-floors for compliance with specification.	This procedure is performed on the steel floor plate, floor plate welds, floor plate to shell welds, internal piping supports connected to the floor plates, tank sumps, and gauging well wear plate. In addition, this procedure recognizes that improper preparation of the tank bottom substrate, by permitting hills and voids, contributes significantly to the potential for early tank bottom hydraulic integrity failure.	Impacts to tank bottom hydraulic integrity include: completion schedule, individual integrity, skill and experience in the plate manufacturing process, those individuals directing, performing, inspecting, and reviewing records. Reliance on subjective opinion. Plate Manufacture complies with Specification <u>A6/A6M</u> or Specification <u>A20/A20M</u> . Welding Complies with API 650, Section 5.2 and API 653, Section 9, ASME and AWS standards as applicable. Certification of Weld Inspectors complies with AWS QC1-96.
<u>7.2 Evaluation of Floor Plate, Weld Construction</u>	<u>Good practices, procedures, record keeping, and oversight of plate manufacturing process, shipment, and storage at site. Compliance with design requirements, welding procedures, certifications and plate preparation prior to completing welds. Experience requirements for construction personnel and inspectors. Performance of work in proposed hydrogen sulfide uses or other environments that may cause cracking. Review structural fill and concrete sub-floors for compliance with specification.</u>	<u>This procedure is performed on the steel floor plate, floor plate welds, floor plate to shell welds, internal piping supports connected to the floor plates, tank sumps, and gauging well wear plate. In addition, this procedure recognizes that improper preparation of the tank bottom substrate, by permitting hills and voids, contributes significantly to the potential for early tank bottom hydraulic integrity failure.</u>	<u>Impacts to tank bottom hydraulic integrity include: completion schedule, individual integrity, skill and experience in the plate manufacturing process, those individuals directing, performing, inspecting, and reviewing records. Reliance on subjective opinion. Plate Manufacture complies with Specification <u>A6/A6M</u> or Specification <u>A20/A20M</u>. Welding Complies with API 650, Section 7.2 and API 653, Section 11, ASME and AWS standards as applicable. Certification of Weld Inspectors complies with AWS QC1-96.</u>
<u>7.3 Evaluation of Connected Under-floor Piping</u>	Accepted practice, procedures, and inspection of completed water draw offs, drain dry piping, and sump systems including the bedding.	This procedure is performed on the tank piping that passes beneath the sub-floor and floor plates of a tank bottom including the welds.	Impacts to piping installation include: completion schedule, individual integrity, skill and experience in the pipe manufacturing process, those individuals directing, performing, inspecting, and reviewing records. Reliance on subjective opinion. Prior to back filling these systems inspect completely.
<u>7.4 Evaluation by Visual Examination of the Tank Floor</u>	Visual inspection of the tank floor, including the plates, welds, shell to floor plate welds, and piping, sumps, and wastewater drains. The inspection may be performed using direct eye, mirrors, cameras, and other suitable instruments. The eye should be placed no more than 60.9 cm (24 in.) from the surface and at an angle of not less than 30°.	Plates, welds, shell to floor plate welds, and piping, sumps and wastewater drains.	Accessibility to visual inspection, cleanliness of area to be inspected, applies to surface defects only, lighting levels, visual acuity of individual performing inspection. Minimum illumination is 15 footcandles for general viewing and 50 footcandles for viewing small anomalies. Individual performing the test should have a visual acuity natural or corrected as measured by reading standard J-2 letters of the Jaeger Chart. Identify cracks, undercut, mechanical defects, gouges, arc strikes, temporary attachment removal area, and incomplete welds.

7.2.1.5 Service conditions that might include the presence of hydrogen sulfide or conditions that may cause weld or plate cracking require the appropriate selection of materials, and quality control for manufacture and fabrication.

7.2.2 Summary of Test Parameters:

7.2.2.1 The user will need to ensure good practices, procedures and record keeping, are used throughout the process to avoid or intercept the foregoing conditions or factors that contribute to tank bottom failure. Specification A36/A36M or other steels for

TABLE 1 Continued

Procedure	General Description of Procedure	General Application	Thresholds, Results, and Limitations
7.5 Evaluation by Radiography Examination	A non-destructive method for inspection of welds that provides information about the internal condition using radiation. The radiation is directed at the weld and either penetrates, is absorbed, or scatters and is then recorded on film or by a device. There are two recognized methods of conducting radiography: Film/Paper Radiography, and Radioscopy.	Accessible floor welds or at the owner's discretion.	The surface to be examined needs to be accessible from both sides. Discrepancies must be suitably aligned with the radiation beam in order to be reliably detected. Creating the image and the interpretation needs to be accomplished by experienced individuals. Radiation exposure to individuals is a hazard and they must be included in a monitoring program. It is a relatively expensive testing method. Perform prior to erecting shell. SNT-TC-1A Level II NDE personnel are required.
7.5 Evaluation by Radiography Examination	A non-destructive method for inspection of welds that provides information about the internal condition using radiation. The radiation is directed at the weld and either penetrates, is absorbed, or scatters and is then recorded on film or by a device. There are two recognized methods of conducting radiography: Film/Paper Radiography, and Radioscopy.	Accessible annular plate welds and shell butt welds or at the owner's discretion.	The surface to be examined needs to be accessible from both sides. Discrepancies must be suitably aligned with the radiation beam in order to be reliably detected. Creating the image and the interpretation needs to be accomplished by experienced individuals. Radiation exposure to individuals is a hazard and they must be included in a monitoring program. It is a relatively expensive testing method. Perform prior to erecting shell. SNT-TC-1A Level II NDE personnel are required.
7.6 Evaluation by Wicking Examination of Corner Weld	Apply highly penetrating oil or dye penetrant to opposite side of first weld pass, and let stand for a period of time. Observe the welded side of the joint.	Shell to bottom plate weld.	Accessibility to viewing, cleanliness of weld area, and visual acuity of individual performing the test. Perform in dry conditions. Test must be performed when ambient temperature is high enough to allow the oil or dye penetrant to flow. Apply dye penetrant or highly penetrating oil to opposite side of first weld pass. Let sit for a minimum of 4 h (12 h is the preferred length of time). Observe the weld side of the joint. Identifies through weld pinholes, porosity, and cracks not visible to the eye. Identifies a leak that passes oil instead of air.
7.7 Evaluation by Bubble Test Examination (Pressure)	Pressure method locates leaks in a pressurized component by the application of a solution or immersion in liquid that will form bubbles as leakage gas passes through it.	Tank floor fillet welded lapped seams, butt welded seams, and shell to bottom weld.	Limited to small tanks or parts of tanks. For visual plus training on the specific procedure used by the manufacturer or fabricator. Training to meet the requirements of SNT-TC-1A.
7.8 Evaluation by Bubble Test Examination (Vacuum)	Apply solution and a vacuum to a localized area.	Tank floor fillet welded lapped seams, butt welded seams, and shell to bottom weld.	Accessibility requires minimum clearance of 15.3 cm (6 in.) between bottom plate and obstruction above test area for placement of device and viewing. Perform test in accordance with a written procedure and ASME BPVC, Section V, Art. 10 App II. Individuals performing the test require visual acuity and training to meet requirements of SNT-TC-1A.