



# FINAL DRAFT

## International Standard

### ISO/FDIS 501

## Hard coal — Determination of the crucible swelling number

*Houille — Détermination de l'indice de gonflement au creuset*

ISO/TC 27/SC 5

Secretariat: **SA**

Voting begins on:  
**2025-02-04**

Voting terminates on:  
**2025-04-01**

iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

ISO/FDIS 501

<https://standards.iteh.ai/catalog/standards/iso/c919ab05-3054-4985-867a-d7186da2ff28/iso-fdis-501>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

ISO/FDIS 501

<https://standards.iteh.ai/catalog/standards/iso/c919ab05-3054-4985-867a-d7186da2ff28/iso-fdis-501>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2025

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>1</b>
<b>5 Preparation of the test sample</b> .....	<b>1</b>
<b>6 Apparatus</b> .....	<b>2</b>
<b>7 Preparation of apparatus</b> .....	<b>4</b>
<b>8 Procedure</b> .....	<b>5</b>
<b>9 Expression of results</b> .....	<b>6</b>
<b>10 Precision of the method</b> .....	<b>7</b>
10.1 Repeatability.....	7
10.2 Reproducibility.....	7
<b>11 Test report</b> .....	<b>7</b>

iTeh Standards  
(<https://standards.itih.ai>)  
Document Preview

[ISO/FDIS 501](https://standards.itih.ai/catalog/standards/iso/c919ab05-3054-4985-867a-d7186da2ff28/iso-fdis-501)

<https://standards.itih.ai/catalog/standards/iso/c919ab05-3054-4985-867a-d7186da2ff28/iso-fdis-501>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 27, *Coal and coke*, Subcommittee SC 5, *Methods of analysis*.

This fifth edition cancels and replaces the fourth edition (ISO 501:2012), which has been technically revised.

The main changes are as follows:

- replaced the word "should" with "shall" throughout the document;
- corrected dimension expressions e.g.  $26 \pm 1,0$  mm to  $26 \text{ mm} \pm 1 \text{ mm}$ ;
- standardised the reporting of  $\frac{1}{2}$  as 0,5

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

# Hard coal — Determination of the crucible swelling number

**WARNING** — Use of this document can involve hazardous materials, operations and equipment. This document does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this document to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

## 1 Scope

This document specifies a method for determining the swelling properties of hard coal when heated in a covered crucible.

NOTE The "crucible swelling number" (CSN) is also known as the "free swelling index" (FSI).

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 13909-4, *Coal and coke — Mechanical sampling — Part 4: Coal — Preparation of test samples*

ISO 18283, *Coal and coke — Manual sampling*

## 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

## 4 Principle

A sample of coal is heated in a covered crucible under standard conditions of time and temperature. The shape of the coke button obtained is classified by comparison with the outlines of a set of standard profiles.

## 5 Preparation of the test sample

The test sample shall be the general analysis test sample prepared in accordance with ISO 13909-4 and ISO 18283. Ensure that the moisture in the sample is in equilibrium with the laboratory atmosphere, exposing it, if necessary, in a thin layer for the minimum time required to achieve equilibrium.

The sample used for the crucible swelling number (CSN) test shall be ground to pass a 212 µm sieve. A small swing hammer crusher with rotary hammers is suitable for grinding samples, a mortar and pestle can be used to grind samples of low mass, e.g. less than 60 g. Avoid very fine grinding, as CSN can be adversely affected with pulverization level. Avoid the use of ring mills as the heat generated during very fine grinding can potentially oxidise the sample and adversely affect the CSN result. Once the sample is prepared to this size specification, the test shall be performed within 24 h in order to avoid oxidation and a potentially misleading CSN result.


## 6 Apparatus

### 6.1 Crucible and lid (see Figure 1): silica crucible, squat form, and silica lid with ring handle.

The crucible shall conform to the following specifications:

External height:	26 mm $\pm$ 1 mm
External diameter at top:	41 mm $\pm$ 1 mm
Internal diameter at base:	14 mm $\pm$ 3 mm
Mass:	12 g $\pm$ 1 g
Capacity:	16 ml to 17,5 ml

Dimensions in millimetres

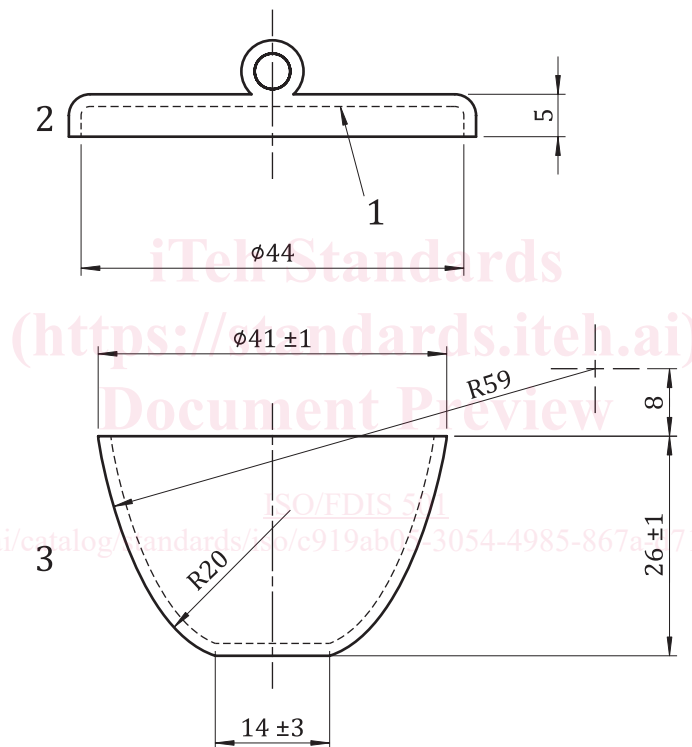

#### Key

- 1 flat surface required
- 2 lid
- 3 crucible

**Figure 1 — Crucible with lid for swelling test**

### 6.2 Pierced silica lid (see Figure 2), similar to that described in 6.1 but with a 6 mm hole through which the thermocouple (6.7) can pass.