

FINAL  
DRAFT

INTERNATIONAL  
STANDARD

ISO/FDIS  
26910-1

ISO/TC 227

Secretariat: JISC

Voting begins on:  
2023-07-19

Voting terminates on:  
2023-09-13

---

---

## Springs — Shot peening —

### Part 1: General procedures

*Ressorts — Grenailage de précontrainte —*

*Partie 1: Modes opératoires généraux*

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/FDIS 26910-1](https://standards.iteh.ai/catalog/standards/sist/1cad9050-46b7-4084-9345-c4b268b6250f/iso-fdis-26910-1)

<https://standards.iteh.ai/catalog/standards/sist/1cad9050-46b7-4084-9345-c4b268b6250f/iso-fdis-26910-1>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number  
ISO/FDIS 26910-1:2023(E)

© ISO 2023

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

ISO/FDIS 26910-1

<https://standards.iteh.ai/catalog/standards/sist/1cad9050-46b7-4084-9345-c4b268b6250f/iso-fdis-26910-1>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2023

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Strategies for conducting shot peening</b> .....	<b>3</b>
4.1 General.....	3
4.2 Mode of shot peening.....	3
4.3 Conditions of shot peening.....	3
4.4 Category of shot peening machine.....	4
4.5 Protection of non-peening surface.....	4
4.6 Pre- and post-peening treatments.....	4
<b>5 Peening media</b> .....	<b>4</b>
<b>6 Almen strip</b> .....	<b>4</b>
6.1 Class of Almen strip.....	4
6.2 Selection of the class of Almen strip.....	5
6.3 Almen strip holder.....	5
<b>7 Method of measurement</b> .....	<b>6</b>
7.1 Measurement of Almen arc height.....	6
7.2 Evaluation of coverage.....	7
7.3 Determination of saturation time.....	8
<b>8 Shot peening machine</b> .....	<b>8</b>
<b>9 Control of shot peening</b> .....	<b>8</b>
9.1 Almen arc height.....	8
9.2 Coverage.....	8
<b>10 Measurement of residual stress</b> .....	<b>8</b>
<b>11 Report</b> .....	<b>8</b>
<b>Annex A (informative) Standard photographs of coverage</b> .....	<b>9</b>
<b>Annex B (informative) Saturation time</b> .....	<b>10</b>
<b>Annex C (informative) Almen gauge</b> .....	<b>12</b>
<b>Bibliography</b> .....	<b>14</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at [www.iso.org/patents](http://www.iso.org/patents). ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 227, *Springs*.

This second edition cancels and replaces the first edition (ISO 26910-1:2009), of which it constitutes a minor revision. It also incorporates the Amendment ISO 26910-1:2009/Amd. 1:2017.

The changes compared to the previous edition are as follows:

- the Normative reference has been updated to ISO 80000-1;
- "or less" has been deleted from the sentence of [3.5](#) saturation time;
- "and size" has been added to the sentence of a) of [4.3](#) Conditions of shot peening;
- "Type A" has been added to the last sentence of [6.2](#) Selection of the class of Almen strip;
- the statuses of [Annexes A](#) and [B](#) have been changed to informative.

A list of all parts in the ISO 26910 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

Shot peening is widely applied to various mechanical and structural elements in a wide range of industrial fields, because of its effective improvement in the strength and life properties at moderate costs. It is also used in some cases for other purposes such as to form thin sheet products, to increase wear resistance, or to assist lubrication effect, deburring and so on. It is, however, especially important for spring industries, as it is indispensable for the achievement of the required fatigue strength and to decrease stress corrosion cracking.

The important effects of shot peening are known to be due mainly to the compressive residual stresses introduced near the shot peened surface, and helped sometimes by the work hardening of the surface layers. Various processing methods have been developed and practised together with diverse materials for shot peening.

This document serves to establish smooth technical communication between the spring manufacturers and industry related to shot peening, including peening machine manufacturers, peening media suppliers and shot peening processors, as well as users of those springs in various industrial sectors.

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

[ISO/FDIS 26910-1](https://standards.iteh.ai/catalog/standards/sist/1cad9050-46b7-4084-9345-c4b268b6250f/iso-fdis-26910-1)

<https://standards.iteh.ai/catalog/standards/sist/1cad9050-46b7-4084-9345-c4b268b6250f/iso-fdis-26910-1>



# Springs — Shot peening —

## Part 1: General procedures

### 1 Scope

This document specifies general requirements for the shot peening process applied to springs in order to improve their resistance to fatigue and stress corrosion cracking, mainly by introducing compressive residual stresses into their surface layers.

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 80000-1, *Quantities and units — Part 1: General*

### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

#### 3.1

##### **shot peening**

cold work applied to the surface of a material or a mechanical element, to improve its fatigue strength and stress corrosion cracking resistance, by a stream of near spherical hard particles at a high velocity that generates compressive residual stresses and work hardening in the surface layer

#### 3.2

##### **peening media**

generally spherical or near-spherical hard particles, made of metals, glasses or ceramics, used for shot peening

Note 1 to entry: Individual particles can be called shots.

#### 3.3

##### **Almen strip**

rectangular metal strip used for evaluating the peening intensity by the magnitude of its bending deformation after shot peening on one surface

#### 3.4

##### **Almen arc height**

*h*

height of the arched deformation of an Almen strip measured on the basis of a fixed span

Note 1 to entry: It is expressed in millimetres.

**3.5**  
**saturation time**

$t$

minimum time for which the successive increase of Almen arc height is 10 % for an additional exposure equal to time  $t$ , i.e. a total time of  $2 t$

**3.6**  
**peening intensity**

intensity of shot peening, dependent on the kinetic energy of shots acting on the unit surface area of the workpiece per unit time, and is usually evaluated by the Almen arc height for the saturation time

**3.7**  
**saturation curve**

trend curve representing the change of Almen arc height with time of shot peening, until the Almen arc height saturates

**3.8**  
**coverage**

area ratio of the dents formed by shot impacts to the total area of the measuring surface

**3.9**  
**residual stress**

internal stress of a material remaining after the removal of external forces and heat applied on it

**3.10**  
**particle size distribution**

size distribution of shots

**3.11**  
**ordinary peening**

mode of shot peening using one type of peening media nominally larger than 0,2 mm and resulting in an Almen arc height of between 0,15 mm and 0,6 mm (A)

**3.12**  
**multi-stage peening**

mode of shot peening consisting of a series of peening at different conditions

Note 1 to entry: The name indicates the number of peening conditions combined, for example, "two-stage peening".

Note 2 to entry: Two-stage peening is the one most practised. It usually consists of a first stage at an intensive peening condition with larger shots at higher speeds, and a second stage at moderate or weak peening condition. The first peening stage generates higher compressive residual stresses deep under the surface of a spring, while the compression is poor near the surface. The second peening generates shallower residual compressive stresses. The sum of the two compressive stresses would give a good distribution pattern of compressive stresses from the surface to the required depth.

**3.13**  
**stress peening**

mode of shot peening applied under a static force corresponding to the working force of the spring during use

Note 1 to entry: Stress peening ensures that a spring will keep its intended compressive residual stresses under the applied tensile stresses at its working state. This is one of the frequently used techniques for laminated leaf springs, for example.

**3.14**  
**hot peening**

mode of shot peening applied at elevated temperatures ranging from 150 °C to 350 °C for steel springs

Note 1 to entry: Hot peening is based on the ageing effect of steels. It is generally advantageous for achieving enhanced compressive residual stresses especially in hard steel springs.



**3.15****heavy peening**

mode of shot peening resulting in an Almen arc height larger than 0,6 mm (A) using a peening media larger than 0,2 mm

**3.16****fine peening**

mode of shot peening resulting in an Almen arc height smaller than 0,15 mm (A) using a peening media not exceeding 0,2 mm

**3.17****X-ray stress measurement**

method for measuring internal stresses near the surface of polycrystalline materials based on X-ray diffraction techniques

**4 Strategies for conducting shot peening****4.1 General**

The mode, condition, category of peening machine, protection of non-peening surface and pre- and post-peening treatment should be determined based upon past experience and anticipated results prior to carrying out the process.

**4.2 Mode of shot peening**

The mode of shot peening shall be one of the following:

- a) ordinary peening;
- b) multi-stage peening;
- c) stress peening;
- d) hot peening;
- e) heavy peening;
- f) fine peening.

**4.3 Conditions of shot peening**

The conditions of shot peening shall be defined for the following items:

- a) type of peening media and size;
- b) desired Almen arc height,  $h$ , in combination with the class of Almen strip;
- c) coverage, indicating the location and area of measurement;
- d) processing time of shot peening, when this applies. A multiplication factor to the saturation time,  $t$ , could be indicated, instead of the Almen arc height,  $h$ , if this is agreed upon by the purchaser and supplier.

For multi-stage peening, the conditions of shot peening shall be indicated for individual stages.

NOTE Mechanical properties of peened material do not always directly correspond to the Almen arc height, since the effect varies depending on the size and shape of shots and the hardness of the material treated.

#### 4.4 Category of shot peening machine

There are two main categories of machines for springs, centrifugal and air-blasting, according to the projection method of shots. The former is suitable for projecting larger amounts of shots on wider areas treating several springs together, and the latter for smaller amounts, but at higher intensities on more focused areas.

The machine category shall be selected considering the design concepts of springs. Other specific details of the machine should be clarified, with its identification code, if necessary.

#### 4.5 Protection of non-peening surface

Areas that do not require shot peening shall be clearly defined. Selected areas where the peening must not affect the springs surface shall be protected as required by appropriate means, such as shields, masks or adhesive tapes.

#### 4.6 Pre- and post-peening treatments

Requirements shall be indicated for:

- a) pre-peening treatment (e.g. cleaning and degreasing);
- b) post-peening treatment (e.g. rust protection, coating and wrapping).

Care should be taken to prevent rusting, as it is generally easy for shot peened materials to start rusting, especially in moist air.

### 5 Peening media

The type of media used shall be as given in [Table 1](#).

**Table 1 — Types of peening media**

Type Name	Code	Material	Apparent density 10 <sup>3</sup> kg/m <sup>3</sup>	Shape	Nominal diameter mm	Hardness HV
Conditioned cut wire shot	CCW	Steel	7,65 to 7,95	Near spherical	0,2 to 3	350 to 850
Cast steel shot	SS	Cast steel	7,45 min.	Spherical	4 max.	200 to 850
Glass beads	GB	Glass	2,30 min.	Spherical	1 max.	450 to 550
Ceramic beads	CB	Ceramic	3,60 to 3,95	Spherical	1 max.	500 to 800

NOTE 1 Cut wire shot can be used if conditioned in-house before shot peening springs to prevent unacceptable surface damage.

NOTE 2 If cut wire shot is used, the characteristic of CCW in [Table 1](#) is applied to cut wire shot.

Any other type of spherical or near spherical media can be used upon agreement between the purchaser and supplier, if it can be demonstrated that no adverse damage is done.

### 6 Almen strip

#### 6.1 Class of Almen strip

Almen strips shall be one of the three classes defined in [Table 2](#), all having the same shape and size as shown in [Figure 1](#).

Table 2 — Classes of Almen strip

Class	Thickness, $\delta$ mm		Hardness <sup>a</sup>	Flatness tolerance <sup>b</sup> mm	Material
	Nominal	Tolerance			
N	0,8	+0,01 -0,04	72,5 – 76 HRA	0,025	Carbon steel, with 0,60 % to 0,80 % of carbon
A	1,3	+0,02 -0,03	44 – 50 HRC	0,025	
C	2,4	+0,01 -0,04	44 – 50 HRC	0,038	

<sup>a</sup> ISO 6508-1.  
<sup>b</sup> ISO 1101.

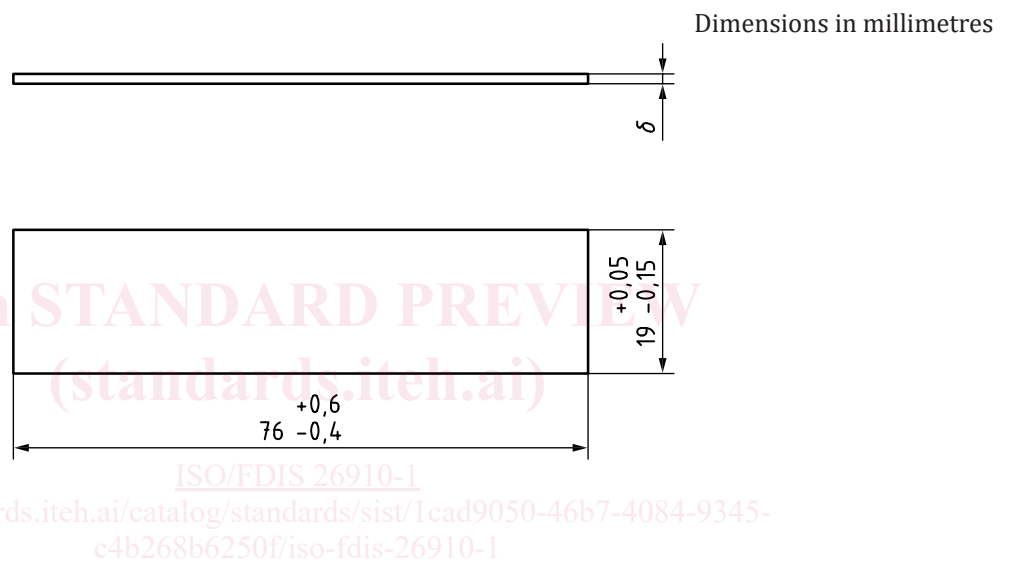


Figure 1 — Shape and size of test strip

## 6.2 Selection of the class of Almen strip

An appropriate class of Almen strip shall be selected, taking into consideration the intensity of shot peening. Various classes of Almen strips give generally different Almen arc heights,  $h$ , according to their thickness,  $\delta$ , even under the same peening condition.

Strip A is for general use in the middle range of peening intensities, and strips N and C are for lower and higher ranges, respectively. Type A Almen strips shall be used for Almen arc heights not greater than 0,6 mm.

## 6.3 Almen strip holder

An Almen strip shall be fixed on a thick steel holder as defined in [Figure 2](#). The holder shall have a flat mounting surface with fastening screws that keep the Almen strip flat in contact with the surface during peening. Care is required so that the screw heads do not affect Almen arc height. The hardness of the holder should be at least 57 HRC to avoid early wear.