



Designation: A476/A476M – 00 (Reapproved 2014)

Standard Specification for Ductile Iron Castings for Paper Mill Dryer Rolls^{1,2}

This standard is issued under the fixed designation A476/A476M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This specification covers ductile iron castings for use in pressure containing paper mill dryer rolls at temperatures up to 450°F [230°C].

1.2 No precise quantitative relationship can be stated between the properties of the iron in various locations of the same casting or between the properties of a casting and those of a test specimen cast from the same iron (see [Appendix X1](#)).

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.3.1 *Exception*—Within the text, the SI units are shown in brackets.

2. Referenced Documents

2.1 *ASTM Standards*:³

[A644 Terminology Relating to Iron Castings](#)

[E8 Test Methods for Tension Testing of Metallic Materials](#)

[E10 Test Method for Brinell Hardness of Metallic Materials](#)

[E94 Guide for Radiographic Examination](#)

[E446 Reference Radiographs for Steel Castings Up to 2 in. \(50.8 mm\) in Thickness](#)

3. Terminology

3.1 Definitions for many terms common to iron castings are found in Terminology [A644](#).

4. Ordering Information

4.1 Orders for material purchased to the requirements of this specification should include the following information:

¹ This specification is under the jurisdiction of ASTM Committee [A04](#) on Iron Castings and is the direct responsibility of Subcommittee [A04.02](#) on Malleable and Ductile Iron Castings.

Current edition approved April 1, 2014. Published April 2014. Originally approved in 1962. Last previous edition approved in 2009 as A476/A476M - 00 (2009). DOI: 10.1520/A0476_A0476M-00R14.

² For ASME Boiler and Pressure Vessel Code Applications see related Specifications SA-467 in Section II of that Code.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

- 4.1.1 Quantity,
- 4.1.2 Specification number and date of issue,
- 4.1.3 Description of casting by pattern number or drawing,
- 4.1.4 Heat treatment, if required (see [5.1](#)),
- 4.1.5 Type of test coupon (see [9.2](#)),
- 4.1.6 Certification, if required (see [13.1](#)),
- 4.1.7 Marking location (see [14.1](#)), and
- 4.1.8 Additional requirements.

5. Heat Treatment

5.1 The castings may be stress relieved at a temperature not to exceed 1200°F [650°C].

6. Chemical Requirements

6.1 The castings shall conform to the following chemical requirements:

Total carbon, min, %	3.0
Silicon, max, %	3.0
Phosphorus, max, %	0.08
Sulfur, max, %	0.05

6.2 The castings shall have a carbon equivalent of 3.8 to 4.5 inclusive.

NOTE 1—The carbon content equivalent is calculated as follows:
Total carbon + 0.3 (silicon + phosphorus)

6.3 The chemical analysis for total carbon shall be made on either chilled cast pencil-type specimens or on thin wafers approximately $\frac{1}{32}$ in. [0.8 mm] thick, cut from test coupons. Drillings shall not be used due to attendant loss of graphite.

7. Mechanical Properties

7.1 The iron represented by test coupons shall conform to tensile requirements prescribed in [Table 1](#).

7.2 The yield strength prescribed in [Table 1](#) may be determined by any of the approved procedures described in 7.3 of Test Methods [E8](#).

7.3 The Brinell hardness of the material shall be a minimum of 201 HB. Hardness tests shall be conducted in accordance with Test Method [E10](#), using a 3000-kgf load. The test may be made on either the casting or on a test coupon representing the casting.

8. Workmanship, Finish, and Appearance

8.1 The castings shall conform to the dimensions on the drawings furnished by the purchaser, or if no drawing has been

TABLE 1 Tensile Requirements

Test Coupon Section Thickness	1 in. [25 mm]	3 in. [75 mm]
Tensile strength, min, ksi [MPa]	80 [555]	80 [555]
Yield strength, min, ksi [MPa]	60 [415]	60 [415]
Elongation in 2 in. [50 mm], min, %	3.0 [3.0]	1.0 [1.0]

provided, to the dimensions predicated by the pattern supplied by the purchaser. Surfaces of the castings shall be free of adhering sand. Runners, risers, fins, and other extraneous metal shall be removed.

9. Sampling


9.1 Test coupons shall be poured from the same iron as the castings represented.

9.2 Test coupons shall be cast either to the “Y” block size and shape shown in Fig. 1 or to the dimensions of the 1-in. [25-mm] keel block shown in Fig. 2. The type of test coupon and, when selected, the size of the “Y” block shall be specified by the purchaser.

9.3 The test coupons shall be cast in open molds made of suitable core sand with a minimum 1½ in. [38 mm] of sand for the 1-in. [25 mm] size and 3 in. [75 mm] of sand for the 3-in. [75-mm] size. The coupons shall be left in the mold until black.

9.4 Table 2 shows the equivalent geometrical shapes with various dimensions and the equivalent “Y” block, based on cooling rates, and may be used as a guide for selection of the proper “Y” block to be specified to represent the casting.

9.5 When the castings are heat treated, the test coupons shall be heat treated with the castings they represent.

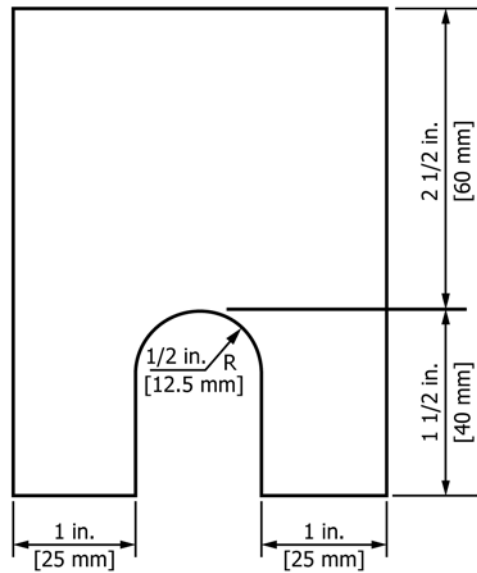

NOTE 1—The length of keel block shall be 6 in. [150 mm].

FIG. 2 Keel Block for Test Coupons

TABLE 2 Equivalent Geometric Shapes Corresponding to “Y” Blocks


“Y” Block Size, in. [mm]	Infinite Plate Thickness, in. [mm]	Round Diameter, in. [mm]	Cube Edge, in. [mm]
1 [25]	0.9 [22.5]	1.75 [44]	2.75 [44]
3 [75]	1.6 [40]	3.1 [78]	4.8 [120]

10. Tension Test

10.1 Tension test specimens shall be obtained from test coupons shown in either Fig. 1 or Fig. 2, and machined to the dimensions shown in Fig. 3. Test coupons cast as “Y” blocks (Fig. 1) shall be sectioned as shown in Fig. 4.


10.2 One tension test shall be performed for each casting.

10.3 If any specimen shows defective machining or flaws, it may be discarded and another substituted from the same casting represented.

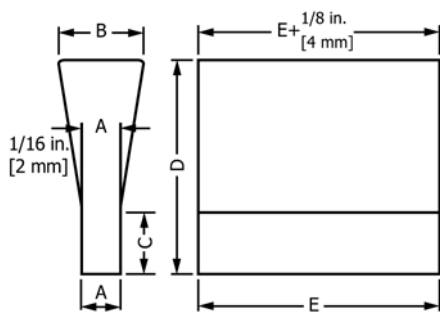

Dimensions	“Y” Block Size	
	For Castings of Thickness ½ in. to 1½ in. [12.5-40 mm]	For Castings of Thickness of 1½ in. [40 mm] and Over
	in. [mm]	in. [mm]
A	1 [25]	3 [75]
B	1½ [55]	5 [125]
C	3 [75]	4 [100]
D	6 [150]	8 [200]
E	7 [175]	7 [175]
	approx	approx

FIG. 1 “Y” Blocks for Test Coupons

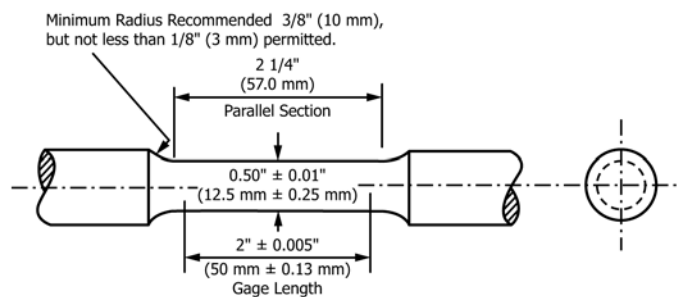

NOTE 1—The gage length and fillets shall be as shown, but the ends may be of any shape to fit the holders of the testing machine in such a way that the load shall be axial. The reduced section shall have a gradual taper from the ends toward the center, with the ends 0.003 to 0.005 in. [0.08-0.13 mm] larger in diameter than the center.

FIG. 3 Standard Round Tension Test Specimen with 2-in. [50-mm] Gage Length