

ISO/FDIS 12046

ISO/TC 41/SC 4

ISO/DIS 12046:2024(en)

2024-06-07

Secretariat: ANSI

Third edition

Date: 2024-09-30

Synchronous belt drives — Automotive belts — Determination of physical properties

Transmissions synchrones par courroies — Courroies pour la construction automobile — Détermination des caractéristiques physiques

(<https://standards.iteh.ai>)

Document Preview

ISO/FDIS 12046

<https://standards.iteh.ai/catalog/standards/iso/33753e97-28be-41a7-81d1-6476025a8a81/iso-fdis-12046>

FDIS stage

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ISO/FDIS 12046](https://standards.itih.ai/catalog/standards/iso/33753e97-28be-41a7-81d1-6476025a8a81/iso-fdis-12046)

<https://standards.itih.ai/catalog/standards/iso/33753e97-28be-41a7-81d1-6476025a8a81/iso-fdis-12046>

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: + 41 22 749 01 11
E-mail: copyright@iso.org
Website: www.iso.org

Published in Switzerland

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/FDIS 12046](#)

<https://standards.iteh.ai/catalog/standards/iso/33753e97-28be-41a7-81d1-6476025a8a81/iso-fdis-12046>

Contents

Foreword.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	1
5 Test methods.....	1
6 General conditions for testing.....	2
6.1 Standard environmental conditions.....	2
6.2 Standard conditions of test specimens.....	2
6.3 Rounding off the test results.....	2
6.4 Test report.....	2
7 Static property tests.....	3
7.1 Test for hardness of rubber core.....	3
7.2 Tensile strength test.....	3
7.3 Fabric adhesion test.....	4
7.4 Tension-cord adhesion test.....	7
7.5 Tooth-shear test.....	8
7.6 Test for resistance to high temperature.....	13
7.7 Test for resistance to low temperature.....	13
7.8 Test for resistance to oil.....	13
7.9 Test for resistance to ozone.....	13
7.10 Test for resistance to water.....	14

ISO/FDIS 12046

<https://standards.iteh.ai/catalog/standards/iso/33753e97-28bc-41a7-81d1-6476025a8a81/iso-fdis-12046>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 4, *Synchronous belt drives*.

This ~~second~~^{third} edition cancels and replaces the second edition (ISO 12046:2012), which has been technically revised.

The main changes are as follows:

- ~~Clause 2~~—~~Clause 2~~—~~Normative References was~~ has been updated;
- ~~Clause 7.9.2~~—~~Volumetric~~volumetric units ~~were~~have been clarified (7.9.2);
- ~~Bibliography was updated~~

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Synchronous belt drives — Automotive belts — Determination of physical properties

1 Scope

This document specifies test methods for determining the physical properties of synchronous belts used in driving engine parts, such as camshafts, fuel injection pumps, balancing shafts. These test methods are intended to provide a means of characterizing synchronous belt properties for belts which are evaluated and qualified by dynamic laboratory and field testing.

NOTE — The dimensional characteristics of these belts are covered in ISO 9010.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 48-2, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness — Part 2: Hardness between 10 IRHD and 100 IRHD)*

ISO 1817, *Rubber, vulcanized or thermoplastic — Determination of the effect of liquids*

3 Terms and definitions

For the purposes of this document, the following terms and definitions given in ISO 5288 apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Principle

The objective of the test methods covered in this document is the evaluation of the physical properties of automotive synchronous belts through standardized testing. These test methods are independent of tooth profiles.

5 Test methods

The tests covered in this document are listed in Table 1.

Table 1 — Tests

Test	Subclause
Hardness of rubber core	7.1
Tensile strength	7.2

Test	Subclause
Fabric adhesion	7.3
Tension-cord adhesion	7.4
Tooth shear	7.5
Resistance to high temperature	7.6
Resistance to low temperature	7.7
Resistance to oil	7.8
Resistance to ozone	7.9
Resistance to water	7.10

6 General conditions for testing

6.1 Standard environmental conditions

Standard conditions in the laboratory shall be maintained at a temperature of (25 ± 5) °C, a relative humidity of (65 ± 20) % and an atmospheric pressure of 86 kPa to 106 kPa. The test conditions should be recorded.

6.2 Standard conditions of test specimens

The test specimens shall be tested at least 16 h after vulcanization and shall be kept for at least 1 h prior to test in a room maintained under standard conditions.

6.3 Rounding off the test results

The results of each test shall be rounded off. Results shall be recorded according to the number of figures specified in [Table 2](#).

Table 2 — Rounding off of results

Test	Unit	Measured test value	Test results to be obtained
Hardness of rubber core	Shore A or IRHD	Integer	Integer
Tensile strength	N	Nearest 10	Nearest 100
Fabric adhesion	N	Integer	Integer
Tension-cord adhesion	N	Nearest 10	Nearest 10
Tooth shear	N	Nearest 10	Nearest 10
EXAMPLES	Nearest tens 3 474 → 3 470 3 475 → 3 480	Nearest hundreds 3 440 → 3 400 3 450 → 3 500	

6.4 Test report

For each test, the test report shall include the following information:

- a) ~~a)~~ number of teeth, pitch, tooth profile and width of specimen;
- b) ~~b)~~ constituent materials of specimen;
- c) ~~c)~~ production code of specimen;
- d) ~~d)~~ date of test;

- e) ~~e)~~ number of specimens;
- f) ~~f)~~ test temperature, relative humidity and atmospheric pressure;
- g) ~~g)~~ type of test apparatus;
- h) reference to this document (including its year of publication).

7 Static property tests

7.1 Test for hardness of rubber core

7.1.1 Test specimens

The test specimen shall be either an endless belt or a cut belt with a minimum length of 100 mm.

7.1.2 Procedure

Place the specimen, with teeth pointing downward, on a flat surface and measure the flat portion of the belt above a tooth, using either;

- —a Shore type A durometer as specified in ISO 48:~~2~~;
- —an IRHD tester as described in ISO 48:~~2~~;
- —an equivalent apparatus.

7.1.3 Expression of results

Record the average of five different measurements along the belt, rounded off as in the following examples.

EXAMPLE 1

$$\frac{74 + 75 + 75 + 74 + 74}{5} = 74,4 \rightarrow 74$$

EXAMPLE 2

$$\frac{75 + 75 + 75 + 74 + 74}{5} = 74,6 \rightarrow 75$$

7.2 Tensile strength test

7.2.1 Test specimens

The test specimen shall be either an endless belt or two cut belts with a minimum length of 250 mm each.

7.2.2 Procedure

Mount an endless-belt test specimen, with teeth pointing upward, on two flat pulleys having an equivalent diameter ranging between 100 mm and 175 mm and which are free to rotate. Apply a tension force to the specimen at the speed of (50 ± 5) mm/min until belt separation occurs.

If two cut belts are used as test specimens, the length gripped shall be at least 50 mm with a minimum distance of 150 mm between the two grips. Apply a tension force to one specimen at the speed of (50 ± 5) mm/min until separation takes place. Repeat the test with the second specimen.

7.2.3 Expression of results

The value for the tensile strength shall be taken as half the measured value for the endless-belt specimen or the smaller of the measured values of the two cut belts. Any data obtained when the specimen separates on the pulley surface or at the gripped portion shall be discarded.


7.3 Fabric adhesion test

7.3.1 Test specimens

Two specimens with a minimum length of 100 mm shall be cut from a belt.

7.3.2 Procedure

Place each specimen in the grips of a tensile-testing device, positioning the root line of the first tooth (No. 1) between 1 and 2, as illustrated in [Figure 1](#) ~~Figure 1.~~

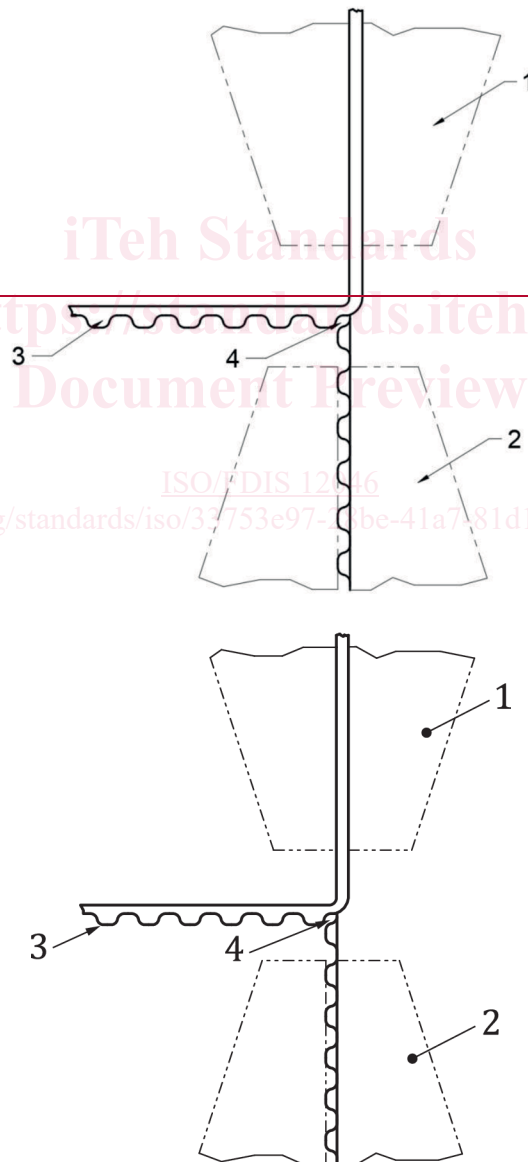

Key

- 1 grip A of the tensile-testing device
- 2 grip B of the tensile-testing device