



Designation: **F2328 – 05 (Reapproved 2011) F2328 – 14**

Standard Test Method for Determining Decarburization and Carburization in Hardened and Tempered Threaded Steel Bolts, Screws, Studs, and Nuts¹

This standard is issued under the fixed designation F2328; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*^{Scope*}

1.1 This test method covers procedures for measuring, classifying, and determining the presence of decarburization and carburization in the threaded section of hardened and tempered inch series steel bolts, screws, studs, nuts, and similar parts which have been heated to facilitate fabrication or to modify ~~its~~their mechanical properties. This test method is not intended to address products which are intentionally carburized to achieve specific results.

1.2 Two routine methods are described for measuring the limits of and determining the presence of decarburization or carburization—the optical method and the microindentation method 1. Either method is appropriate for routine examinations. The microindentation method 2 shall be considered the referee method.

1.3 For the purpose of these tests, there are ~~three~~four classes of hardened and tempered steel products for which specific measurements must be made with respect to their physical properties.

1.4 The values stated in inch-pound units are to be regarded as standard. No other units of measurement are included in this standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[E3 Guide for Preparation of Metallographic Specimens](#) [TM F2328-14](#)

[E384 Test Method for Knoop and Vickers Hardness of Materials](#)

[F1789 Terminology for F16 Mechanical Fasteners](#)

3. Terminology

3.1 *Definitions:*

3.1.1 *carburization*—process or result of increasing the carbon content of the surface layers of the steel fastener product.

3.1.2 *decarburization*—in accordance with Terminology [F1789](#), is a loss of carbon from the surface layer of the fastener, normally associated with heat treatment.

3.1.3 *gross decarburization*—also known as *complete decarburization*, is characterized by a sufficient carbon loss to show only clearly defined ferrite grains.

3.1.4 *partial decarburization*—characterized as a loss of carbon sufficient to cause a lighter shade of tempered martensite than that of the immediately adjacent base metal, but as being of insufficient carbon loss to show clearly defined ferrite grains.

4. Significance and Use

4.1 Decarburization and carburization are two surface conditions created, either intentionally or unintentionally, as with a pre-existing condition created during the rod rolling process, the rod/wire annealing process, or while heat treating threaded steel

¹ This test method is under the jurisdiction of ASTM Committee [F16](#) on Fasteners and is the direct responsibility of Subcommittee [F16.01](#) on Test Methods. Current edition approved ~~May 1, 2011~~Aug. 1, 2014. Published ~~June 2011~~September 2014. Originally approved in 2004. Last previous edition approved in ~~2005~~2011 as ~~F2328 – 05~~F2328 – 05(2011). DOI: ~~10.1520/F2328-05R11~~10.1520/F2328-14.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

***A Summary of Changes section appears at the end of this standard**

products. Too much of either will adversely affect the safety and performance of the threaded product. Therefore, limits have been established for three different product groups: the harder and greater the tensile strength of the product, the more susceptible to failure the product becomes if these limits are exceeded.

4.2 When testing to a particular product specification that lists the dimensions and microindentation data to be used, that data shall take precedence over the tables in this test method.

4.3 There are only two viable methods available to detect these deficiencies, either by the visual method or the microindentation method. Both methods are used for routine inspections when evaluations are conducted at a single location on the product sample.

4.3.1 Because an evaluation at a specific location may not be representative of the whole part, the referee method employs the microindentation method taken as an average of evaluations conducted on four adjacent threads. This procedure significantly reduces the random test variables when compared to testing on a single thread.

4.4 Specifying this test method does not specify or imply that testing shall be for either decarburization or carburization alone or for both conditions. When either test method is performed, both conditions will be apparent and shall be reported. For example, if an order is placed to test for decarburization and none is found, but the presence of carburization is detected, it shall be reported on the test report that carburization was found.

5. Class of Decarburization

5.1 *Class Determination*—These measurements by Class are predicated upon their relationship between the height (H) of the external thread at its maximum boundary, disregarding any surface coating, and N, which is the minimum thread height in the non-decarburized zone (see Figs. 1-3). The dimensions for N and H are listed in Table 2 for each Class. Dimension G (Table 1 and Fig. 1) represents the maximum depth of gross or complete decarburization.

NOTE 1—Refer to the product standard for specific requirements. When limits are not specified, use Table 1 as a suggested reference.

6. Preparation

6.1 The use of either the optical or microindentation method requires the finished product to be longitudinally cross-sectioned, approximately through the threaded axis, and mounted for grinding and polishing in any suitable medium which will provide edge retention of the specimen. This shall be performed in accordance with good metallographic practice. See Practice E3.

7. Evaluation by the Optical Method

7.1 Etch the mounted specimen (Section 6) in a 2 to 4 % nital or picral solution to exhibit the microstructure. Examine the specimen at 100× magnification using a method capable of measuring distances to at least 0.001 in. resolution. The width of any light-etching band of martensite defines the depth of decarburization. Compare the image with Fig. 1 for the maximum limits for G by taking a measurement on a line perpendicular to the flank of the thread midway between the thread crest and root (pitch diameter).

7.2 *Interpretation of Results:*

7.2.1 Allowable limits for partial decarburization shall be in accordance with 3.1.4 and Fig. 1, and the measured values shall be in accordance with Table 2, when measured in accordance with the illustrations in Figs. 2 and 3.

7.2.2 Allowable limits for gross decarburization (G) shall be in accordance with 3.1.3 and the measured values as defined in Table 1. The optical method is the only valid method for evaluating the depth of gross decarburization. Gross decarburization is prohibited in Class 3 products.

7.2.3 Carburization is identified when the tempered martensite is a darker shade than the immediately adjacent base metal. If visible evidence of surface carburization is present on the surface zone, the microindentation method, in accordance with Section 8, shall be used.

7.2.4 The optical method may not be appropriate for specimens with certain coatings, such as zinc, where the coating can affect the etching process and distort the appearance of the base material microstructure. These coatings shall be removed prior to mounting if the coating prevents proper etching. Care must also be exercised to not alter the surface condition of the substrate during the coating removal process.

7.2.5 If the results of the optical method indicate a possible nonconformance in the measurement of partial decarburization or carburization, or are otherwise inconclusive, the microindentation method (Section 8) shall be performed after the specimens are repolished.

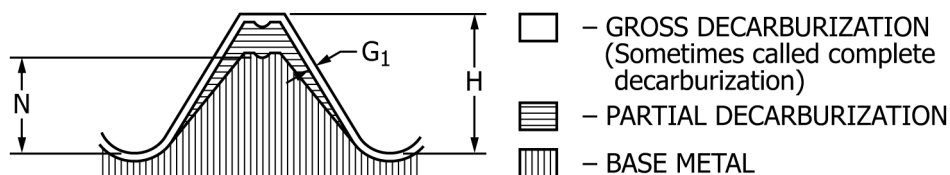


FIG. 1 Decarburization Zones