

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14869-1:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/781e24cc-cfcd-41f1-9314-bed4a757e5bb/sist-en-14869-1-2004>

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 14869-1

July 2004

ICS 83.180

English version

Structural adhesives - Determination of shear behaviour of structural bonds - Part 1: Torsion test method using butt-bonded hollow cylinders (ISO 11003-1:2001, modified)

Adhésifs structuraux - Détermination du comportement en cisaillement d'adhésifs structuraux - Partie 1: Méthode d'essai en torsion de cylindres creux collés bout à bout (ISO 11003-1:2001, modifiée)

Strukturklebstoffe - Bestimmung des Scherverhaltens struktureller Klebungen - Teil 1: Torsionsprüfverfahren unter Verwendung stumpf verklebter Hohlzylinder (ISO 11003-1:2001, modifiziert)

This European Standard was approved by CEN on 16 April 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Principle.....	4
5 Safety clause	4
6 Apparatus	4
7 Test specimen	7
7.1 Preparation	7
7.1.1 Substrate material.....	7
7.1.2 Preparation of the surface	7
7.1.3 Bonding	7
7.1.4 Adhesive bond	9
7.1.5 Dimensions.....	11
7.2 Number of specimens.....	11
8 Test conditions	11
8.1 Temperature	11
8.2 Shear rate	11
9 Procedure	12
10 Calculations.....	12
11 Precision.....	14
12 Test report	14

ITech STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 14869-1:2004

<https://standards.iteh.ai/catalog/standards/sist/781e24cc-cfcd-41f1-9314->

<bed4a757e5bb/sist-en-14869-1-2004>

Foreword

The text of the International Standard from Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) has been taken over as a European Standard (EN 14869-1:2004) by Technical Committee CEN/TC 193, "Adhesives", the secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 11003-1:2001 has been approved by CEN as a European Standard with agreed common modifications as given below:

- The title has been modified **(standards.iteh.ai)**
- Clause 2 "Normative references" has been updated
- Clause 3 "Terms and definitions" is new
- Clause 5 "Safety clause" is new
- Figures 2 and 3 have changed
- Subclauses 7.1.4 Adhesive bond, 7.1.5 Dimensions and subclauses 10.2 and 10.3 have changed.

EN 14869-1:2004 (E)**1 Scope**

This part of EN 14869 specifies a shear test for the characterization of adhesives in a bond. The shear stress/strain properties of the adhesive (including the shear modulus) are useful for advanced design work, e.g. in finite element analysis methods.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 923:1998, *Adhesives – Terms and definitions*.

EN 13887, *Structural adhesives – Guidelines for surface preparation of metals and plastics prior to adhesive bonding*.

EN ISO 291, *Plastics — Standard atmospheres for conditioning and testing*.

EN ISO 10365, *Adhesives - Designation of main failure patterns (ISO 10365:1992)*.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 923:1998 apply.

<https://standards.iteh.ai/catalog/standards/sist/781e24cc-cfcd-41f1-9314-bed4a757e5bb/sist-en-14869-1-2004>

4 Principle

The shear deformation of the adhesive in an annular bond between two hollow cylinders, and the corresponding torque, are measured and recorded up to failure of the joint.

5 Safety clause

The users of this standard shall be familiar with normal laboratory practice. This standard does not purport to address all safety problems, if any, associated with its use. It is the responsibility of the user to establish safety and health practices and to ensure compliance with any European and national regulatory conditions.

6 Apparatus


6.1 Torsion-testing machine, with a capacity of at least 300 N·m and preferably of 1 000 N·m. Alternatively, a suitably adapted tensile-testing machine may be used. The machine shall include equipment for recording the torque instantaneously with an error of less than 1%. The gripping heads shall be accurately aligned and, if no hydraulic gripping mechanism is available, all bolts and holes shall be precisely machined so that the specimens are mounted in the apparatus and tested free of uncontrolled loads. The machine shall be equipped with an adequately thermostatted chamber if tests are to be carried out at temperatures different from the ambient temperature.

6.2 Displacement sensor (see Figure 1), capable of measuring, as near as possible to the bond line, the displacement of the two adherends relative to each other and hence the deformation of the adhesive. The sensor and its associated target shall be rigidly mounted on the two adherends as shown in Figure 1. The range of the displacement-measuring equipment shall be adjustable to permit the full-scale reading to be varied between 2 μm and 1 000 μm . The equipment shall be capable of measuring displacements to an accuracy of $\pm 1 \mu\text{m}$. The sensor shall be of lightweight and robust construction since it is subjected to high accelerations on failure of the specimen.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 14869-1:2004](https://standards.iteh.ai/catalog/standards/sist/781e24cc-cfcd-41f1-9314-bed4a757e5bb/sist-en-14869-1-2004)

<https://standards.iteh.ai/catalog/standards/sist/781e24cc-cfcd-41f1-9314-bed4a757e5bb/sist-en-14869-1-2004>

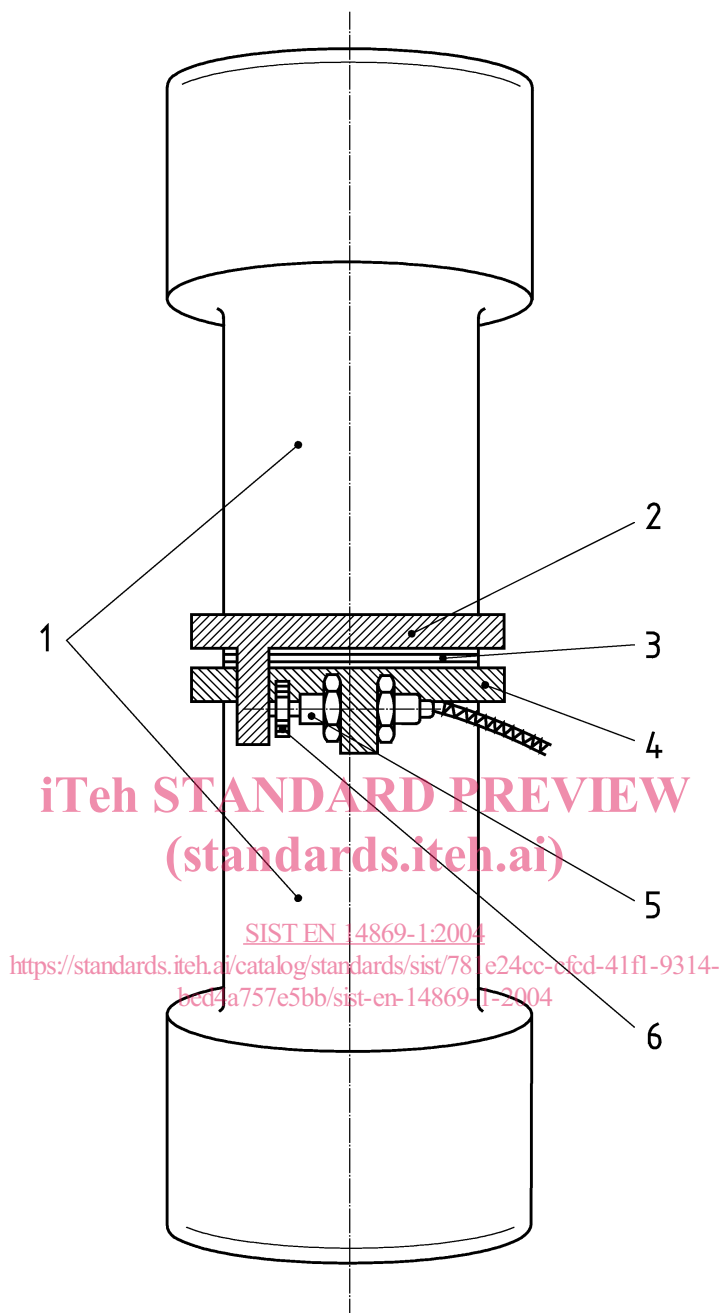

Key

- 1 Adherends
- 2 Target support (on upper adherend)
- 3 Butt joint
- 4 Transducer support (on lower adherend)
- 5 Displacement transducer
- 6 Target

Figure 1 — Adhesive-layer specimen with displacement transducer mounted in the test apparatus

7 Test specimen

7.1 Preparation

7.1.1 Substrate material

Aluminium alloy or steel are suitable materials for the adherends. Other materials are acceptable provided the material (including pre-treated surface layers) has a shear modulus at least ten times higher than that of the adhesive.

7.1.2 Preparation of the surface

The surfaces to be bonded shall be prepared in accordance with EN 13887 or by any method leading to a cohesive failure within the adhesive layer.

7.1.3 Bonding

Prepare the specimens in accordance with the instructions of the manufacturer of the adhesive. Information about conditioning of the specimen shall be included in the test report.

A joint completely filled with adhesive is essential for the reliability of the test. The two adherends shall be bonded coaxially, with a maximum lateral displacement between their two axes of $0,002 r_o$ (= outer radius), and a maximum angular deviation so that the bond line thickness varies by no more than 5% of the recommended thickness. The joining device shall prevent the adhesive from running out of the joint and any displacement of the two adherends during curing.

NOTE To achieve this, the two hollow cylinders may be aligned with the help of a plug made of polytetrafluoroethylene (PTFE) or any other suitable device. A temperature-resistant O-ring, inserted into the PTFE plug and placed just below the bond, stops the adhesive from running out of the joint. At the other ends of the adherends, two plates fastened to a threaded rod passing through the PTFE plug prevent any displacement during curing (see Figure 2).