
INTERNATIONAL STANDARD



3538

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Road vehicles — Safety glasses — Test methods for optical properties

Véhicules routiers — Vitres de sécurité — Méthodes d'essai des propriétés optiques

Second edition — 1978-06-15

ITeH STANDARD PREVIEW
(standards.iteh.ai)

[ISO 3538:1978](https://standards.iteh.ai/catalog/standards/sist/c84e6a1f-931e-4439-a2af-b909d2dda875/iso-3538-1978)

<https://standards.iteh.ai/catalog/standards/sist/c84e6a1f-931e-4439-a2af-b909d2dda875/iso-3538-1978>

UDC 629.113 : 666.155 : 666.181.6 : 620.1 : 535.3

Ref. No. ISO 3538-1978 (E)

Descriptors : motor vehicles, window glazing, safety glass, optical tests, distortion, visibility, light transmission

Price based on 8 pages

FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 3538 was developed by Technical Committee ISO/TC 22, *Road vehicles*. This second edition contains the new clause 7, which was circulated, in March 1977, as amendment 1.

This amendment has been approved by the member bodies of the following countries :

Australia	Italy	Romania
Austria	Japan	South Africa, Rep. of
Belgium	Korea, Dem. P. Rep. of	Spain
Brazil	Korea, Rep. of	Sweden
Canada	Mexico	Switzerland
Finland	Netherlands	Turkey
France	New Zealand	United Kingdom
Germany	Poland	U.S.S.R.
Iran	Portugal	

<https://standards.iteh.ai/catalog/standards/sist/c84e6a1f-931e-4439-a2af-b909d2dda875/iso-3538-1978>

The member body of the following country expressed disapproval of the amendment on technical grounds :

U.S.A.

This second edition cancels and replaces the first edition (i.e. ISO 3538-1975), which had been approved by the member bodies of the following countries :

Austria	Iran	Spain
Brazil	Israel	Sweden
Bulgaria	Italy	Switzerland
Canada	Netherlands	Turkey
Czechoslovakia	Poland	United Kingdom
Finland	Portugal	U.S.A.
France	Romania	Yugoslavia
Hungary	South Africa, Rep. of	

The member bodies of the following countries had expressed disapproval of the document on technical grounds :

Australia
Belgium
Germany

Road vehicles — Safety glasses — Test methods for optical properties

1 SCOPE AND FIELD OF APPLICATION

This International Standard specifies optical test methods relating to the safety requirements for all safety glasses in a road vehicle, whatever the type of glass or other material of which they are composed.

2 REFERENCES

ISO 48, *Vulcanized rubbers — Determination of hardness (Hardness between 30 and 85 IRHD)*.

ISO 3536/1, *Road vehicles — Safety glasses — Vocabulary — Part 1*.

3 TEST CONDITIONS

Unless otherwise specified, the tests shall be carried out under the following conditions :

Temperature : 20 ± 5 °C

Pressure : 860 to 1 060 mbar *

Relative humidity : 60 ± 20 %

4 APPLICATION OF TESTS

For certain types of safety glass, it is not necessary to carry out all the tests specified in this International Standard, when the results, according to the purpose of testing, can be predicted with certainty from a knowledge of the properties of the safety glass concerned.

5 LIGHT TRANSMISSION TEST

5.1 Purpose of test

The purpose of this test is to determine whether the safety glass has a certain regular light transmittance.

5.2 Apparatus

5.2.1 Light source, consisting of an incandescent lamp, the filament of which is contained within a parallelepiped $1,5 \text{ mm} \times 1,5 \text{ mm} \times 3 \text{ mm}$. The voltage at the lamp terminals shall be such that the colour temperature is $2\,856 \pm 50 \text{ K}$. This voltage shall be stabilized within $1/1\,000$. The instrument used to check the voltage shall be of appropriate accuracy.

5.2.2 Optical system, consisting of a lens with a focal length f of at least 500 mm and corrected for chromatic aberrations. The clear aperture of the lens shall not exceed $f/20$. The distance between the lens and the light source shall be adjusted in order to obtain a light beam which is substantially parallel. A diaphragm shall be inserted to limit the diameter of the light beam to $7 \pm 1 \text{ mm}$. This diaphragm shall be situated at a distance of $100 \pm 50 \text{ mm}$ from the lens on the side remote from the light source. The point of measurement shall be taken at the centre of the light beam.

5.2.3 Measuring equipment. The receiver shall have a relative spectral sensitivity in substantial agreement with the relative spectral luminous efficiency for the CIE¹⁾ standard photometric observer for photopic vision. The sensitive surface of the receiver shall be covered with a diffusing medium and shall have at least twice the cross-section of the light beam emitted by the optical system. If an integrating sphere is used, the aperture of the sphere shall be at least twice the cross-section of the parallel portion of the beam.

The linearity of the receiver and the associated indicating instrument shall be equal to, or better than, 2 % of the effective part of the scale.

The receiver shall be centred on the axis of the light beam.

* 1 mbar = 100 Pa = 100 N/m²

1) International Commission on Illumination.

5.3 Procedure

Adjust the instrument indicating the response of the receiver to indicate 100 divisions when the safety glass is not inserted in the light path. When no light is falling on the receiver, the instrument shall read zero.

Place the safety glass at a distance from the receiver of approximately five times the diameter of the receiver.

Insert the safety glass between the diaphragm and the receiver and adjust its orientation in such a way that the angle of incidence of the light beam is equal to $0 \pm 5^\circ$. The regular transmittance shall be measured on the safety glass, and for every point measured, the number of divisions, n , shown on the indicating instrument, shall be read. The regular transmittance τ_r is equal to $n/100$.

5.4 Expression of results

The regular transmittance τ_r shall be determined at any point on the safety glass, in accordance with the method specified above.

the inside of the circle subtends an angle of η minutes of arc at a point situated at x metres [figure 1 b)];

where

η is the limit value of secondary image separation;

x is the distance from the safety glass to the target (not less than 7 m);

D is given by the formula

$$D = x \tan \eta$$

The illuminated target consists of a light box, approximately 300 mm X 300 mm X 150 mm, the front of which is most conveniently constructed from glass masked with opaque black paper or coated with matt black paint. The box shall be illuminated by a suitable light source. The inside of the box shall be coated with matt white paint.

It may be convenient to use other forms of target, such as shown in figure 4. It is also acceptable to replace the target system with a projection system and to view the resulting images on a screen.

iTeh STANDARD PREVIEW
(standards.iht.com)

6 SECONDARY IMAGE SEPARATION TEST

6.1 Purpose of test

The purpose of this test is to determine the angular separation between the primary and secondary images.

6.2 Field of application

Two types of tests are recognized :

- target test;
- collimation telescope test.

These tests may be used for approval purposes, quality control or product evaluation as appropriate.

6.3 Target test

6.3.1 Apparatus

This method involves viewing an illuminated target through the safety glass. The target may be designed in such a way that the test can be carried out on a simple "Go — No Go" basis.

The target shall preferably be in the form of either

- a) an illuminated "ring" target, the outer diameter, D , of which subtends an angle of η minutes of arc at a point situated at x metres [figure 1 a)], or
- b) an illuminated "ring and spot" target, the dimensions of which are such that the distance, D , from a point on the edge of the spot to the nearest point on

6.3.2 Procedure

Mount the safety glass at the designed rake angle on a suitable stand in such a way that the observation is carried out in the horizontal plane passing through the centre of the target.

The light box shall be viewed in a dark or semi-dark room, through each part of the area being examined, in order to detect the presence of any secondary image associated with the illuminated target. Rotate the safety glass as necessary to ensure that the correct direction of view is maintained. A monocular may be used for viewing.

6.3.3 Expression of results

Determine whether

- using target a) (see figure 1), the primary and secondary images of the circle separate, i.e. whether the limit value of η is exceeded, or,
- using target b) (see figure 1), the secondary image of the spot shifts beyond the point of tangency with the inside edge of the circle, i.e. whether the limit value of η is exceeded.

6.4 Collimation telescope test

6.4.1 Apparatus

The apparatus consists of a collimator and telescope and may be set up in accordance with figure 3. Any equivalent optical system may, however, be used.



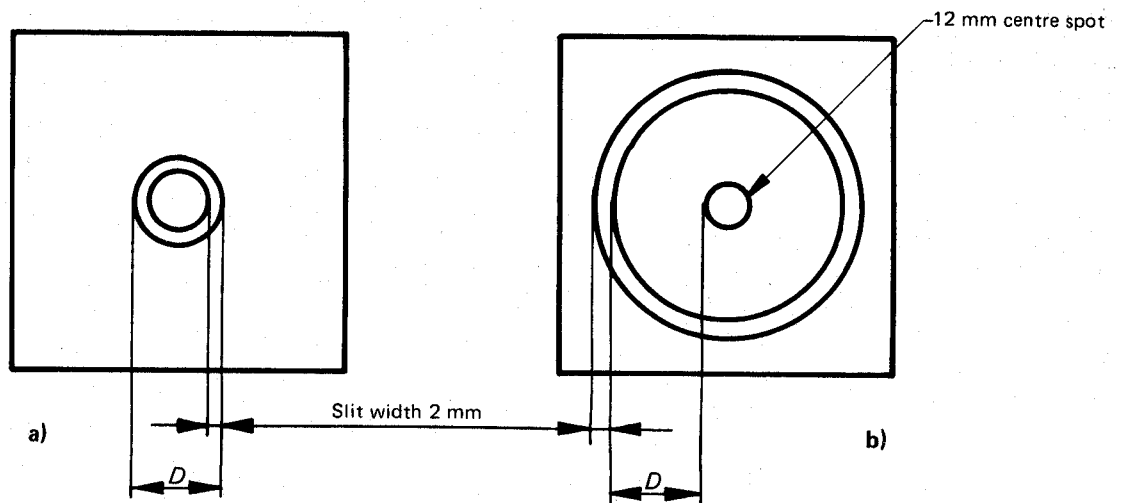


FIGURE 1 — Dimensions of targets

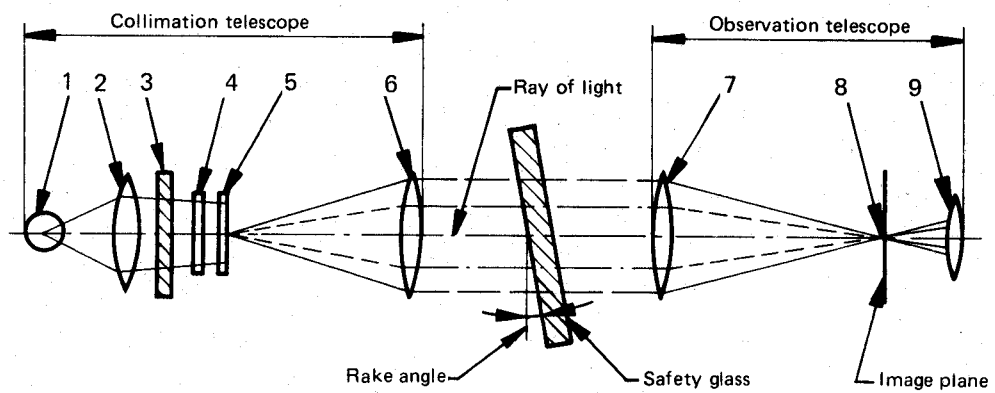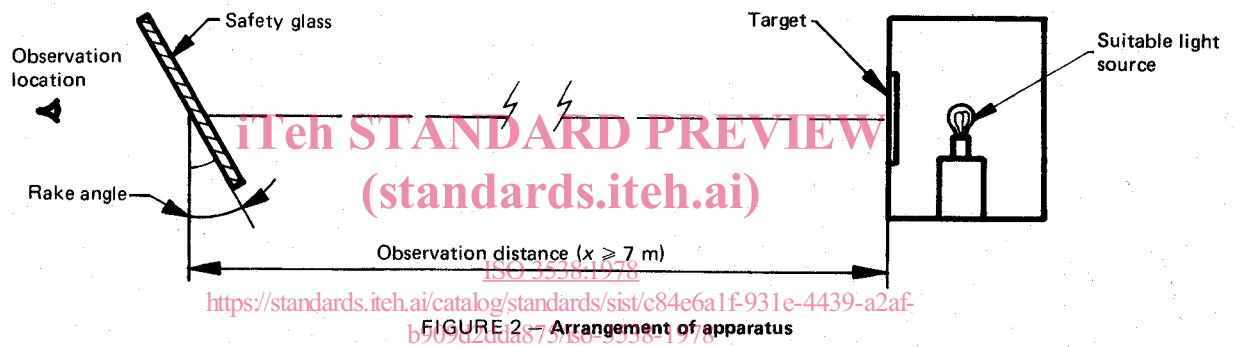

- 1) Bulb
- 2) Condenser, aperture $> 8,6$ mm
- 3) Ground-glass screen, aperture $>$ condenser aperture
- 4) Colour filter with central hole approximately 0,3 diameter; diameter $> 8,6$ mm
- 5) Polar co-ordinate plate, diameter $> 8,6$ mm
- 6) Achromatic lens, $f \geq 86$ mm, aperture 10 mm
- 7) Achromatic lens, $f \geq 86$ mm, aperture 10 mm
- 8) Black spot, diameter approximately 0,3 mm
- 9) Achromatic lens, $f = 20$ mm, aperture ≤ 10 mm

FIGURE 3 — Apparatus for collimation telescope test

6.4.2 Procedure

The collimation telescope forms at infinity the image of a polar co-ordinate system with a bright point at its centre (see figure 4).

In the focal plane of the observation telescope, a small opaque spot with a diameter slightly larger than of the projected bright point is placed on the optical axis, thus obscuring the bright point.

When a sample which exhibits a secondary image is placed between the telescope and the collimator, a second, less bright point appears at a certain distance from the centre of the polar co-ordinate system. The secondary image separation can be read out as the distance between the points seen through the observation telescope (see figure 4).

(The distance between the dark spot and the bright point at the centre of the polar co-ordinate system represents the optical deviation.)

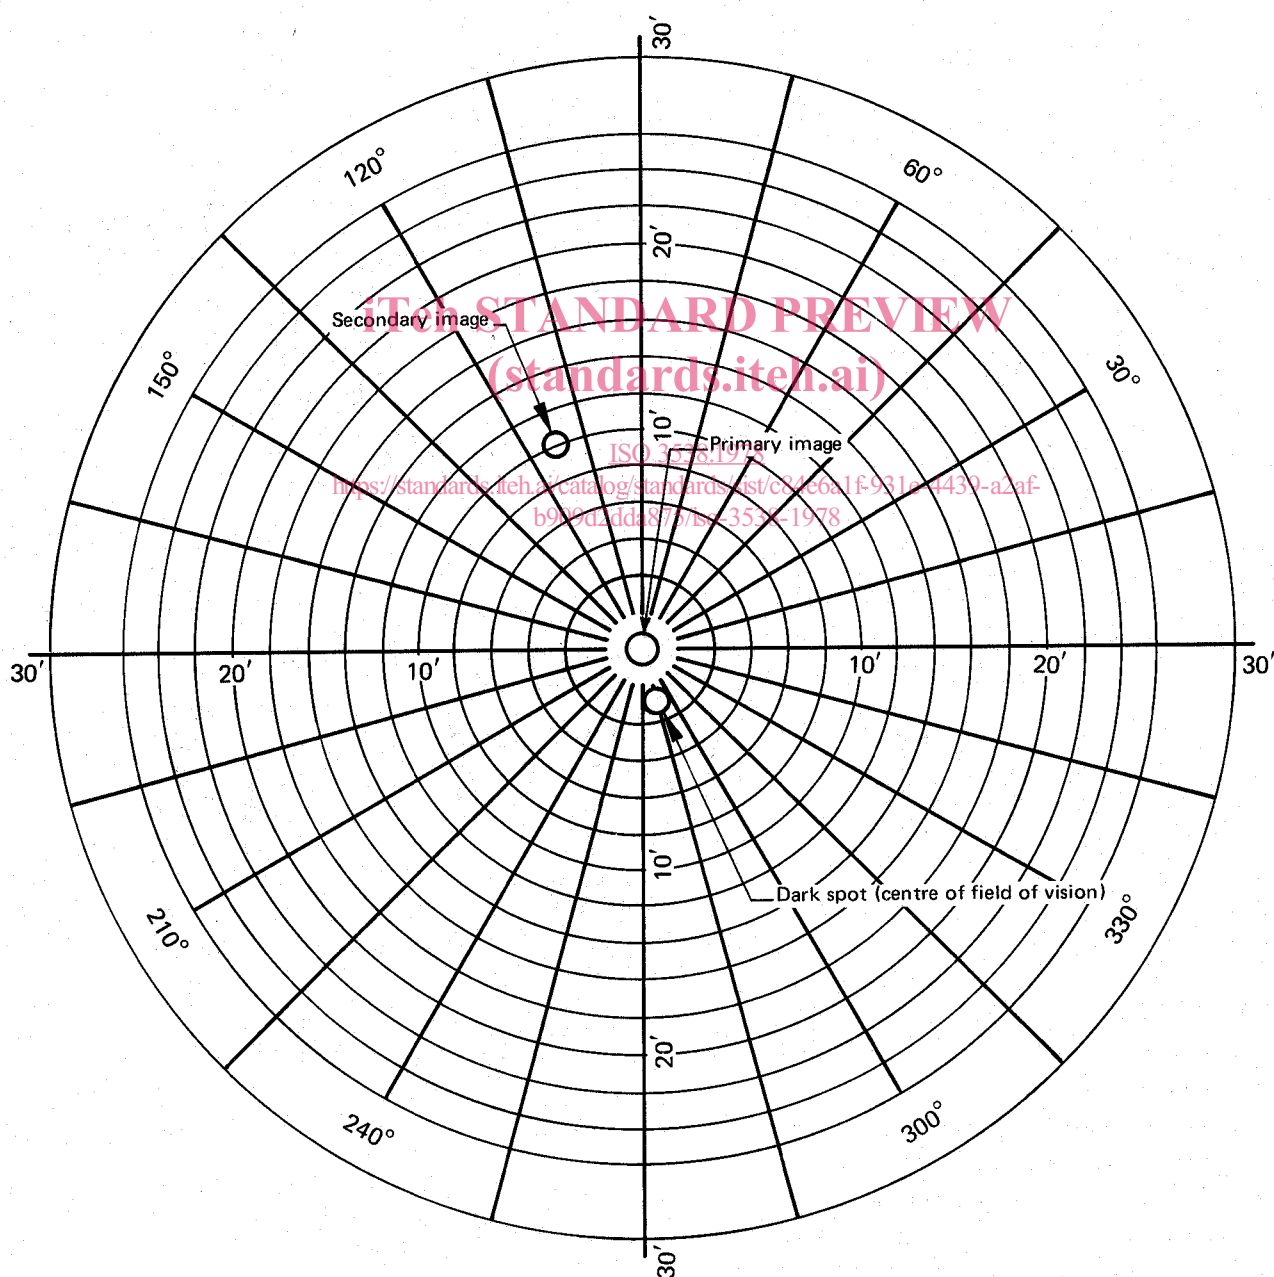


FIGURE 4 – Example of observation by the collimation telescope test

6.4.3 Expression of results

The safety glass shall first be examined using a simple scanning technique to establish the area giving the most severe secondary image. The worst area shall then be examined using the collimator-telescope system at the appropriate angle of incidence. The maximum secondary image separation shall be measured.

7 OPTICAL DISTORTION TEST

7.1 Purpose of test

The purpose of this test is to determine the optical distortion of the safety glass.

7.2 Field of application

The method specified is a projection method which permits the evaluation of the optical distortion of a safety glass.

7.3 Definitions

7.3.1 optical deviation : The angle between the true and apparent direction of a point viewed through the safety glass, the magnitude of the deviation being a function of the angle of incidence of the line of sight, the thickness and inclination of the glass and the radius of curvature at the point of incidence.

7.3.2 optical distortion in a given direction MM' : The algebraic difference in angular deviation $\Delta\alpha$ measured between two points M and M' on the surface of the glass, the distance between them being such that their projections

in a plane at right angles to the direction of vision are separated by a given distance Δx (see figure 5).

NOTES

$\Delta\alpha = \alpha_1 - \alpha_2$, i.e. the optical distortion in the direction MM' .

$\Delta x = MC$, i.e. the distance between two straight lines parallel to the direction of vision, and passing through the points M and M'.

Anti-clockwise deviation should be regarded as positive, and clockwise deviation as negative.

7.3.3 optical distortion at a point M : The optical distortion maximum for all directions MM' from the point M.

7.4 Apparatus

This method involves the projection of an appropriate slide (raster) through the safety glass being tested onto a display screen. The change in shape of the projected image caused by the insertion of the glass provides a measure of the distortion.

The apparatus shall consist of the following items, arranged as shown in figure 6.

7.4.1 Projector, of good quality, with a high-intensity point light source, having for example, the following characteristics :

- focal length at least 90 mm;
- aperture approximately 1/2,5;
- 150 W quartz halogen lamp (if used without a filter);
- 250 W quartz halogen lamp (if a green filter is used).

The projector is shown schematically in figure 7. An 8 mm diameter diaphragm is positioned approximately 10 mm from the front lens of the objective.

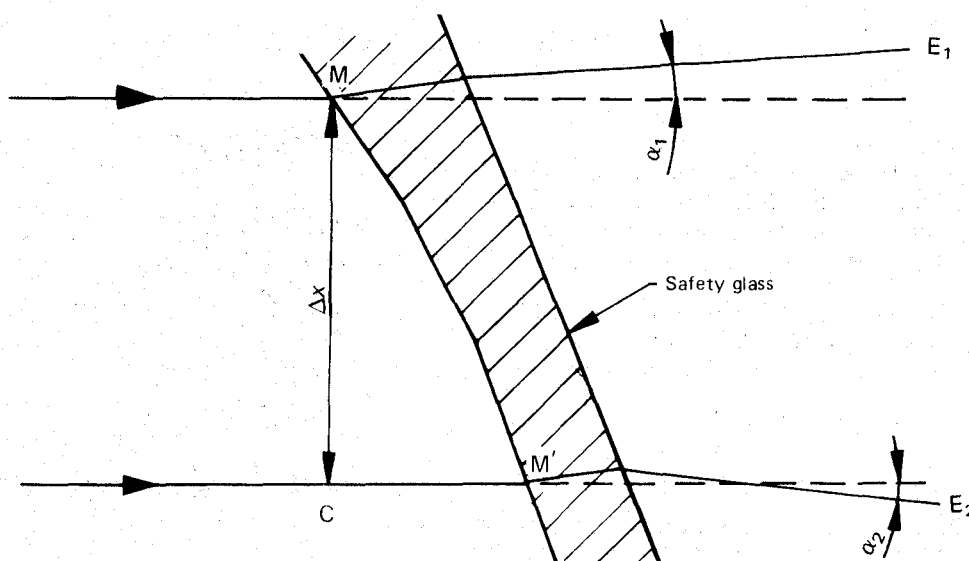


FIGURE 5 — Diagrammatic representation of optical distortion

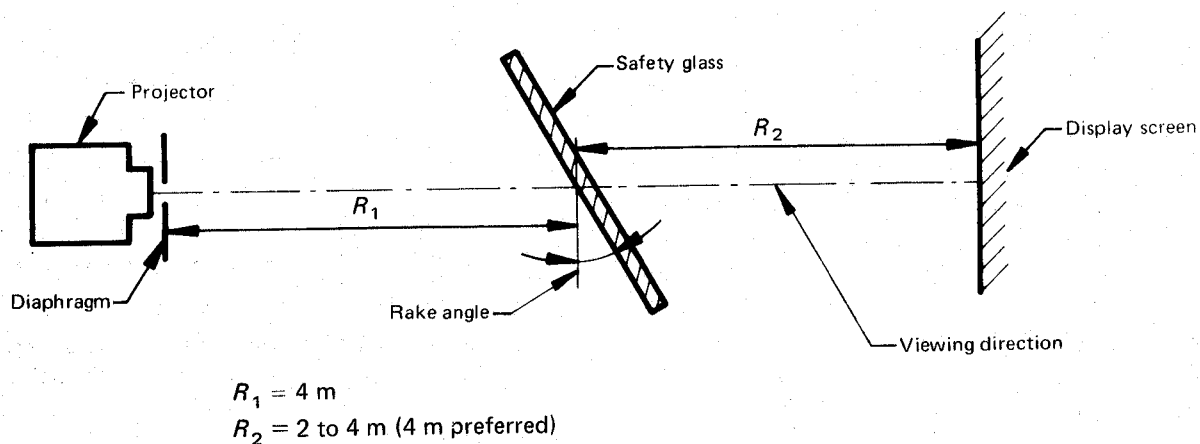


FIGURE 6 – Arrangement of the apparatus for the optical distortion test

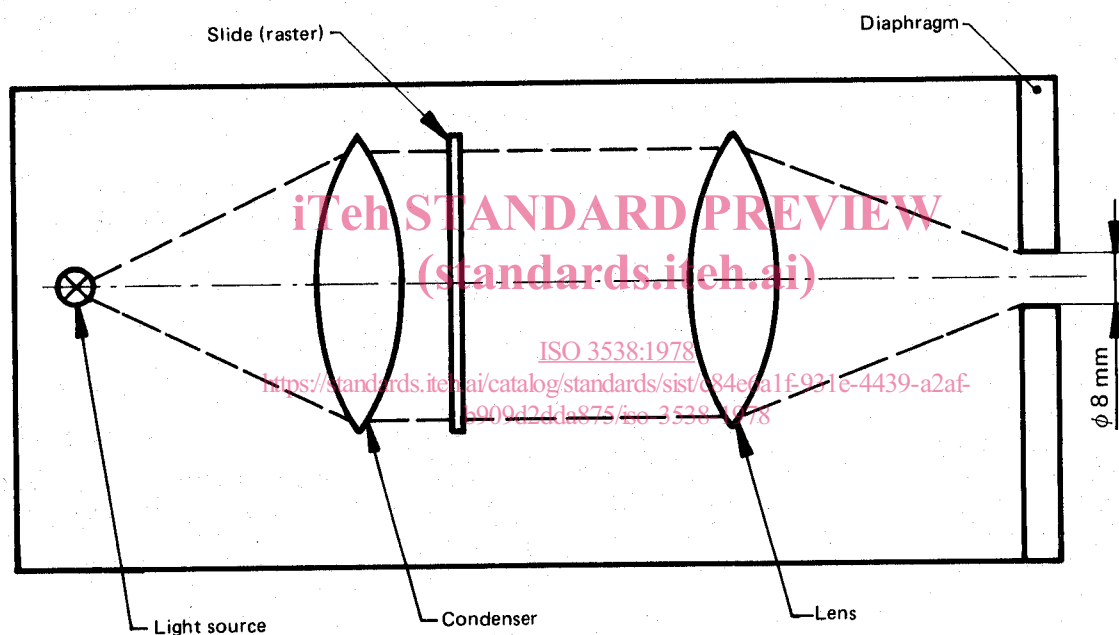


FIGURE 7 – Optical arrangement of the projector

7.4.2 Slides (rasters), consisting, for example, of an array of bright circular shapes on a dark background (see figure 8). The slide shall be of sufficiently high quality and contrast to enable measurement to be carried out with a tolerance less than 5 %.

In the absence of the safety glass to be examined, the dimensions of the circular shapes shall be such that when projected on the screen these form an array of circles of diameter $\frac{R_1 + R_2}{R_1} \Delta x$ (see figures 5 and 6).

NOTES

- 1 Because of the possibility of distortion in the optical distortion system, it is recommended that only the centre zone of the projected image be used for measurement purposes.
- 2 The arrangement of the apparatus should be such that the ratio R_1/R_2 is unity, to preserve the accuracy of measurement.

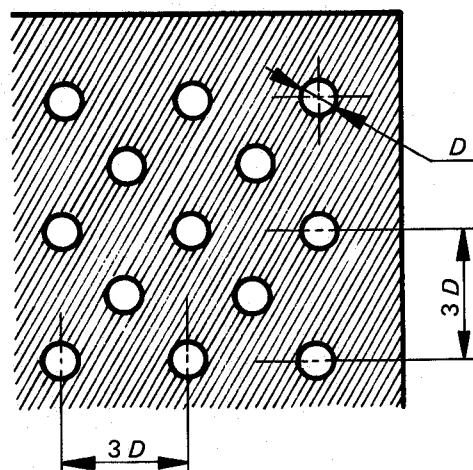


FIGURE 8 – Enlarged section of the slide

7.4.3 Support stand, preferably one permitting vertical and horizontal scanning, as well as rotation of the safety glass.

7.4.4 Checking template, for measuring the change in dimensions, where a rapid assessment is required. A suitable design is shown in figure 9.

7.5 Procedure

7.5.1 General

Mount the safety glass on the support stand (7.4.3) at the designed rake angle. Project the test image through the area being examined. Rotate the safety glass or move it either horizontally or vertically in order to examine the whole of the specified area.

7.5.2 Assessment using checking template

Where a rapid assessment is sufficient, to a precision of not better than 20 %, calculate the value of A (see figure 9) from the limit value $\Delta\alpha_L$ for the change deviation and the value of R_2 , the distance from the safety glass to the display screen :

$$A = 0,145 \Delta\alpha_L \times R_2$$

The relationship between the change in diameter of the projected image Δd and the change in angular deviation $\Delta\alpha$ is given by

$$\Delta d = 0,29 \Delta\alpha \times R_2$$

where

Δd is in millimetres;

A is in millimetres;

$\Delta\alpha_L$ is in minutes of arc;

$\Delta\alpha$ is in minutes of arc;

R_2 is in metres.

7.5.3 Measurement using photoelectric device

Where a precise measurement is required, to a precision of better than 10 % of the limit value, measure Δd on the projection axis, the value of the spot width being taken at the point where the luminance is 0,5 times the maximum luminance value.

7.6 Expression of results

Evaluate the optical distortion of the safety glass by measuring Δd in all directions at any point of the surface to be examined, in order to find Δd max.

7.7 Alternative method

In addition, a strioscopic technique is permitted as an alternative to the projection techniques, provided that the precision of the measurements given in 7.5.2 and 7.5.3 is maintained.

8 VISIBILITY TEST AFTER FRACTURE

8.1 Purpose of test

The purpose of this test is to determine whether the safety glass allows a certain visibility after fracture. This test shall be carried out on the outside face of the safety glass.

8.2 Apparatus

Instrument capable of causing the glass to break from the impacted surface such as a hammer with a pointed head or an automatic punch.

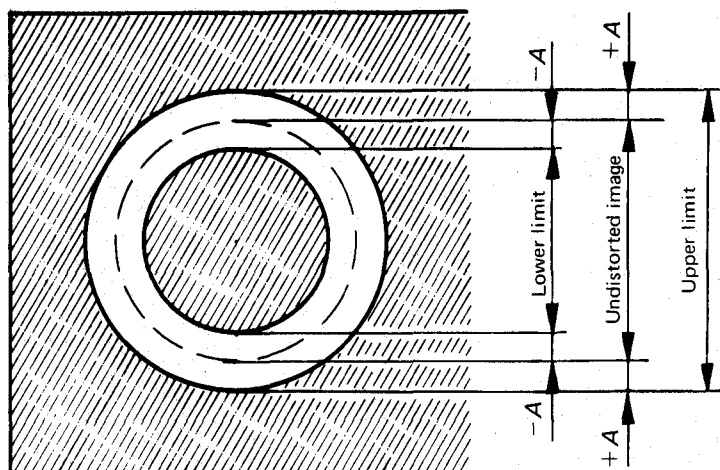


FIGURE 9 — Design for a suitable checking template