

INTERNATIONAL
STANDARD

ISO
3597-1

First edition
1993-11-15

**Textile-glass-reinforced plastics —
Determination of mechanical properties on
rods made of roving-reinforced resin —**

iTeh Standards

Part 1:

(<https://iteh.ai/standards/iso-3597-1-1993>) preparation of rods

Document Preview

*Plastiques renforcés verre textile — Détermination des propriétés
mécaniques sur joncs de stratifis —*

Partie 1: Notions générales et préparation des joncs

<https://standards.iteh.ai/catalog/standards/iso/c9956e1c-de27-4290-bcfe-135c15a88803/iso-3597-1-1993>



Reference number
ISO 3597-1:1993(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 3597-1 was prepared by Technical Committee ISO/TC 61, *Plastics*, Sub-Committee SC 13, *Composites and reinforcement fibres*.

This first edition, together with the other parts of ISO 3597, cancels and replaces ISO 3597:1977, which has been technically revised.

ISO 3597 consists of the following parts, under the general title *Textile-glass-reinforced plastics — Determination of mechanical properties on rods made of roving-reinforced resin*:

- Part 1: *General considerations and preparation of rods*
- Part 2: *Determination of flexural strength*
- Part 3: *Determination of compressive strength*
- Part 4: *Determination of apparent interlaminar shear strength*

Annex A of this part of ISO 3597 is for information only.

© ISO 1993

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Textile-glass-reinforced plastics — Determination of mechanical properties on rods made of roving-reinforced resin —

Part 1: General considerations and preparation of rods

1 Scope

This part of ISO 3597 provides general information and specifies a method for preparing specimens (rods) intended to be used for tests specified in the other parts of ISO 3597.

2 Normative references

<https://standards.iteh.ai/catalog/standards/iso/c9936efc-de>
The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 3597. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 3597 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 7822:1990, *Textile glass reinforced plastics — Determination of void content — Loss on ignition, mechanical disintegration and statistical counting methods*.

3 Principles

The testing methods briefly described hereafter are generally performed on as-made rods. They may however, also be carried out on rods which have been

submitted to a boiling water pretreatment for a specified time.

The preparation of rods as detailed in clause 5 includes the manufacture and division of rods into specimens of given length and their treatment in boiling water, if such treatment is required.

In order to obtain consistent results, conditions for the preparation of the rods (resin mixture, impregnation system and pulling speed, cure conditions, etc.) shall be as uniform as possible. Furthermore, if the roving specification requires that the void content of rods to be tested shall be within given limits, this characteristic shall be determined in accordance with ISO 7822.

3.1 Determination of flexural strength

The specimen is laid horizontally on two supports and deformed at constant speed by applying a stress at midspan until the specimen breaks or until the strain has reached a predetermined level.

The flexural strength of the specimen, expressed in megapascals, is the stress measured at that moment.

3.2 Determination of compressive strength

The specimen is axially compressed by applying a stress on the flanges at constant speed until the specimen breaks or until the deformation has reached a predetermined level.

The compressive strength of the specimen, expressed in megapascals, is the stress measured at that moment.

3.3 Determination of apparent interlaminar shear strength

A simple flexural test is carried out as described in 3.1 on a specimen, using however a span shorter than that used for the standard flexural test.

The apparent interlaminar shear strength of the specimen, expressed in megapascals, is the stress measured at failure or the maximum stress that is reached in the test.

4 Conditioning and testing atmospheres

The atmosphere required for conditioning and for testing the specimens is specified in ISO 291.

5 Preparation of the test specimens

5.1 Apparatus and material

5.1.1 Mould, in the form of a rigid cylinder having a minimum length of 300 mm and a standard internal diameter of $4\text{ mm} \pm 0,1\text{ mm}$ (for flexural and interlaminar shear strength tests) or $6\text{ mm} \pm 0,1\text{ mm}$ (for compression test). If other diameters are chosen, these shall be selected by agreement between the interested parties from the range of 3 mm to 10 mm (with tolerances of $\pm 0,1\text{ mm}$). It is highly recommended however that the standard diameter be chosen, since the use of different diameters will not allow true comparison of the results.

[ISO 3597-1-1993](https://standards.iteh.ai/catalog/standards/iso/c9936efc-de27-4290-bc1e-155cf5a88805/iso-3597-1-1993)

The mould may be constructed of glass or polytetrafluoroethylene.

A release agent may be used if the shrinkage after moulding is very low (typical of epoxy resins).

5.1.2 Resin.

Not all resin systems are necessarily suitable; the system used shall be at the discretion of the roving supplier. In the event of dispute, the system used shall be declared and shall form the basis for the test; it may be the subject of an agreement between the interested parties. The selected resin system shall be mixed in accordance with the resin manufacturer's detailed instructions (see annex A for examples of resin formulas with curing conditions).

5.1.3 Metal wire or synthetic yarn (for example polyamide or polyester), for pulling the roving through the mould (5.1.1).

5.1.4 Impregnation equipment (see figure 1), including one or two impregnating baths. It is recommended that a device for removing air bubbles by means of rollers be included. It is also recommended that, for pultrusion of the rods, the machine be adjustable to a constant speed in the range of 1 mm/s to 12 mm/s.

5.1.5 Oven with air circulation, for curing and/or postcuring the resin at the recommended temperature.

5.1.6 Diamond-tipped saw.

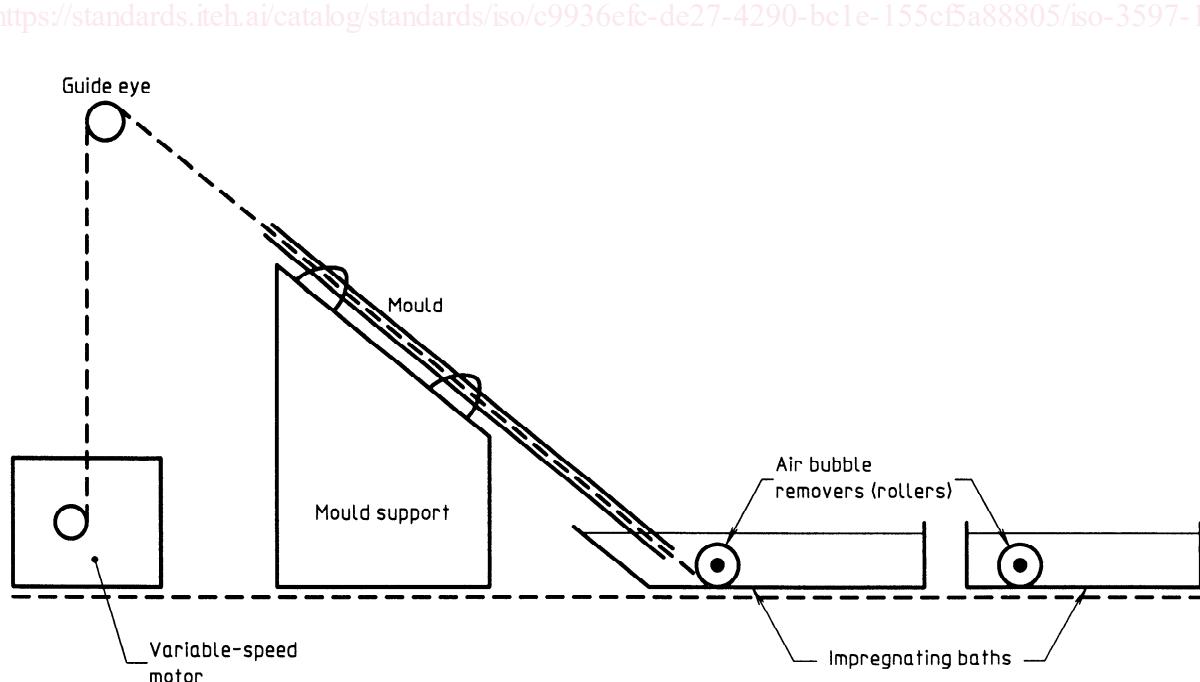


Figure 1 — Example of equipment set-up for impregnation of rovings