



Designation: ~~D2211 – 00 (Reapproved 2010)~~ D2211 – 00 (Reapproved 2015)

Standard Test Method for Elongation of Leather¹

This standard is issued under the fixed designation D2211; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the measurement of the elongation or stretch characteristics of leather produced by a tensile load. This test method is intended for use on all types of leather and with all of the breaking load tests. This test method does not apply to wet blue.

1.2 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D1610 Practice for Conditioning Leather and Leather Products for Testing](#)

[D2209 Test Method for Tensile Strength of Leather](#)

3. Terminology

3.1 *Definitions:*

3.1.1 *elongation, or stretch*—the increase in length of a span of specimen under tension.

4. Significance and Use

4.1 The elongation measurement may be made at any designated load and is expressed as a percentage of the original distance between the jaws or between bench marks of the unstretched specimen. The speed of the machine is important. Speeds under or more than 10 ± 2 in./min (4.2 ± 0.8 mm/s) will give variables in the results, thus affecting the reproducibility of the method. The direction relative to the backbone and the width of the test specimen determines the magnitude of the elongation. This test method is excellent for development, control, specification acceptance, and service evaluation of leather. This test method may not apply when the conditions of the test employed differ widely from those specified in the test method.

5. Apparatus

5.1 *Testing Machine*, as described in Test Method [D2209](#).

5.2 *Dividers*, having legs at least 4 in. (102 mm) long and an adjustable screw arrangement for fixing the distance between them.

5.3 *Steel Scale*, graduated to read in 0.02 in. (0.5 mm).

6. Test Specimen

6.1 The specimen shall be dumbbell in shape when the test is made with the tension test. It shall be cut from the test unit of leather by means of a die as shown in Fig. 1 of Test Method [D2209](#). The direction of the long axis relative to the backbone shall be noted.

¹ This test method is under the jurisdiction of ASTM Committee [D31](#) on Leather and is the direct responsibility of Subcommittee [D31.07](#) on Physical Properties. This test method was developed in cooperation with the American Leather Chemists Assn.

Current edition approved ~~Oct. 1, 2010~~ May 1, 2015. Published ~~November 2010~~ July 2015. Originally approved in 1963. Last previous edition approved in ~~2005~~ 2010 as D2211 – 00 (~~2005~~ (2010)). DOI: ~~10.1520/D2211-00R10~~ 10.1520/D2211-00R15.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

6.2 The specimen for narrow strap, welting, lace, and round belting leathers shall be a piece of leather uniform in width and 6 in. (152 mm) long.

6.3 The specimen for the grab method of determining breaking load shall be 6 in. (152 mm) long and 3 in. (76 mm) wide.

7. Conditioning

7.1 All specimens shall be conditioned as prescribed in Practice D1610. Conditioning other than as prescribed shall be noted in the results.

8. Procedure

8.1 Mount the specimen symmetrically with the jaws separated a distance of 4 in. (102 mm).

8.2 Operate the machine so that the movable grip travels at a speed of 10 ± 2 in./min (4.2 ± 0.8 mm/s).

8.3 Follow the distance between the jaws or the difference between bench marks with the dividers until the load at which the elongation is desired has been reached. Take all measurements between the inner edges of the jaws or between the inner edges of the bench marks. Measure the distance between the points of the legs of the dividers to the nearest 0.02 in. (0.5 mm). An autographic attachment is preferred for determining the elongation. With this arrangement the elongation may be obtained from the chart at any desired load.

8.4 If the elongation is determined as a span shorter than the distance between the jaws, use a 2-in. (51-mm) bench marker or its equivalent, as shown in Fig. 1. Mark the specimen over the span at which it is desired to make the elongation measurement.

NOTE 1—In general, results obtained for elongation over a 2-in. (51-mm) span marked by the bench marker on the narrow section of the tension test specimen will be greater than that obtained by determining the average elongation over the entire span between the jaws.

8.5 If an autographic recorder is used, read the elongation to the nearest 0.1 in. (2.5 mm).

9. Calculation

9.1 Calculate the elongation to the nearest 0.1 % of the original distance over the span as follows:

$$\text{Elongation, \%} = [(D_2 - D_1)/D_1] \times 100 \tag{1}$$

where:

D_1 = span of the original unstretched specimen, in. (mm), and


D_2 = span of the stretched specimen, in. (mm), when the required load has been applied.

10. Report

10.1 The report shall include the following:

10.1.1 Percentage elongation reported for each specimen or average and reported as the elongation of the sample, and

10.1.2 Direction of the long axis of the specimen relative to the backbone.

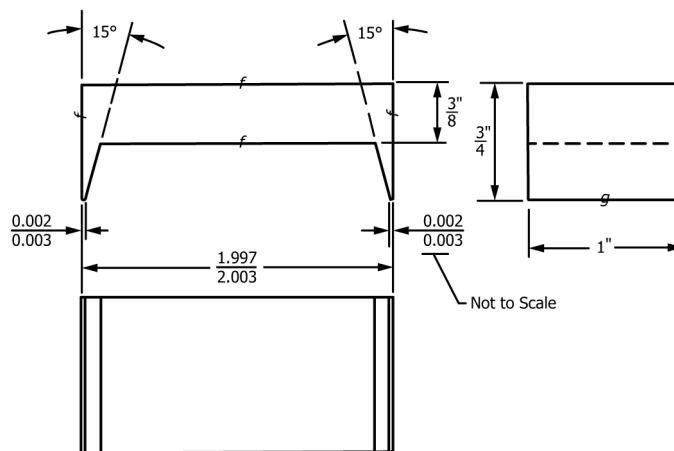

Metric Equivalents		0.002	0.003	3/8	3/4	1	1.997	2.003
in.		0.002	0.003	3/8	3/4	1	1.997	2.003
(mm)		(0.05)	(0.08)	(9.5)	(19)	(25.4)	(50.72)	(50.88)

FIG. 1 Bench Marker