



## Designation: ~~A1001–01 (Reapproved 2010)~~ A1001 – 01 (Reapproved 2015)

# Standard Specification for High Strength Steel Castings in Heavy Sections<sup>1</sup>

This standard is issued under the fixed designation A1001; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This specification covers cast alloy steels in the normalized and tempered or quenched and tempered condition, in section sizes through 37 in. (940 mm), suitable for high strain gradient conditions such as those encountered in hooks, shackles, support frames, and other lifting devices. The classes of steel in this specification are weldable only with qualified procedures.

1.2 Section range and class selection will depend on design and service conditions. Users should note that this specification contemplates mechanical property gradients.

1.3 The values stated in inch-pound units or SI units are to be regarded separately as standard. Within the text, the SI units are shown in brackets. The values stated in each system are not exact equivalents; therefore, each system must be used independently of the other. Combining values from the two systems may result in non-conformities with the specification. Inch-pound units are applicable for material ordered to this Specification and SI units for material ordered to this Specification.

1.4 If, by agreement, castings are to be supplied in a partially completed condition, that is, all of the provisions of the product specification have not been filled, then the material marking (see Section 15) and certification (see Section 14) are to reflect the extent to which the product specification requirements have been met.

## 2. Referenced Documents

### 2.1 *ASTM Standards:*<sup>2</sup>

[A370 Test Methods and Definitions for Mechanical Testing of Steel Products](#)

[A609/A609M Practice for Castings, Carbon, Low-Alloy, and Martensitic Stainless Steel, Ultrasonic Examination Thereof](#)

[A703/A703M Specification for Steel Castings, General Requirements, for Pressure-Containing Parts](#)

[E94 Guide for Radiographic Examination](#)

[E165 Practice for Liquid Penetrant Examination for General Industry](#)

[E709 Guide for Magnetic Particle Testing](#)

[E1019 Test Methods for Determination of Carbon, Sulfur, Nitrogen, and Oxygen in Steel, Iron, Nickel, and Cobalt Alloys by Various Combustion and Fusion Techniques](#)

[E1447 Test Method for Determination of Hydrogen in Titanium and Titanium Alloys by Inert Gas Fusion Thermal Conductivity/Infrared Detection Method](#)

[E1806 Practice for Sampling Steel and Iron for Determination of Chemical Composition](#)

### 2.2 *Manufacturers Standardization of the Valve and Fittings Industry Standards:*

[MSS SP-55 Quality Standard for Steel Castings – Visual Method](#)<sup>3</sup>

## 3. General Conditions for Delivery

3.1 Materials furnished to this Specification shall conform to the applicable requirements of Specification [A703/A703M](#), including the supplementary requirements that are indicated on the purchase order.

3.2 Terminology and test methods shall be in accordance with Test Methods and Definitions [A370](#).

3.3 In the case of conflict between requirements of this specification and referenced specifications, the former shall prevail.

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee A01.18 on Castings.

Current edition approved Oct. 1, 2010 Dec. 15, 2015. Published December 2010 December 2015. Originally approved in 1999. Last previous edition approved in 2006 2010 as ~~A1001–01~~ A1001 – 01 (2010). (~~2006~~)–DOI: ~~10.1520/A1001-01R10~~ 10.1520/A1001-01R15.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from Manufacturers Standardization Society of the Valve and Fittings Industry (MSS), 127 Park St., NE, Vienna, VA 22180-4602.

#### 4. Ordering Information

4.1 It shall be the responsibility of the purchaser to specify all requirements that are necessary for material ordered under this specification. Such requirements to be considered include, but are not limited to, the following:

4.1.1 A description of the casting by pattern number or a fully dimensional and toleranced drawing,

4.1.2 ASTM designation and year of issue,

4.1.3 Section range and class of steel (see [Table 1](#)),

4.1.4 Definition of inspection methods, extent of examination, frequency, casting quality zones, and acceptance criteria (see [Section 11](#)).

4.1.5 Product marking locations (see [Section 15](#)),

4.1.6 Certification report options (see [Section 14](#)),

4.1.7 Options in the specification (see [1.4](#) and [11.6](#)), and

4.1.8 The supplementary requirements desired.

#### 5. Test Block Requirements

5.1 The supplier shall produce a minimum of one test block for each heat.

5.2 Test block configuration shall be in accordance with [Fig. 1](#). A standard draft angle is permitted over the length “L” of the test block provided the minimum cylinder diameter is greater than “T” given in [Table 2](#).

5.3 Test block size shall be in accordance with [Table 2](#) for specified section range. The section range selection made by the purchaser (see [4.1.3](#)) should consider casting section size and geometry, service conditions, mechanical property correlations developed by the supplier, or other important factors.

5.4 Tension and Charpy impact tests shall be performed on specimens taken from both the 1/8T and 3/8T locations and shall be oriented within the 8-in. (203-mm) midsection as shown in [Fig. 1](#).

5.5 Oxygen and nitrogen gas content tests shall be performed on specimens taken from the 3/8T location and shall be within the 8 in. (203 mm) midsection as shown in [Fig. 1](#).

#### 6. Materials and Manufacture

6.1 The steel shall be made by electric furnace process with methods to conform to the maximum gas levels given in [Table 3](#). These methods may include a special refining process such as argon-oxygen-decarburization (AOD).

6.2 Heat treatment procedure shall be reported to the purchaser by the supplier for the specified section range, class, and grade.

6.2.1 Multiple austenitizing is permitted.

6.2.2 Multiple tempering is permitted. The minimum final tempering temperature shall not be less than 1100°F (593°C). Post weld heat treatment shall not be less than 1050°F (566°C).

**TABLE 1 Required Mechanical Properties**

Section Range	Class	Chemistry Grade <sup>A</sup>	Tensile Strength		Yield Strength, min ksi (MPa) at 0.2 % Offset		Elongation, 2 in (50 mm) or 4d, min, %		Reduction of Area, min %		Charpy V-Notch, Min Average, ft-lb (J)	
			T/8 <sup>B</sup>	3T/8 <sup>B</sup>	T/8 <sup>B</sup>	3T/8 <sup>B</sup>	T/8 <sup>B</sup>	3T/8 <sup>B</sup>	T/8 <sup>B</sup>	3T/8 <sup>B</sup>	T/8 <sup>B</sup>	3T/8 <sup>B</sup>
1	A	I, II	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
1	B	I	105 (725)	95 (655)	85 (585)	76 (525)	15	11	30	22	25 (34)	15 (20)
1	C	I	90 (620)	80 (550)	70 (485)	63 (435)	17	13	34	26	25 (34)	15 (20)
2	A	I	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
2	B	I	105 (725)	95 (655)	85 (585)	76 (525)	16	12	32	24	25 (34)	15 (20)
2	C	I	90 (620)	80 (550)	70 (485)	63 (435)	18	14	36	28	25 (34)	15 (20)
3	A	I, III	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
3	B	I	105 (725)	95 (655)	85 (585)	76 (525)	17	13	34	26	25 (34)	15 (20)
3	C	I	90 (620)	80 (550)	70 (485)	63 (435)	19	16	38	32	25 (34)	15 (20)
4	A	I, II	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
4	B	I	105 (725)	95 (655)	85 (585)	76 (525)	19	16	38	32	25 (34)	15 (20)
4	C	I	90 (620)	80 (550)	70 (485)	63 (435)	21	18	42	36	25 (34)	15 (20)
5	A	I, II	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
5	B	I	105 (725)	95 (655)	85 (585)	76 (525)	19	16	38	32	25 (34)	15 (20)
5	C	I	90 (620)	80 (550)	70 (485)	63 (435)	21	18	42	36	25 (34)	15 (20)
6	A	I	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
6	B	I	105 (725)	95 (655)	85 (585)	76 (525)	19	16	38	32	25 (34)	15 (20)
6	C	I	90 (620)	80 (550)	70 (485)	63 (435)	21	18	42	36	25 (34)	15 (20)
7	A	I	110 (760)	100 (690)	90 (620)	80 (550)	18	15	36	30	25 (34)	15 (20)
7	B	I	105 (725)	95 (655)	85 (585)	76 (525)	19	16	38	32	25 (34)	15 (20)
7	C	I	90 (620)	80 (550)	70 (485)	63 (435)	21	18	42	36	25 (34)	15 (20)

<sup>A</sup> See [7.1](#). Chemistry other than these listed can be used if properties are met.

<sup>B</sup> See [Fig. 1](#).

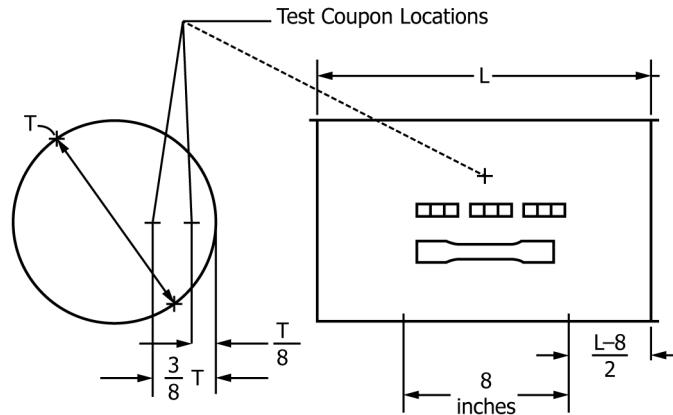


FIG. 1 Test Block Configuration

TABLE 2 Section Range Definition and Test Block Dimensions

Section Range	Section Size, in (mm)		Test Block Dimensions, in (mm) <sup>A</sup>	
	Over	Not Over	T	L
1	3 (76)	5 (127)	4 (102)	8 (203)
2	5 (127)	7 (178)	6 (152)	8 (203)
3	7 (178)	11 (279)	9 (229)	9 (229)
4	11 (279)	15 (381)	13 (330)	13 (330)
5	15 (381)	21 (533)	18 (457)	18 (457)
6	21 (533)	29 (737)	25 (635)	25 (635)
7	29 (737)	37 (940)	33 (813)	33 (813)

<sup>A</sup> See Fig. 1.

TABLE 3 Maximum Gas Content Levels

Section Range	Nitrogen, ppm	Oxygen, ppm	Oxygen Analysis Tolerance, ppm	Oxygen Analysis Limit, ppm <sup>A</sup>
1	110	100	30	130
2	110	100	30	130
3	100	90	27	117
4	100	90	27	117
5	90	80	24	104
6	80	70	21	91
7	70	60	18	78

<sup>A</sup>Specification compliance level is average value of three determinations, see 10.3

6.3 Test block(s) may be heat treated separately from the castings they represent.

6.3.1 Test block(s) shall be heat treated in the same production heat treat equipment, in the same facility, and to the same procedure as the castings to be produced. Test block(s) are excluded from post weld heat treatment (see 12.2.9).

6.3.2 The test block(s) tempering temperature shall be within  $\pm 25^\circ\text{F}$  ( $14^\circ\text{C}$ ) of the casting tempering temperature.

6.4 Heat treatment charts showing time and temperature shall be prepared and held available for inspection by the purchaser.

## 7. Chemical Composition

7.1 Supplier shall select the casting chemistry Grade from Table 1 for the section range, and class specified by the purchaser.

7.1.1 Chemical composition shall conform to Table 4 for Grades II and III.

7.1.2 Grade I designates the use of an alternate chemistry selected by the supplier. Alternate chemistries shall conform to the allowable element ranges and limits given in Table 5.

7.2 A product analysis shall be made for specification conformance. The product analysis shall be performed on a specimen taken from the test block(s) in Section 5 and shall be from the  $\frac{3}{8}T$  location and shall be within the 8 in. (203 mm) midsection as shown in Fig. 1. The supplier shall perform the product analysis in addition to any other process control analysis.

7.3 Retests for conformance are permitted in accordance with Section 13.

## 8. Tension Test

8.1 Tension tests shall be performed on test specimens taken from test block(s) as determined in Section 5.