



SLOVENSKI STANDARD

SIST-TS ENV 12404:2004

01-januar-2004

Durability of wood and wood-based products - Assessment of the effectiveness of a masonry fungicide to prevent growth into wood of Dry Rot *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray - Laboratory method

Durability of wood and wood-based products - Assessment of the effectiveness of a masonry fungicide to prevent growth into wood of Dry Rot *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray - Laboratory method

Dauerhaftigkeit von Holz und Holzprodukten - Bestimmung der Wirksamkeit eines Schutzmittels gegen das Überwachsen von "Echtem Hausschwamm" *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray vom Mauerwerk auf das Holz - Laboratoriumsverfahren

[SIST-TS ENV 12404:2004](https://standards.iteh.ai/catalog/standards/sist/21af07a-a3a2-42e2-87bd-40e20b300124/ENV-12404)

Durabilité du bois et des matériaux dérivés du bois - Evaluation de l'efficacité d'un fongicide de maçonnerie pour empêcher le développement dans le bois de la mэрule *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray - Méthode de laboratoire

Ta slovenski standard je istoveten z: ENV 12404:1997

ICS:

71.100.50 Wood-protecting chemicals

SIST-TS ENV 12404:2004

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST-TS ENV 12404:2004](#)

<https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004>

EUROPEAN PRESTANDARD

ENV 12404

PRÉNORME EUROPÉENNE

EUROPÄISCHE VORNORM

January 1997

ICS 71.100.50

Descriptors: wood, wood preservatives, fungicides, masonry works, durability, effectiveness, bioassay, laboratory tests, pest control

English version

**Durability of wood and wood-based products -
Assessment of the effectiveness of a masonry
fungicide to prevent growth into wood of Dry Rot
Serpula lacrymans (Schumacher ex Fries) S.F.
Gray - Laboratory method**

Durabilité du bois et des matériaux dérivés du bois - Evaluation de l'efficacité d'un fongicide de maçonnerie pour empêcher le développement dans le bois de la mèche Serpula lacrymans (Schumacher ex Fries) S.F. Gray - Méthode de laboratoire

Dauernhaftigkeit von Holz und Holzprodukten - Bestimmung der Wirksamkeit eines Schutzmittels gegen das Überwachsen von "Echtem Hausschwamm" Serpula lacrymans (Schumacher ex Fries) S.F. Gray vom Mauerwerk auf das Holz - Laboratoriumsverfahren

SIST-TS ENV 12404:2004

<https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004>

This European Prestandard (ENV) was approved by CEN on 1996-09-20 as a prospective standard for provisional application. The period of validity of this ENV is limited initially to three years. After two years the members of CEN will be requested to submit their comments, particularly on the question whether the ENV can be converted into an European Standard (EN).

CEN members are required to announce the existence of this ENV in the same way as for an EN and to make the ENV available promptly at national level in an appropriate form. It is permissible to keep conflicting national standards in force (in parallel to the ENV) until the final decision about the possible conversion of the ENV into an EN is reached.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents

Foreword	3
0 Introduction	4
1 Scope	4
2 Normative references	4
3 Definitions	5
4 Principle	5
5 Test materials	5
6 Sample of the preservative	9
7 Mortar test specimens	9
8 Wood test specimens	11
9 Procedure	12
10 Statement of the results	15
11 Test report	15
Annex A (informative) Test fungi	17
Annex B (normative) Methods of sterilization	19
Annex C (informative) Example of a test report	21

SIST-TS ENV 12404:2004

<https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004>

Foreword

This European Prestandard has been prepared by Technical Committee CEN/TC 38 "Durability of wood and wood-based products" the secretariat of which is held by AFNOR.

According to the CEN/CENELEC Internal Regulations, the national standards organisations of the following countries are bound to announce this European Prestandard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST-TS ENV 12404:2004](https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004)

<https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004>

0 Introduction

This European Prestandard describes a laboratory method of test for the assessment of the effectiveness of a masonry fungicide applied to masonry for the prevention of the growth of dry rot, *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray into wood.

This laboratory method enables the determination of the concentration of a preservative within mortar which could prevent the dry rot fungus from growing through a given mortar layer treated with this preservative.

1 Scope

This European Prestandard specifies a method for determining the performance of a preservative, applied to the upper surface of the mortar test specimens, in preventing the growth of dry rot through the treated mortar when exposed to the test fungus

This method is only applicable to masonry fungicides applied as a true solution of the preservative in water or dilute oil in water emulsion. It is not applicable to rods, pastes and other similar preservative types. This method is applicable to preservatives applied to masonry by brushing, spraying and/or injection techniques or mixed into rendering and plastering mortar for masonry.

STANDARD PREVIEW
 (standards.iteh.ai)

2 Normative references

SIST-TS ENV 12404:2004

This European Prestandard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to, or revisions of any of these publications apply to this European Prestandard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 113	Wood preservatives - Test method for determining the protective effectiveness against wood destroying basidiomycetes - Determination of the toxic values
ENV 413-1	Masonry cement - Part 1 : Specification
ENV 459-1	Building lime - Part 1 : Definitions, specifications and conformity criteria
EN 599-1	Durability of wood and wood-based products - Performance of preventive wood preservatives as determined by biological tests - Part 1 : Specification according to hazard class
EN ISO 3696	Water for analytical laboratory use - Specification and test methods

3 Definitions

For the purposes of this European Prestandard, the following definitions apply :

3.1 masonry fungicide

Fungicidal/fungistatic product applied to masonry and other mineral construction materials to prevent the growth of dry rot through or over the treated material.

3.2 performance

Behaviour of the preservative product in terms of its effectiveness in test.

3.3 preservative

Formulated masonry fungicide in the form received from the supplier for the test.

3.4 supplier

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Sponsor of the test.

[SIST-TS ENV 12404:2004](https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004)

4 Principle <https://standards.iteh.ai/catalog/standards/sist/21afc07a-a3a2-42e2-87bd-43de13eb8f20/sist-ts-env-12404-2004>

The preservative to be tested is applied by pipette (or in accordance with the sponsor's instruction) to the upper surface of mortar test specimens. The mortar test specimens are contained in rigid tubes and an untreated wooden sample is placed on top of these mortar test specimens. The bases of the mortar specimens are exposed to dry rot attack for a given time. The assessment of the performance of the test preservative consists of checking the growth of the fungus through the mortar and the evaluation of any attack of the wooden sample contained in the rigid tube.

5 Test materials

5.1 Test fungus

5.1.1 Obligatory test fungus

- *Serpula lacrymans* (Schumacher ex Fries) S.F. Gray, strain BAM Ebw.315.

5.1.2 Optional test fungi

For specific regional uses or conditions, it is also possible to use other strains of dry rot (e.g. *Serpula lacrymans* FPRL 12 C) known to be capable of growing through masonry.

NOTE : Other fungal species can grow through masonry. This method of test could be used to assess the ability of these fungi to grow through mortar specimens.

5.1.3 Maintenance of strains

The strains shall be maintained and treated in accordance with the instructions from their laboratory of origin (see annex A). If a strain shows signs of degeneration, it shall no longer be used and the testing laboratory shall obtain a new standard culture of the strain.

5.2 Products and reagents

5.2.1 Water, distilled or deionized, conform to grade 3 of EN ISO 3696.

5.2.2 Malt - mineral salt - agar culture medium ; consiting :

- malt extract	in concentrated form	12,50 g
	or in powder form	10,00 g
- agar causing no inhibition of growth of fungi		15,00 g
- potassium dihydrogen phosphate (KH ₂ PO ₄)		2,72 g
- calcium sulfate, dihydrate (Ca SO ₄ . 2H ₂ O)		0,38 g
- magnesium sulfate heptahydrate (MgSO ₄ . 7 H ₂ O)		0,62 g
- water (5.2.1) to make up to 1 000 ml.		

Place all the ingredients in a 1 000 ml beaker measure and gently heat , stirring occasionally, until completely dissolved.

Pour 150 ml of the culture medium into each culture vessel (5.3.1).

Close the vessels with screw cap without a hole a quarter of a turn less than full closure and sterilise the closed vessels in the autoclave (5.3.8) at $(121 \pm 2) ^\circ\text{C}$ for 30 min. Let them cool standing upright.

5.2.3 Nutrient solution, a 5 % (m/m) aqueous solution of malt extract.

5.2.4 Equipment for chemical gas or for steam sterilisation or access to a radiation source (see annex B).

5.2.5 Carbon dioxide, compressed gas in cylinders.

5.2.6 Sodium chloride, saturated solution in water.

5.2.7 Portland cement, conforming to ENV 413-1.

5.2.8 Hydrated building lime, conforming to ENV 459-1.

5.2.9 Bricklaying mortar sand ; quartz sand with a particle size equal to or less than 1 mm, washed under running tap water until the water is no longer turbid.

5.3 Apparatus

5.3.1 Culture vessels

Straight sided flat bottom glass culture vessels with an aperture of 50 mm to 60 mm (see figure 3), provided with both screw caps without a hole, used for culturing the test fungus (9.1), and screw caps with a central hole equal in size to the outer diameter of the tube (5.3.2.) plus the thickness of the tubing (5.3.3.) in diameter.

NOTE : The alternative type C.2 of test vessels described in EN 113, have been found to be suitable.

5.3.2 Rigid tubes, which can be sterilized using an autoclave (for example glass, or polyvinylidene fluoride) with an inner diameter of 35 mm to 46 mm and a length of at least 150 mm.

5.3.3 Tubing, with a diameter corresponding to the outer diameter of the rigid tubes (5.3.2.) with a wall thickness of $(1,0 \pm 0,5)$ mm and cut into lengths of $(40,0 \pm 1,0)$ mm capable of being sterilized using an autoclave.

NOTE : Tubing made of rubber has been found to be suitable.

5.3.4 Inert supports of maximum thickness 3 mm and when in use, do not obscure more than 10 % of the mortar surface.

NOTE : Stainless steel washers of overall diameter 25 mm have been found to be suitable. Two supports are required for each test assembly.

5.3.5 Conditioning chamber, well ventilated and controlled at (20 ± 2) °C and (65 ± 5) % relative humidity.

5.3.6 Culture chamber, dark and controlled at (22 ± 1) °C and (70 ± 5) % relative humidity.

5.3.7 Drying oven, capable of being controlled at (45 ± 1) °C.

5.3.8 Autoclave, adjustable to (121 ± 2) °C.

5.3.9 Containers, to prepare the mortar and the preservative solutions, made of a material that does not react with their contents.

5.3.10 Mortar mould apparatus, consisting of a plastic frame for example polyvinyl chloride (PVC) with a height of $(10 \pm 0,5)$ mm, a porous support (for example clay house building bricks, ceramic plates) to absorb the excess water in the fresh mortar and a cloth (for example muslin cloth, cheese cloth) with the same dimensions as the frame to aid demoulding the mortar specimens (see figure 2).

5.3.11 Plastic lath, used to smooth the surface of the mortar after casting in the plastic frame.

5.3.12 Circular tamper with a flat base, a diameter of 3 mm to 5 mm to less than the internal diameter of the rigid tube (5.3.2), and at least 50 mm longer than the rigid tube.

5.3.13 Racks on which to place the treated mortar test specimens an example is shown in figure 1.

dimensions in millimetres

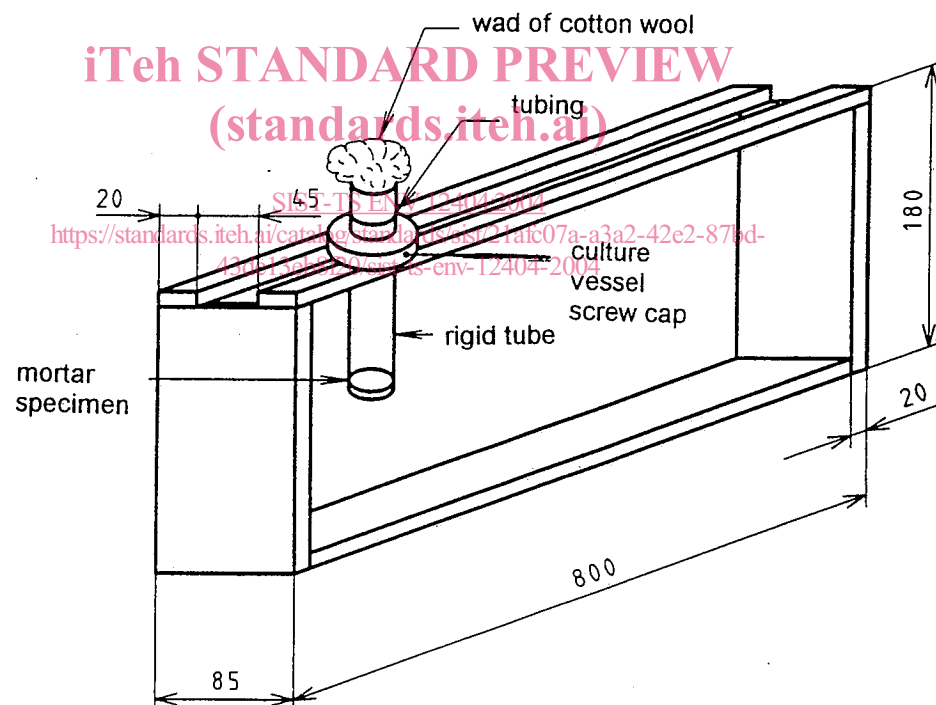


Figure 1 : Example of a rack

5.3.14 Sterile single-use pipettes of $(1,0 \pm 0,1)$ ml content.

5.3.15 Ordinary laboratory equipment, including for example balances accurate to 0,01 g, sealable containers, forceps.

5.3.16 Microbiological safety cabinet, providing protection to the operator and to the work.

6 Sample of the preservative

The sample shall be representative of the product to be tested. It shall be identified as specified in EN 599-1.

7 Mortar test specimens

7.1. Preparation of mortar

Dry a quantity of the quartz sand (5.2.9) in the drying oven (5.3.7) at (45 ± 1) °C. Measure out nine parts by volume of the dried quartz sand and weigh, then place into a container (5.3.9). Add two parts by volume hydrated building lime (5.2.8) and one part by volume Portland cement (5.2.7) and mix thoroughly. Add 16 ml water (5.2.1) per 100 g quartz sand and mix until a homogeneous mortar is obtained.

7.2. Preparation of mortar test specimens

Before casting the fresh mortar in the mortar mould apparatus (5.3.10), soak the porous support in water for 30 min. Place the cloth and plastic frame on the porous support. Cast the fresh mortar in the frame and smooth the surface with the plastic lath (5.3.11). Push the rigid tubes gently in the fresh mortar until the bottom of the tube touches the support. Smooth the surface of the mortar inside the tube using the circular tamper (5.3.12) (see figure 2).

Remove the mortar from around the outside of the tubes and cover the tops of the tubes with a moistened cloth. Store the tubes vertically, with the mortar test specimens at the bottom, in the conditioning chamber (5.3.5) for five weeks.

NOTE : The moistened cloth prevents the mortar from drying out too quickly but can be removed after the first week of conditioning.