



Designation: D8034/D8034M – 16

Standard Test Method for Simulated Service Corrosion Testing of Non-Aqueous Engine Coolants¹

This standard is issued under the fixed designation D8034/D8034M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope

1.1 This test method evaluates the effect of a circulating engine coolant on metal test specimens and automotive cooling system components under controlled, essentially isothermal laboratory conditions.

1.2 This test method specifies test material, cooling system components, type of coolant, and coolant flow conditions that are considered typical of current automotive use.

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard. Some values have only SI units because the inch-pound equivalents are not used in practice.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Section 6.

2. Referenced Documents

2.1 *ASTM Standards:*²

[D1121 Test Method for Reserve Alkalinity of Engine Coolants and Antirusts](#)

[D1176 Practice for Sampling and Preparing Aqueous Solutions of Engine Coolants or Antirusts for Testing Purposes](#)

[D1193 Specification for Reagent Water](#)

[D1287 Test Method for pH of Engine Coolants and Antirusts](#)

[D2570 Test Method for Simulated Service Corrosion Testing of Engine Coolants](#)

¹ This test method is under the jurisdiction of ASTM Committee D15 on Engine Coolants and Related Fluids and is the direct responsibility of Subcommittee D15.22 on Non-Aqueous Coolants.

Current edition approved July 1, 2016. Published September 2016. DOI: 10.1520/D8034_D8034M-16.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[D7935/D7935M Test Method for Corrosion Test for Non-Aqueous Engine Coolants in Glassware](#)

[E203 Test Method for Water Using Volumetric Karl Fischer Titration](#)

2.2 *SAE Standards:*³

[SAE J20e Standard for Coolant System Hoses](#)

2.3 *ASTM Adjuncts:*

Coolant reservoir (1 drawing)⁴

Framework for test equipment (3 drawings and B/M)⁵

3. Summary of Test Method

3.1 An engine coolant is circulated for 1064 h at 96.1°C [205°F] in a flow loop consisting of a metal reservoir, an automotive coolant pump, an automotive radiator, and connecting rubber hoses. Test specimens representative of engine cooling system metals are mounted inside the reservoir, which simulates an engine cylinder block. At the end of the test period, the corrosion-inhibiting properties of the coolant are determined by measuring the mass losses of the test specimens, and by visual examination of the interior surfaces of the components.

4. Significance and Use

4.1 This test method, by a closer approach to engine cooling system conditions, provides better evaluation and selective screening of engine coolants than is possible from glassware testing (Test Method [D7935/D7935M](#)). The improvement is achieved by controlled circulation of the coolant, by the use of automotive cooling system components, and by a greater ratio of metal surface area to coolant volume.

4.2 Although this test method provides improved discrimination, it cannot conclusively predict satisfactory corrosion inhibition and service life. If greater assurance of

³ Available from SAE International (SAE), 400 Commonwealth Dr., Warrendale, PA 15096, <http://www.sae.org>.

⁴ Detail drawings are available from ASTM International Headquarters. Order Adjunct No. [ADJD257001](#). Original adjunct produced in 1982. Reservoirs of cast iron or cast aluminum, made in accordance with these drawings may be obtained from Commercial Machine Service, 1099 Touhy Ave., Elk Grove Village, IL 60007.

⁵ Detail and assembly drawings of a suitable framework and arrangement of components thereon are available from ASTM International Headquarters. Order Adjunct No. [ADJD257002](#). Original adjunct produced in 1982.

satisfactory performance is desired, it should be obtained from full-scale engine tests and from field testing in actual service.

4.3 Significance and interpretation of the test and its limitations are discussed further in **Appendix X1**.

4.4 The substitution of components in the apparatus of Section 5 is permissible if agreed upon by the contracting parties.

5. Apparatus

5.1 *Reservoir*—An assembly drawing of this component⁴ is shown in **Fig. 1**. The material of construction, representing that of the engine cylinder block, shall be SAE G3500 Gray Iron for Automotive Castings.⁶ No air line is to be attached.

⁶ Aluminum or iron may be used if mutually agreed upon between the parties involved.

5.2 *Automotive Components*—These shall be those normally used with a 4-, 6-, or 8-cylinder automobile engine used in current automobiles in the United States, in the 1.6 to 5.0-L [98 to 305-in.] range of piston displacement. General characteristics shall be as follows:

5.2.1 *Radiator*—Aluminum radiator, GM part No. 3093506, or equivalent, may be used subject to mutual agreement of the parties involved. The radiator has a “neck” with a hose nipple and the top of the neck accepts a pressure cap.

5.2.2 *Radiator Pressure Cap*—80 to 100 kPa [12 to 15 psig], GM part No. 6410427. The pressure valve in the cap is removed so as to allow free movement of coolant into and out of the hose nipple. The only purpose of the cap is to be able to open or close the opening at the top of the radiator neck.

5.2.3 *Pressurized Expansion Tank*—A plastic tank approximately 2 L, capable of withstanding a gauge pressure of 136 kPa [20 psig] at 96.1°C [205°F]. The tank has an opening

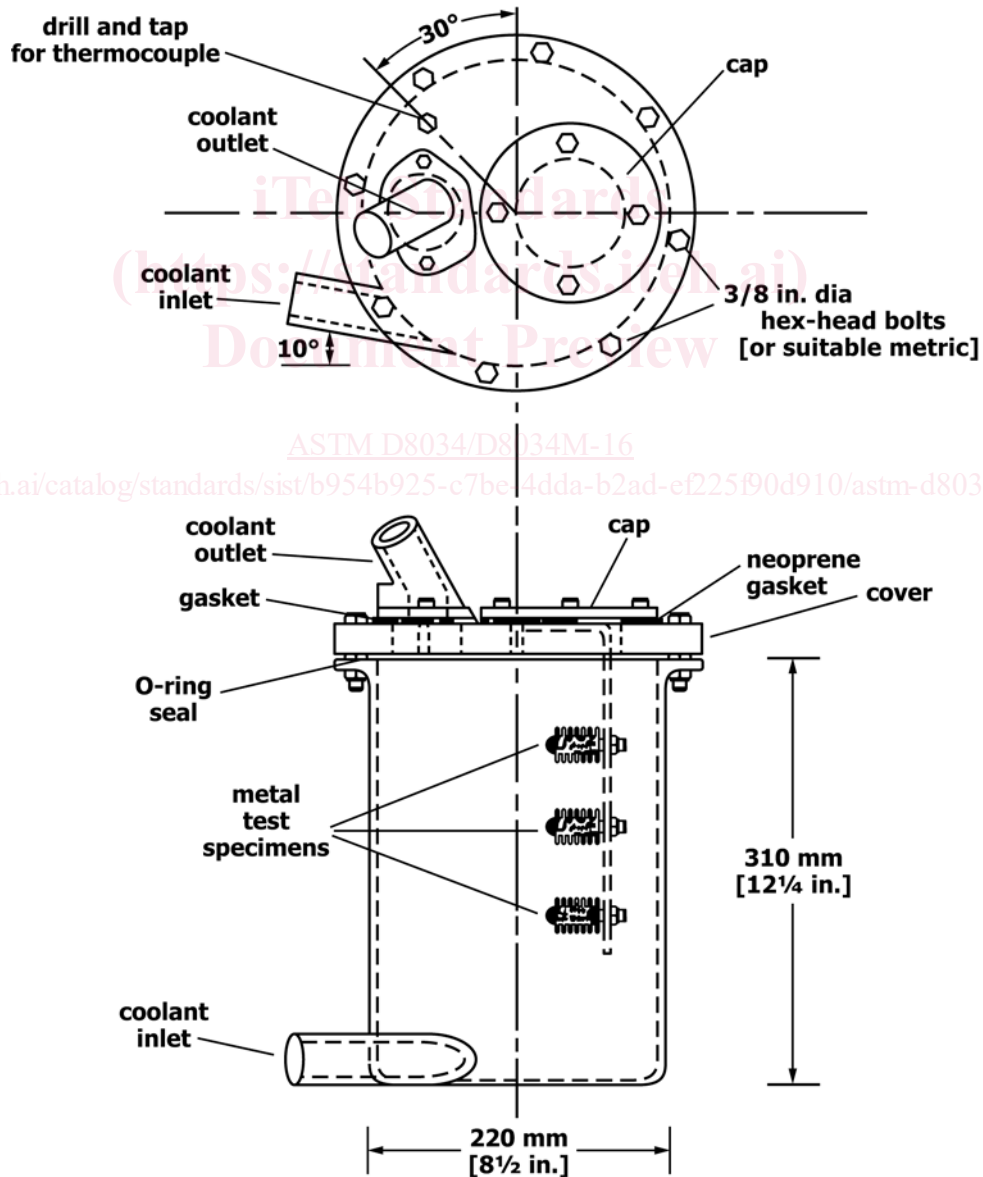


FIG. 1 Reservoir

at the top to accept a pressure cap and a nipple at the bottom to accept a hose. Any other openings are sealed.

5.2.4 *Expansion Tank Pressure Cap*—80 to 100 kPa [12 to 15 psig] to fit the opening at the top of the expansion tank.

5.2.5 *Coolant Pump*—GM part No. 14033483 (aluminum matching front end cover). GM part No. 14033526 (aluminum provides back cover), coolant discharge parts and mounting for pump, or equivalent, may be used subject to mutual agreement of the parties involved.

5.2.6 *Coolant Outlet*—GM part No. 14033198 (aluminum), or equivalent, may be used subject to mutual agreement of the parties involved.

5.2.7 *Hoses*—Reinforced elastomer, meeting the requirements of SAE J20e Type 20R1 Standard Wall Class D-2 requirements; heat-resistant cover; temperature rating: -40 to 125°C [-40 to 257°F].

5.2.8 *Hose Clamps*—Preferably worm-screw type (constant tension may be used).

5.3 *Pipe Fittings*—The preferred material for the fittings required in the hose connections between pump discharge ports and reservoir inlet is malleable cast iron. A satisfactory alternative is steel.

5.4 *Electric Motor*—1.1 kW [1½ hp] or larger, drip-proof or explosion-proof in accordance with local safety regulations.

5.5 *Pulleys and Drive Belt*—Sized to drive the pump at a speed that will produce a flow rate of 1.3 to 1.6 L/s [20 to 25 gal/min] for the General Motors 2.8-L [173-in.³] V-6 engine. The flow rate at operating temperature is determined by a flow measurement device⁷ located between pump discharge and reservoir inlet, as indicated in Fig. 2. The pressure drop between pump discharge and reservoir inlet, measured by the pressure gages shown in Fig. 2, must be maintained when the flow measurement device is removed from the system. This can be done by substituting for the flow measurement device a variable-flow restriction, such as a valve, which can be adjusted to produce the same pressure drop as that measured across the flow measurement device at the specified flow rate.

5.6 *Electric Heater*—About 2000 W, either a hot plate installed under the reservoir, or a circumferential, metal-clad heater band around the reservoir.

5.7 *Thermoregulator*—A suitable temperature regulator shall be used to maintain the coolant temperature between the limits specified by 9.3. The sensing unit of the regulator shall be installed in an opening on the reservoir cover.

⁷ Flow rate indicator, 0.3 to 3.0 L/s [4 to 50 gal/min], of bronze construction is satisfactory.

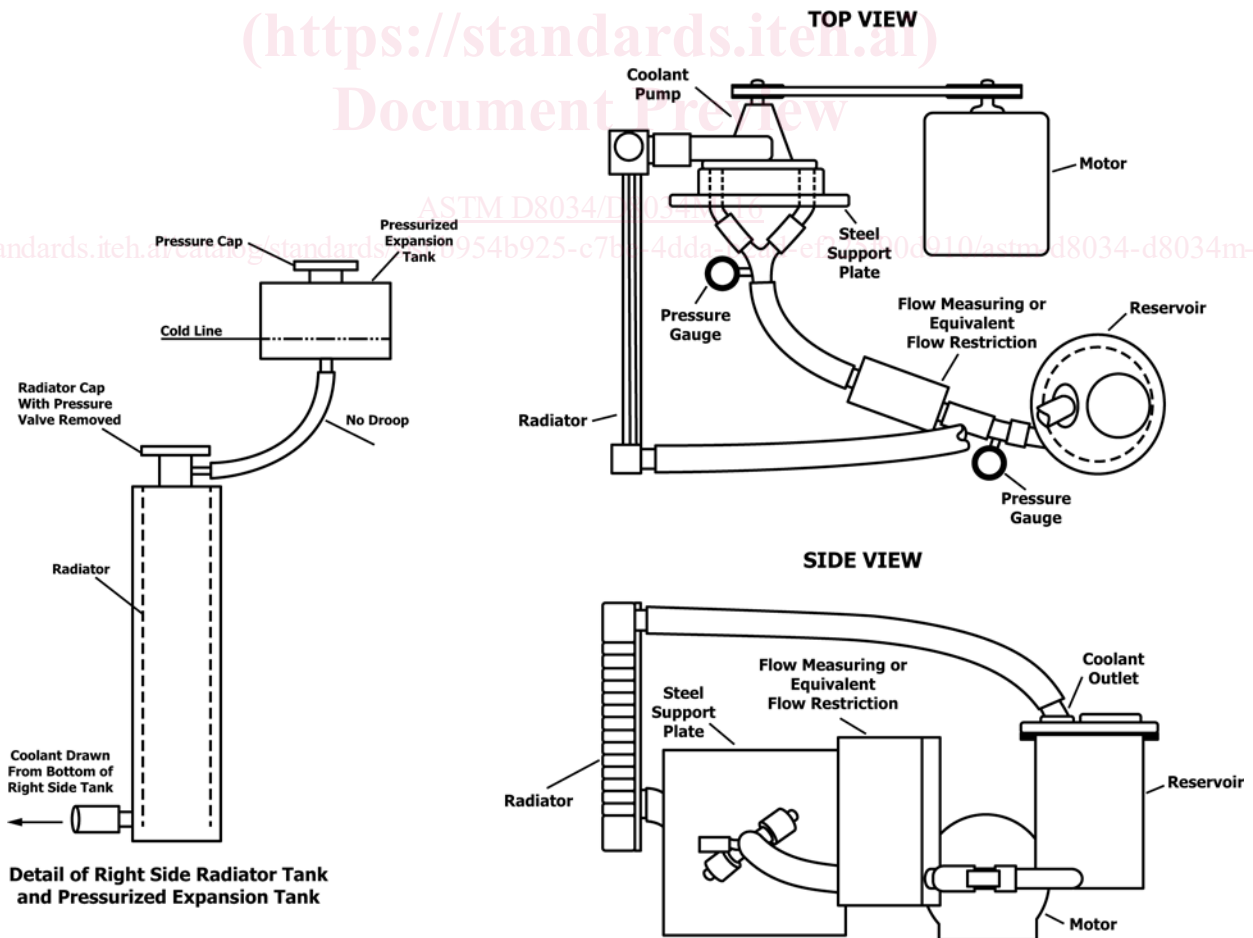


FIG. 2 Assembly of Test Apparatus