



Designation: F 1407 – 99a

Standard Test Method for Resistance of Chemical Protective Clothing Materials to Liquid Permeation—Permeation Cup Method¹

This standard is issued under the fixed designation F 1407; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

INTRODUCTION

Workers involved in the production, use, and transportation of chemicals can be exposed to numerous compounds capable of causing harm upon contact with the human body. The deleterious effects of these chemicals can range from acute trauma, such as dermatitis or burns, to chronic degenerative disease, such as cancer or pulmonary fibrosis. Since engineering controls may not eliminate all possible exposures, attention is often given to reducing the potential for direct skin contact through the use of protective clothing that resists degradation, penetration, and permeation.

This test method provides a simple, gravimetric means for measuring the resistance of clothing materials to permeation by liquid chemicals. Permeation testing by a more sophisticated procedure and penetration testing are addressed by separate methods: Test Methods F 739 and F 903, respectively. Test Methods for measuring the effects of chemicals on the physical properties of rubbers, plastics, and coated fabrics may be found in Test Method D 471, Test Method D 543, and Test Methods D 751, respectively. Guide F 1001 designates 21 chemicals for use with these tests.

1. Scope

1.1 This test method measures the barrier effectiveness of a specimen of protective clothing upon continuous contact with a liquid.

1.1.1 *Procedure A*—For use when a value for the cumulative amount of chemical permeated in 1 h is desired.

1.1.2 *Procedure B*—For use when breakthrough detection time and permeation rate values are desired.

1.2 Although not addressed herein, the effect of the test chemical on the clothing material can be determined by comparing the weight or other physical properties of the specimen before and after the permeation test.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* Specific precautionary statements are given in Section 2.

2. Referenced Documents

2.1 ASTM Standards:

¹ This test method is under the jurisdiction of ASTM Committee F-23 on Protective Clothing and is the direct responsibility of Subcommittee F23.30 on Chemical Resistance.

Current edition approved June 10, 1999. Published August 1999. Originally published as F 1407 – 92. Last previous edition F 1407 – 99.

D 471 Test Method for Rubber Property—Effect of Liquids²

D 543 Practices for Evaluating Resistance of Plastics to Chemical Reagents³

D 751 Test Methods for Coated Fabrics⁴

E 105 Practice for Probability Sampling of Materials⁵

F 739 Test Method for Resistance of Protective Clothing Materials to Permeation by Liquids and Gases Under Conditions of Continuous Contact⁶

F 903 Test Method for Resistance of Materials Used In Protective Clothing to Penetration by Liquids⁶

F 1001 Guide for Selection of Chemicals to Evaluate Protective Clothing Materials⁶

2.2 Federal Standard:

No. 191, Method 4030.2 Measurement of the Thickness of Materials⁷

3. Terminology

3.1 Definitions:

² Annual Book of ASTM Standards, Vol 09.01.

³ Annual Book of ASTM Standards, Vol 08.01.

⁴ Annual Book of ASTM Standards, Vol 09.02.

⁵ Annual Book of ASTM Standards, Vol 14.02.

⁶ Annual Book of ASTM Standards, Vol 11.03.

⁷ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

3.1.1 *cumulative permeation, n*—the total mass of chemical that permeates during a specified time from when the material is first contacted.

3.1.2 *degradation, n*—a deleterious change in one or more properties of a material.

3.1.3 *penetration, n*—in a protective clothing material or item, the process by which a solid, liquid, or gas moves through closures, seams, interstices, and pinholes or other imperfections on a non-molecular level.

3.1.4 *permeation, n*—the process by which a chemical moves through a protective clothing material on a molecular level.

3.1.4.1 *Discussion*—Permeation involves the following: (1) sorption of molecules of the chemical into the contacted (challenge side) surface of the material, (2) diffusion of the sorbed molecules in the material, and (3) desorption of the molecules from the opposite (collection side) surface of the material.

3.1.5 *steady-state permeation rate, n*—a constant rate of permeation that occurs after breakthrough when all forces affecting permeation have reached equilibrium.

3.1.6 *test chemical, n*—the liquid that is used to challenge the protective clothing material specimen.

3.1.6.1 *Discussion*—The liquid can be either one component (that is, a neat liquid) or have several components (that is, a mixture).

3.2 *Definitions of Terms Specific to this Standard:*

3.2.1 *breakthrough detection time, n*—the elapsed time measured from the start of the test to the weighing time immediately preceding the weighing time at which permeation is indicated.

3.2.2 *protective clothing material, n*—any material or combination of materials used in an item of clothing for the purpose of isolating parts of the body from a potential hazard.

3.2.2.1 *Discussion*—In this test method the particular hazard is permeation of a hazardous chemical.

3.2.3 *time interval, n*—the time between weighings of the permeation cup.

4. Summary of Test Method


4.1 The resistance of a protective clothing material to permeation by a test chemical is assessed by measuring the cumulative permeation, breakthrough detection time, and permeation rate through replicate specimens of the material.

4.2 A clothing material specimen is secured over the mouth of a shallow cup that holds the test chemical. The normally outside surface of the material faces the chemical; the other side is open to the atmosphere. See Fig. 1.

4.3 The cup assembly is weighed, inverted, and reweighed at predetermined time intervals to determine the amount of chemical that permeates the material and subsequently evaporates to the atmosphere.

4.4 Based on the amount of chemical lost from the cup during the exposure period, the breakthrough detection time, permeation rate, and cumulative mass of chemical permeating the clothing material are calculated.

4.5 Detection of permeation requires sufficient volatility of the test chemical, and the appropriate combination of analytical balance and weighing interval.

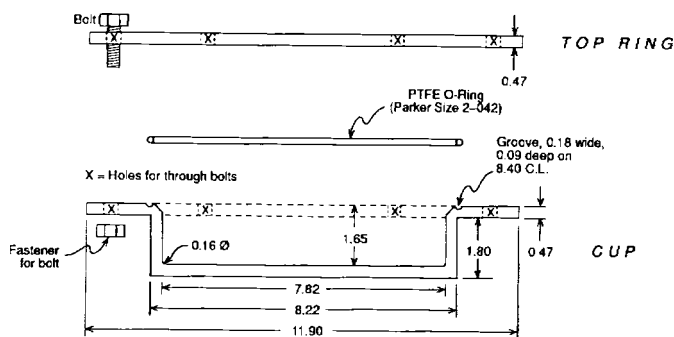

NOTE—Dimensions in centimetres.

FIG. 1 ASTM Permeation Cup

4.5.1 See Section 10 for volatility test.

4.5.2 The likelihood of detecting chemical permeation increases as (1) the sensitivity of the balance is increased and (2) the time between weighings and the length of the test are increased.

4.6 In extreme cases the chemical could so severely degrade the clothing material that the chemical will drip or otherwise flow from the inverted cup.

5. Significance and Use

5.1 This test method establishes a standard procedure for rapidly (in 1 h or less) determining the chemical resistance of specimens of protective clothing materials. This test method can be used to rank materials as to their suitability for use with liquids of known or unknown composition.

5.2 The breakthrough detection time, permeation rate, or cumulative permeation can be used to identify protective clothing materials that are more likely to limit potential exposures to chemicals. Longer breakthrough detection times and lower cumulative amounts permeated and permeation rates are characteristics of materials that are better barriers to the test chemical.

5.3 In general this test method is less sensitive than Test Method F 739 coupled with sensitive analytical procedures. In cases where the chemical of concern is highly toxic and contact of even a very small amount with the skin may be detrimental to health, the permeation cup method is not recommended. Use Test Method F 739.

5.4 Upon permeating the clothing material, the chemical must evaporate in order for a weight loss to occur and permeation to be detected. Consequently, the test method may not be applicable for chemicals having low volatility (that is, vapor pressure). The vapor pressure below which this test method is not applicable has not been determined.

5.4.1 A procedure for assessing volatility is described in Section 10.

5.5 The results of this test method are highly dependent on the test temperature. If the objective is to compare different clothing materials, all tests shall be conducted at the same temperature ($\pm 3^\circ\text{C}$).

6. Apparatus

6.1 *Thickness Gage*, suitable for measuring thickness to the nearest 0.02 mm (0.001 in.), as specified in Fed. Std. No. 191

Method 5030.2, shall be used to determine the thickness of each material specimen tested.

6.2 *Analytical Balance*, readable and reproducible to at least ± 1 mg, is required for measuring the weight loss of the permeation cup. The capacity of the balance should be at least 50 g more than the weight of an empty permeation cup.

6.3 *Permeation Cup*, shown in Fig. 1, is constructed of metal (aluminum is recommended) and is composed of the cup, O-ring (PTFE is recommended), retaining ring (aluminum is recommended), and six fasteners (stainless steel is recommended) for securing the retaining ring to the cup. The circular opening in the retaining ring has a diameter of 7.8 ± 0.05 cm, corresponding to an area of 47.8 cm².

6.3.1 Materials other than aluminum may be used in the construction of the permeation cup. Such materials may be desirable for tests involving chemicals which are incompatible with aluminum (for example, acids).

6.3.2 A chemically resistant coating may be applied to the permeation cup to increase its range of chemical compatibility. Polytetrafluoroethylene (PTFE) has been used successfully as a coating.

6.3.3 In place of the O-ring, either the cup or the retaining ring may be machined such that a seal is achieved when the retaining ring is fastened to the cup.

6.3.4 The volume available for the test liquid is approximately 80 mL, although this amount of chemical is not required nor recommended for performing the test.

6.4 *Torquing Device*, to seal the retaining ring to the cup.

6.5 *Lubricant*, to prevent galling between the fasteners and the cup.

7. Safety Precautions

7.1 Before carrying out this test method, safety precautions recommended for handling any potentially hazardous chemical should be identified and reviewed to provide full protection to all personnel.

7.1.1 For carcinogenic, mutagenic, teratogenic, and other toxic (poisonous) chemicals, the work area should be isolated, well-ventilated, and meticulously clean. Involved personnel should be outfitted with appropriate protective clothing and equipment.

7.1.2 For corrosive or otherwise hazardous chemicals, involved personnel should, as a minimum, be outfitted with protective clothing and equipment.

7.2 Provisions should be made for handling spills of the test chemical or splashes to the eyes or skin.

7.3 Appropriate procedures for the disposal of chemicals should be followed.

7.4 The test should be performed in a laboratory fume hood or outdoors.

NOTE 1—In order to obtain stable readings from the analytical balance, it may be necessary to shield the balance or at least its pan from air currents.

8. Test Specimen

8.1 A protective clothing material specimen may consist of either a single layer or a composite of multiple layers that is representative of an actual protective clothing construction

with all layers arranged in proper order. In each test, the specimen's normally outer surface shall contact the test chemical.

8.1.1 If, in a proposed design of an article of protective clothing, different materials or thicknesses of materials are specified at different locations, specimens from each location shall be tested.

8.1.2 If, in a proposed design of an article of protective clothing, seams are specified, additional specimens containing such seams shall be tested. Care must be taken to ensure that the permeation cup can be properly sealed when specimens of nonuniform thickness are tested.

8.2 Each material specimen shall have a diameter at least 5 mm greater than the outside diameter of the O-ring or sealing mechanism.

8.3 A minimum of three specimens shall be tested for each material, composite, area (in the case of a heterogeneous design), or other condition. Random specimens may be generated as described in Practice E 105.

9. Conditioning

9.1 No conditioning of the test specimen is required.

10. Volatility Test

10.1 Weight loss from the cup is the result of chemical diffusion to and evaporation from the surface of the clothing specimen that faces the air. If the volatility of the chemical is too low, the diffusing chemical will not evaporate from this surface of the specimen as rapidly as it arrives there. In the extreme case, there might be no weight loss even though chemical has diffused through the specimen.

10.2 Evaporation rate increases with temperature.

10.3 Detection of evaporation is dependent on the sensitivity of the balance and the surface area available for evaporation.

10.4 To determine whether the volatility of the test chemical is sufficient for the permeation cup method to be applicable, use the following test:

10.4.1 Place about 20 g of the test chemical into the cup.

10.4.2 Place the cup (uncovered) on the balance, being careful not to spill the chemical.

10.4.3 Record the weight of the cup.

10.4.4 Leave the cup on the balance for the shortest weighing time interval that will be used during the test. The shortest time interval may be the entire duration of the test if cumulative weight loss is the test objective (see Procedure A).

10.4.5 At the end of the period, record the weight of the cup. If the weight loss is >10 mg, then the chemical has sufficient volatility for the permeation cup test to be performed.

10.4.5.1 Because volatility is dependent on temperature and the detection of evaporation is dependent on the sensitivity of the balance, it may be necessary to rerun the volatility test each time any one of these parameters is changed.

10.4.5.2 If no evaporation is detected, consider lengthening the minimum time interval and rerunning the volatility test.

NOTE 2—When the test liquid is a mixture, weight loss during the volatility test may be due to the evaporation of a component that may not permeate the clothing specimen.