



Designation: **E2533—09 E2533 – 16**

Standard Guide for Nondestructive Testing of Polymer Matrix Composites Used in Aerospace Applications¹

This standard is issued under the fixed designation E2533; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 This guide provides information to help engineers select appropriate nondestructive testing (NDT) methods to characterize aerospace polymer matrix composites (PMCs). This guide does not intend to describe every inspection technology. Rather, emphasis is placed on established NDT methods that have been developed into consensus standards and that are currently used by industry. Specific practices and test methods are not described in detail, but are referenced. The referenced NDT practices and test methods have demonstrated utility in quality assurance of PMCs during process design and optimization, process control, after manufacture inspection, in-service inspection, and health monitoring.

1.2 This guide does not specify accept-reject criteria and is not intended to be used as a means for approving composite materials or components for service.

1.3 This guide covers the following established NDT methods as applied to ~~polymeric matrix composites: Acoustic Emission, PMCs: Acoustic Emission (AE, 7), Computed Tomography, Tomography (CT, 8), Leak Testing (LT, 9), Radiographic Testing, Radiography, Radioscopy, Shearography, Computed Radiography, Digital Radiography, and Radioscopy (RT, CR, DR, RTR, 10), Shearography (11), Strain Measurement (contact methods), methods, 12 Thermography, Ultrasound, (-), Thermography (13), Ultrasonic Testing (UT, 14), and Visual NDT Testing (VT, 15).~~

1.4 The value of this guide consists of the narrative descriptions of general procedures and significance and use sections for established NDT methods as applied to ~~polymeric matrix composites, PMCs.~~ Additional information is provided about the use of currently active standard documents (an emphasis is placed on applicable standard guides, practices, and test methods of ASTM Committee E07 on Nondestructive Testing), geometry and size considerations, safety and hazards considerations, and information about physical reference standards.

1.5 To ensure proper use of the referenced standard documents, there are recognized NDT specialists ~~that~~ who are certified in accordance with industry and company NDT specifications. It is recommended that a NDT specialist be a part of any composite component design, quality assurance, in-service maintenance or damage examination.

1.6 This guide summarizes the application of NDT methods to fiber- and fabric-reinforced polymeric matrix composites. The composites of interest are primarily, but not exclusively limited to those containing high modulus (greater than 20 GPa (3×10^6 psi)) fibers. Furthermore, an emphasis is placed on composites with continuous (versus discontinuous) fiber reinforcement.

1.7 This guide is applicable to polymeric matrix composites containing but not limited to bismaleimide, epoxy, phenolic, poly(amide imide), polybenzimidazole, polyester (thermosetting and thermoplastic), poly(ether ether ketone), poly(ether imide), polyimide (thermosetting and thermoplastic), poly(phenylene sulfide), or polysulfone matrices; and alumina, aramid, boron, carbon, glass, quartz, or silicon carbide fibers.

1.8 The composite materials considered herein include uniaxial laminae, cross-ply laminates, angle-ply laminates, and structural sandwich constructions. The composite components made therefrom include filament-wound pressure vessels, flight control surfaces, and various structural composites.

1.9 For current and potential NDT procedures for finding indications of discontinuities in the composite overwrap in filament-wound pressure vessels, also known as composite overwrapped pressure vessels (COPVs), refer to Guide [E2981](#).

¹ This guide is under the jurisdiction of ASTM Committee [E07](#) on Nondestructive Testing and is the direct responsibility of Subcommittee [E07.10](#) on Specialized NDT Methods.

Current edition approved ~~May 15, 2009~~ July 1, 2016. Published ~~July 2009~~ October 2016. Originally approved in 2009. Last previous edition approved as E2533-09. DOI: [10.1520/E2533-09-10.1520/E2533-16](#).

1.10 For a summary of the application of destructive ASTM standard test methods (and other supporting standards) to continuous-fiber reinforced PMCs, refer to Guide [D4762](#).

1.11 The values stated in SI units are to be regarded as the standard. The values given in parentheses are provided for information only.

1.12 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

[C274 Terminology of Structural Sandwich Constructions](#) (Withdrawn 2016)³

[D3878 Terminology for Composite Materials](#)

[D4762 Guide for Testing Polymer Matrix Composite Materials](#)

[E543 Specification for Agencies Performing Nondestructive Testing](#)

[E1316 Terminology for Nondestructive Examinations](#)

[E1742 Practice for Radiographic Examination](#)

[E2981 Guide for Nondestructive Testing of the Composite Overwraps in Filament Wound Pressure Vessels Used in Aerospace Applications](#)

2.2 ASNT Standard:

[SNT-TC-1A Recommended Practice for Personnel Qualification and Certification in Nondestructive Testing](#)⁴

2.3 ASTM Adjuncts:

Curing Press Straining ~~Block~~Block (13 Drawings)⁵

3. Terminology

3.1 *Abbreviations*—The following abbreviations are adopted in this guide: Acoustic Emission (AE), Computed Radiography (CR), Computed Tomography (CT), Digital RadiologyRadiography (DR), Leak Testing (LT), Radiography (RT), Radioscopy (RTR), and Ultrasound (UT).

3.2 *Definitions*—Definitions of terms related to NDT of aerospace composites which appear in Terminology [E1316](#) and Terminology ~~D3676~~[D3878](#) shall apply to the terms used in the guide.

3.3 Definitions of Terms Specific to This Standard:

3.3.1 *aerospace*—any component that will be installed on a system that flies.

3.3.2 *cognizant engineering organization*—the company, government agency, or other authority responsible for the design, or end use, of the system or component for which NDT is required. This, in addition to the design personnel, may include personnel from engineering, materials and process engineering, stress analysis, NDT, or quality groups and other, as appropriate.

3.3.3 *composite material*—see Terminology [D3878](#).

3.3.4 *composite component*—a finished part containing composite material(s) that is in its end use application configuration, and which has undergone processing, fabrication, and assembly to the extent specified by the drawing, purchase order, or contract.

3.3.5 *composite shell*—a multilayer filament-winding that comprises a second shell that reinforces the inner shell. The composite shell consists of continuous fibers, impregnated with a matrix material, wound around the inner shell, and cured in place. The number of layers, fiber orientation, and composite shell thickness may vary from point-to-point.

3.3.6 *disbond*—see Terminology [D3878](#).

3.3.7 *filament wound pressure vessel*—an inner shell over-wrapped with composite layers that form a composite shell. The inner shell or liner may consist of an impervious metallic or nonmetallic material. The vessel may be cylindrical or spherical and will have at least one penetration with valve attachments for introducing and holding pressurized liquids or gases.

3.3.8 *in-service*—refers to composite components that have completed initial fabrication and are in use (or in storage) for their intended function.

3.3.9 *microcrack*—invisible cracks (< 50 to 100 μm size) that are precursors to visible cracks. In angle-ply continuous fiber-reinforced composites, for example, microcracks form preferentially under tensile loading in the matrix in off-axis plies.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

⁴ Available from American Society for Nondestructive Testing, P. O. Box 28518, 1711 Arlington Lane, Columbus, OH 43228-0518.

⁵ Available from ASTM International Headquarters. Order Adjunct No. [ADJf1364](#).

Since most microcracks do not penetrate the reinforcing fibers, microcracks in a cross-plyed tape laminate or in a laminate made from cloth prepreg are usually limited to the thickness of a single ply.

3.3.10 *reference standards*—objects that provide a known, reproducible and repeatable response to a specific stimulus. May be in the form of hardware or software.

3.3.11 *structural sandwich construction*—see Terminology C274.

4. Summary of Guide

4.1 This guide describes and provides references for the practice and utilization of the following established NDT methods as applied to polymeric matrix composites:

4.1.1 Acoustic Emission (Section 7).

4.1.2 Computed Tomography (X-ray Method) (Section 8).

4.1.3 Leak Testing (Section 9).

4.1.4 Radiography, Computed Radiography (CR), Digital Radiology (DR) Radiography, Digital Radiography with Digital Detector Array (DDA) Systems, and Radioscopy (Section 10)

4.1.5 Shearography (Section 11).

4.1.6 Strain Measurement (Strain Gauges) (Section 12).

4.1.7 Infrared Thermography (Non-Contact Methods Using Infrared Camera) (Section 13).

4.1.8 ~~Ultrasound~~ Ultrasonic Testing (Section 14).

4.1.9 Visual ~~NDT~~ Testing (Section 15).

4.2 *NDT Method Selection*—Composite components such as laminates, moldings, and subassemblies may be inspected by simple procedures consisting of dimensional and tolerance measurements, weight and density determinations, cure determinations by hardness measurements, visual ~~examination~~ testing for defects, and tapping for void determinations. If the integrity of the subassembly warrants a more complete inspection, this can be accomplished by using various NDT methods. Nondestructive tests can usually be made rapidly. However, nondestructive testing will, in general, add to component cost and should be used only when warranted on critical applications. Also, the extent of NDT on composite parts depends on whether the part is a primary structure safety of ~~flight~~, flight part, or secondary structure non-safety of ~~flight~~, flight part. The type or class of part is usually defined on the engineering drawing. Some of the ~~defects~~ flaws that can be detected by NDT are given in Table 1.

4.3 Other critical defect characteristics not mentioned in Table 1 that need to be considered when establishing NDE procedures include defect size, defect shape, defect depth, defect orientation, fiber volume fraction, resin rich regions, resin poor regions, cure state, fiber sizing, fiber-matrix bonding, crazing (cracking of amorphous matrix resins due to exposure to stress or the service environment), residual and internal stress, degradation (chemical and physical attack), and impact damage.

ASTM E2533-16

https://standards.iteh.ai/catalog/standards/sist/758c9a82-5ca4-4277-90ad-823b080453b3/astm-e2533-16
TABLE 1 Defects/Flaws Detected By NDT Methods

Defect	Acoustic Emission	Computed Tomography	Leak Testing	Radiology Radiography with DDA; Radiography, CR, Radioscopy	Shearography Measurement	Strain Measurement	Thermography	Ultrasonic Testing	Visual NDT Testing
Contamination		X		X				X	X
Damaged Filaments	X	X		X					
Delamination	X	X			X		X	X	X
Density Variation		X		X			X	X	
Deformation under Load					X	X			
Disbond		X			X		X	X	X
Fiber Debonding	X	X ^A					X	X	
Fiber Misalignment		X		X			X		
Fractures	X	X		X			X	X	X
Inclusions		X		X			X	X	X
Leaks	X		X					X	
Loose or Moving Parts	X								
Microcracks	X	X ^B		X ^{B,C}	X			X	
Moisture		X		X ^{D,E}			X		
Porosity	X	X		X			X	X	
Thickness Variation		X		X ^F	X		X	X	
Undercure								X	
Volumetric Effects		X							
Voids	X	X	X	X			X	X	

^A Can detect after impact (voids).

^B Depends on opening/size of crack.

^C Depends on angle of beam relative to planar defect and opening.

^D Only in central projection (Radiography, CR).

^E Radioscopic mode (Radiology (Radiography with DDA)).

^F For Radiography, applicable to CR and digitized films only.

4.4 *General Facility and Personnel Qualification*—Minimum general requirements for NDT facilities and personnel qualification are given in Practice E543. This practice can be used as a basis to evaluate testing or inspection agencies, or both, and is intended for use for the qualifying or accrediting, or both, of testing or inspection agencies, public or private. ~~Method specific considerations are discussed in the appropriate section (Sections 7 to 15).~~

4.5 *General Equipment and Instrumentation Considerations*—General equipment and ~~instrumentations~~instrumentation considerations are provided in Practice E543. NDT method specific considerations are discussed in the appropriate section of this guide (Sections 7 to 15).

4.6 *Reference Standards*—Physical reference standards simulating target imperfections or discontinuities are used to validate NDT results. The use of physical reference standards also helps to ensure reproducibility and repeatability of measurements. Certified physical reference standards calibrated by accepted government or industrial agencies may be used.

4.7 *Extent of Examination*—Specific applications may require local regions or the entire component to be examined. Examination may be real time or delayed based upon the availability of data. Examination may be direct, or indirect, on site or remote as specified in the contractual agreement or established requirements documents.

4.8 *Timing of Examination*—Examinations shall be performed in accordance with the contractual agreement or established requirements documents, and may be performed during the life cycle of the article under test.

4.9 *Type of Examinations*—Many different NDT system configurations are possible due to the wide range of system components available. It is important for the purchaser of NDT to understand the capability and limitations of the applicable configuration. Selection of the NDT ~~Method~~method and system shall be at the discretion of the testing agency unless specified by the purchaser in a contract or requirements document (that is, engineering drawing, specifications, etc.).

~~4.8.1 Many different NDT system configurations are possible due to the wide range of system components available. It is important for the purchaser of NDT to understand the capability and limitations of the applicable configuration.~~

4.10 A tabular comparison of most of the established NDT methods discussed in the guide is given in Appendix X1 of Practice E543; namely, acoustic emission, leak testing, radiography, strain measurement, thermography (infrared), and ultrasound are covered. The comparison summarizes properties sensed or measured, typical discontinuities detected, representative application, applicable ASTM standards, and advantages and limitations. A similar overview is provided ~~below (in Table 2).~~

5. Significance and Use

5.1 This guide references requirements that are intended to control the quality of NDT data. The purpose of this guide, therefore, is not to establish acceptance criteria and therefore approve composite materials or components for aerospace service.

5.2 Certain ~~Practices~~procedures referenced in the guide are written so they can be specified on the engineering drawing, specification, purchase order, or contract, for example, Practice E1742 (Radiography).

5.3 *Acceptance Criteria*—Determination about whether a composite material or component meets acceptance criteria and is suitable for aerospace service must be made by the cognizant engineering organization. When examinations are performed in accordance with the referenced documents in this guide, the engineering drawing, specification, purchase order, or contract shall indicate the acceptance criteria.

5.3.1 Accept/reject criteria shall consist of a listing of the expected kinds of imperfections and the rejection level for each.

5.3.2 The classification of the articles under test into zones for various accept/reject criteria shall be determined from contractual documents.

5.3.3 *Rejection of Composite Articles*—If the type, size, or quantities of defects are found to be outside the allowable limits specified by the drawing, purchase order, or contract, the composite article shall be separated from acceptable articles, appropriately identified as discrepant, and submitted for material review by the cognizant engineering organization, and dispositioned as (1) acceptable as is, (2) subject to further rework or repair to make the materials or component acceptable, or (3) scrapped when required by contractual documents.

5.3.4 Acceptance criteria and interpretation of result shall be defined in requirements documents prior to performing the examination. Advance agreement should be reached between the purchaser and supplier regarding the interpretation of the results of the examinations. All discontinuities having signals that exceed the rejection level as defined by the process requirements documents shall be rejected unless it is determined from the part drawing that the rejectable discontinuities will not remain in the finished part.

5.4 *Life Cycle Considerations*—The referenced NDT practices and test methods have demonstrated utility in quality assurance of PMCs during the life cycle of the product. The modern NDT paradigm that has evolved and matured over the last ~~twenty~~twenty-five years has been fully demonstrated to provide benefits from the application of NDT during: (a) product and process design and optimization, (b) on-line process control, (c) after manufacture inspection, (d) in-service inspection, and (e) ~~and~~ health monitoring.

5.4.1 In-process NDT can be used for feedback process control since all tests are based upon measurements which do not damage the article under test.

TABLE 2 General Overview of Established NDT Methods

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Acoustic Emission	Global monitoring of composite structures to detect and locate active sources in real time.	Remote and continuous monitoring on an entire composite article in real time is possible. Can also detect growth of active imperfections or discontinuities, and to detect and determine the location of discontinuities and defects that may be inaccessible by other NDT methods.	The part being inspected must be stressed by an external stimulus. With the exception of certain imperfections or discontinuities that AE detects by friction-generated AE (for example, delamination surfaces rubbing), AE-inactive (non-propagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.	The AE technique records transient elastic waves produced by applied stress or resulting stress relaxation of the composite material or component. The mechanical waves are produced as either burst or continuous AE. AE activity, intensity and severity correlated with applied stress yield information on the degradation within the article under test.	Inspection tests and results are unique to each application and should be conducted with expert oversight.
<u>Acoustic Emission</u>	<u>Global monitoring of composite structures to detect and locate active sources in real time.</u>	<u>Remote and continuous monitoring on an entire composite article in real time is possible. Can also detect growth of active imperfections or discontinuities, and detect and determine the location of discontinuities and defects that may be inaccessible by other NDT methods.</u>	<u>The part being inspected must be stressed by an external stimulus. With the exception of certain imperfections or discontinuities that AE detects by friction-generated AE (for example, delamination surfaces rubbing), AE-inactive (non-propagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.</u>	<u>The AE technique records transient elastic waves produced by applied stress or resulting stress relaxation of the composite material or component. The mechanical waves are produced as either burst or continuous AE. AE activity, intensity and severity correlated with applied stress yield information on the degradation within the article under test.</u>	<u>Inspection tests and results are unique to each application and should be conducted with expert oversight.</u>
Computed Tomography	Detects sub-surface volumetric imperfections or discontinuities. Provides quantitative, volumetric analysis of imperfections or discontinuities detectable by other NDT methods. Also suitable for measuring geometric characteristics.	Produces clear cross-sectional image slices of an object. Obtains 3D imperfection or discontinuity data. Extensive image processing capability.	Requires access to all sides of the article under test. Not very applicable to the inspection of large areas, or objects with high (>15) aspect ratios.	A digitized cross-sectional CT-density map (tomogram) of the article under test. Allows full, three dimensional CT-density maps to be obtained for sufficiently small composite parts.	Tooling and/or part-handling fixtures may be required.
<u>Computed Tomography</u>	<u>Detects sub-surface volumetric imperfections or discontinuities. Provides quantitative, volumetric analysis of imperfections or discontinuities detectable by other NDT methods. Also suitable for measuring geometric characteristics.</u>	<u>Produces clear cross-sectional image slices of an object. Obtains 3D imperfection or discontinuity data. Extensive image processing capability.</u>	<u>Requires access to all sides of the article under test. Not very applicable to the inspection of large areas, or objects with high (>15) aspect ratios.</u>	<u>A digitized cross-sectional CT-density map (tomogram) of the article under test. Allows full, three dimensional CT-density maps to be obtained for sufficiently small composite parts.</u>	<u>Tooling and/or part-handling fixtures may be required.</u>

5.4.2 The applicability of NDT methods to evaluate PMC materials and components during their life cycle is summarized in [Tables 3 and 4](#).

TABLE 2 Continued

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Leak Testing	Any composite material or component across which a differential pressure exists and where through-leakage or in-leakage of product, air, water vapor, or other contaminant over the projected service life are of concern.	Less ambiguous than liquid penetrant testing; more sensitive than AE or UT.	Test equipment costs increase as the required leak test sensitivity increases.	Qualitative indications, for example bubbles, or quantitative measurements, for example, detector deflections, that ascertain the presence or location, or concentration or leak rate of a leaking fluid.	Different techniques are available for characterization of large leaks (with rates as high as 10^{-2} Pa m ³ s ⁻¹ (10^{-1} std cm ³ s ⁻¹)) and small leaks (rates less than 10^{-5} Pa m ³ s ⁻¹ (10^{-4} std cm ³ s ⁻¹)).
Leak Testing	Any composite material or component across which a differential pressure exists and where through-leakage or in-leakage of product, air, water vapor, or other contaminant over the projected service life are of concern.	Less ambiguous than liquid penetrant testing; more sensitive than AE or UT.	Test equipment costs increase as the required leak test sensitivity increases.	Qualitative indications, for example bubbles, or quantitative measurements, for example, detector deflections, that ascertain the presence or location, or concentration or leak rate of a leaking fluid.	Different techniques are available for characterization of large leaks (with rates as high as 10^{-2} Pa m ³ s ⁻¹ (10^{-1} std cm ³ s ⁻¹)) and small leaks (rates less than 10^{-5} Pa m ³ s ⁻¹ (10^{-4} std cm ³ s ⁻¹)).
Radiography, Computed Radiology, Radiology with Digital Detector Arrays, Radioscopy	Primarily detects subsurface imperfections or discontinuities such as porosity & inclusions. Planar imperfections or discontinuities are detected if the beam is directed along the imperfection or discontinuity and the unsharpness is less than the imperfection or discontinuity opening/size.	Film and some imaging plates can be cut and placed almost anywhere on the part. Digital images can be processed for additional information and automated defect recognition. In radioscopy, techniques using an image intensifier and DDA can be automated by interfacing with a robot or part manipulator thus allowing the potential for a faster inspection	Requires access to both sides of the article under test. Accessibility may need to be evaluated. Unable to determine depth of imperfections or discontinuities; sometimes possible from digital images after calibration or with additional X-ray exposures from different directions.	Projected area and density variation of subsurface imperfections or discontinuities.	Part may need to be moved to an X-ray lab; Film RT requires film storage and disposal of chemicals which can be expensive. Digital techniques (CR, DDA) are usually faster. Radiation safety. In radioscopy, radiation safety more problematic if a moving source is used, versus movement of part.
Radiography, Computed Radiography, Radiography with Digital Detector Arrays, Radioscopy	Primarily detects subsurface imperfections or discontinuities such as porosity & inclusions. Planar imperfections or discontinuities are detected if the beam is directed along the imperfection or discontinuity and the unsharpness is less than the imperfection or discontinuity opening/size.	Film and some imaging plates can be cut and placed almost anywhere on the part. Digital images can be processed for additional information and automated defect recognition. In radioscopy, techniques using an image intensifier and DDA can be automated by interfacing with a robot or part manipulator thus allowing the potential for a faster inspection	Requires access to both sides of the article under test. Accessibility may need to be evaluated. Unable to determine depth of imperfections or discontinuities; sometimes possible from digital images after calibration or with additional X-ray exposures from different directions.	Projected area and density variation of subsurface imperfections or discontinuities.	Part may need to be moved to an X-ray lab; Film RT requires film storage and disposal of chemicals which can be expensive. Digital techniques (CR, DDA) are usually faster. Radiation safety. In radioscopy, radiation safety more problematic if a moving source is used, versus movement of part.
Shearography	Detects subsurface imperfections or discontinuities or changes in modulus or out-of-plane deformation.	Well suited for high speed, automated inspection in production environments.	Subsurface imperfection or discontinuity must be sufficiently large to cause measurable surface dis deformation under load. Surface condition, especially glossiness, can interfere with accurate shearographic detection; thus requiring the use of surface dulling agents (exception: thermal shearography).	An interference pattern created by subtracting or superimposing images of the article under test taken before and after loading, thus revealing localized strain concentrations.	Additional equipment is required to determine surface derivative slope changes, and thus use the method as a quantitative tool.

5.5 General Geometry and Size Considerations—Part contour, curvature, and surface condition may limit the ability of certain tests to detect imperfections with the desired accuracy.

TABLE 2 *Continued*

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
<u>Shearography</u>	<u>Detects subsurface imperfections or discontinuities or changes in modulus or out-of-plane deformation.</u>	<u>Well suited for high speed, automated inspection in production environments.</u>	<u>Subsurface imperfection or discontinuity must be sufficiently large to cause measurable surface deformation under load. Surface condition, especially glossiness, can interfere with accurate shearographic detection, thus requiring the use of surface dulling agents (exception: thermal shearography).</u>	<u>An interference pattern created by subtracting or superimposing images of the article under test taken before and after loading, thus revealing localized strain concentrations.</u>	<u>Additional equipment is required to determine surface derivative slope changes, and thus uses the method as a quantitative tool.</u>
Strain Measurement	Can be used to measure static and dynamic tensile and compressive strain, as well as shearing, Poisson, bending, and torsional strains.	Relatively inexpensive, and less bulky and better resolution than extensometers (can achieve an overall accuracy of better than $\pm 0.10\%$ strain).	Individual strain gauges cannot be calibrated and are susceptible to unwanted noise and other sources of error such as expansion or contraction of the strain-gauge element, change in the resistivity, and hysteresis and creep caused by imperfect bonding.	The output of a resistance measuring circuit is expressed in millivolts output per volt input.	Depending on desired sensitivity, resistance to drift, insensitivity to temperature variations, or stability of installation, a variety of strain gauges are available (for example, semiconductor wafer sensors, metallic bonded strain gauges, thin-film and diffused semiconductor strain gauges).
Thermography	Detects disbands, delaminations, voids, pits, cracks, inclusions, and occlusions, especially in thin articles under test having low thermal conductivity, low reflectivity/high emissivity surfaces, and in materials which dissipate energy efficiently,	Quick observation of large surfaces and identification of regions that should be examined more carefully.	Composites have temperature limits beyond which irreversible matrix and fiber damage can occur. Imperfection or discontinuity detection depends on orientation of an imperfection or discontinuity relative to the direction of heat flow. In thicker materials, only qualitative indications of imperfections or discontinuities are possible.	The aerial temperature distribution is measured by mapping contours of equal temperature (isotherms), thus yielding a heat emission pattern related to surface and subsurface defects.	Both contact (requires application of a coating) and noncontact methods (relies on detection of infrared blackbody radiation) are available. Thermography is either passive or active, active thermography can be further subdivided into pulse or lock-in techniques.
Ultrasound	<u>Detects sub-surface imperfections or discontinuities. There are two primary techniques; pulse echo for one sided inspections and through transmission for two sided inspections.</u>	<u>Detects sub-surface imperfections or discontinuities including porosity, inclusions, & delaminations.</u>	<u>Requires a relatively flat and smooth surface. Material type can affect inspectability.</u>	<u>Imperfections or discontinuities are directly recorded on amplitude images.</u>	<u>Possible fluid entrapment; Possible fluid absorption into porous materials such as composites. Numerous techniques available including longitudinal, shear or surface waves. Attenuation can be comparatively high in PMCs compared to metallic articles.</u>
<u>Ultrasonic Testing</u>	<u>Detects sub-surface imperfections or discontinuities. There are two primary techniques; pulse echo for one sided inspections and through transmission for two sided inspections.</u>	<u>Detects sub-surface imperfections or discontinuities including porosity, inclusions, and delaminations.</u>	<u>Requires a relatively flat and smooth surface. Material type can affect inspectability.</u>	<u>Imperfections or discontinuities are directly recorded on amplitude images.</u>	<u>Possible fluid entrapment; possible fluid absorption into porous materials such as composites. Numerous techniques available including longitudinal, shear or surface waves. Attenuation can be comparatively high in PMCs compared to metallic articles.</u>

TABLE 2 *Continued*

NDT Method	Applications	Advantages	Limitations	What Is Seen and Reported?	Other Considerations
Visual NDT	Detects disruptions on surfaces being viewed.	Low cost. Detect surface imperfections or discontinuities including delaminations, fiber breakage, impact damage.	Requires direct line of sight.	Imperfections or discontinuities are directly recorded on inspection documentation sometimes photographs.	Can find imperfections or discontinuities on inside diameters if a central conductor can be inserted and satisfactory electrical contact made.
Visual Testing	Detects disruptions on surfaces being viewed.	Low cost. Detect surface imperfections or discontinuities including delaminations, fiber breakage, impact damage.	Requires direct line of sight.	Imperfections or discontinuities are directly recorded on inspection documentation sometimes photographs.	Can find imperfections or discontinuities on inside diameters if a central conductor can be inserted and satisfactory electrical contact made.

TABLE 3 Application Examples of Established NDT Methods During Life Cycle

NDT Method	Application
Acoustic Emission	May be used for quality control of production and fabrication processes (for example, to evaluate adhesive bonding after lay-up winding or curing), for proof-testing of pressure vessels after fabrication, and for periodic in-service and health monitoring inspections prior to failure.
Computed Tomography	May be used as a post-fabrication metrological method to verify engineering tolerances.
Leak Testing	May be used to validate leak tightness following fabrication, and in-service re-qualification of pressure vessels. For example, helium leak detection can be used during composite article fabrication to detect and seal leaks permanently (preferable) or temporarily in such a manner to allow repair at a later time. Similarly, halogen gas leak detection has been used in production examination.
Radiography and Radioscopy	May be used during fabrication inspection to evaluate honeycomb core imperfections or discontinuities such as node bonds, core-to-core splices, core-to-structure splices, porosity, included material as well as verification of structural placement. Water included material bonded structure not for laminates.
Shearography	May be used in quality assurance, material optimization, and manufacturing process control.
Strain Measurement	May be used during proof testing before placement into service, or during periodic re-qualification. Can be destructive depending on the strain thresholds reached during test.
Thermography	May be used to follow imperfection or discontinuity growth during service. If video thermographic equipment is used, systems that are being dynamically tested or used can be examined in real-time.
Ultrasound	Automatic recording systems allow parts to be removed from a processing line when defect severity exceeds established limits. Measurement of the apparent attenuation in composite materials is useful in applications such as comparison of crystallinity and fiber loading in different lots, or the assessment of environmental degradation. Most common method applied for laminar oriented defect detection such as impact damage causing delamination fiber fracturing, included material, and porosity.
Ultrasonic Testing	Automatic recording systems allow parts to be removed from a processing line when defect severity exceeds established limits. Measurement of the apparent attenuation in composite materials is useful in applications such as comparison of crystallinity and fiber loading in different lots, or the assessment of environmental degradation. The most common method is applied for laminar oriented defect detection such as impact damage causing delamination fiber fracturing, included material, and porosity.
Visual NDT	Used primarily for quality inspections of composite materials and components upon receipt (after fabrication and before installation).
Visual Testing	Used primarily for quality inspections of composite materials and components upon receipt (after fabrication and before installation).

5.6 *Reporting*—Reports and records shall be specified by agreement between purchaser and supplier. It is recommended that any NDT report or archival record contain information, when available, about the material type, method of fabrication, manufacturers name, part number, lot, date of lay-up and/or of cure, date and pressure load of previous tests (for pressure vessels), and previous service history (for in-service and failed composite articles). Forwards and backwards compatibility of data, data availability, criticality (length of data retention), specification change, specification revision and date, software and hardware considerations will also govern how reporting is performed.

6. Procedure

6.1 When NDT produces an indication of a material discontinuity, the indication is subject to interpretation as false, nonrelevant, or relevant (Fig. 1). If the indication has been interpreted as relevant, the necessary subsequent evaluation will result in the decision to accept or reject the composite material or component.

TABLE 4 Application of Established NDT Methods During the Life Cycle of Polymeric Matrix Composites

Defect	Product and Process Design and Optimization	On-Line Process Control	After Manufacture Inspection	In-Service Inspection	Health Monitoring
Acoustic Emission	X	X	X	X	X
Computed Tomography			X		
Leak Testing	X	X		X ^A	
Radiography and Radioscopy	X	X	X	X	
Shearography	X	X	X	X	
Strain Measurement			X		X
Thermography			X	X	
Ultrasound	X	X	X	X	X
Ultrasonic Testing	X	X	X	X	X
Visual Testing	X	X	X	X	X

^A Applicable to composites used in storage and distribution of fluids and gases, for example, filament-wound pressure vessels.

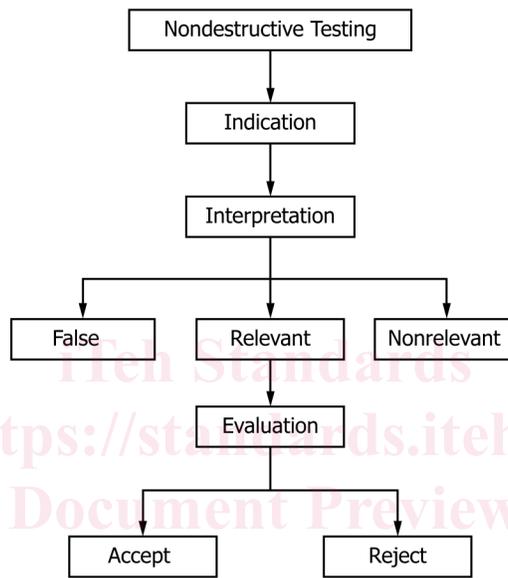


FIG. 1 Consequences of Detecting a Material Discontinuity (Indication) by NDT

<https://standards.iteh.ai/catalog/standards/sist/758ece82-5ca4-4277-90ad-823b080453b3/astm-e2533-16>

7. Acoustic Emission

7.1 Referenced Documents

7.1.1 ASTM Standards:²

- E569 Practice for Acoustic Emission Monitoring of Structures during Controlled Simulation
- E650 Guide for Mounting Piezoelectric Acoustic Emission Sensors
- E750 Practice for Characterizing Acoustic Emission Instrumentation
- E976 Guide for Determining the Reproducibility of Acoustic Emission Sensor Response
- E1067 Practice for Acoustic Emission Examination of Fiberglass Reinforced Plastic Resin (FRP) Tanks/Vessels
- E1118 Practice for Acoustic Emission Examination of Reinforced Thermosetting Resin Pipe (RTRP)
- E1211 Practice for Leak Detection and Location Using Surface-Mounted Acoustic Emission Sensors
- E1419 Test Method for Examination of Seamless, Gas-Filled, Pressure Vessels Using Acoustic Emission
- E1932 Guide for Acoustic Emission Examination of Small Parts
- E2076 Test Method for Examination of Fiberglass Reinforced Plastic Fan Blades Using Acoustic Emission
- E2191 Test Method for Examination of Gas-Filled Filament-Wound Composite Pressure Vessels Using Acoustic Emission

7.1.2 Compressed Gas Association Standard:⁶

Pamphlet C-6.4 Methods for Visual Inspection of AGA NGV2 Containers

7.1.3 Military Handbooks and Standard:⁷

MIL-HDBK-732A Nondestructive Testing Methods of Composite Materials—Acoustic Emission

7.2 General Procedure

⁶ Available from Compressed Gas Association, 1725 Jefferson Davis Hwy., Suite 1004, Arlington, VA 22202-4102.

⁷ Available for Standardization Documents Order Desk, Bldg 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

TABLE 5 Summary of Acoustic Emission

Applications	How It Works	Advantages	Limitations	What Is Seen and Reported?
<p>Global monitoring of composite structures to detect and locate active sources.</p> <p>Evaluation of the structural integrity of finished composite components such as pipes, tubes, tanks, and pressure vessels.</p> <p>Quality control of production and fabrication processes (for example, during lay-up winding, or curing).</p> <p>Proof-testing after fabrication. Also can be used as an alternative method to periodic hydrostatic proof testing.</p> <p>Periodic monitoring of regions of interest or concern during service.</p> <p>Continuous, realtime monitoring of structures (health monitoring).</p> <p>Evaluation of adhesive bonding.</p> <p>Monitoring crack growth prior to failure.</p> <p>Leak detection.</p>	<p>AE Transducers are coupled to the article under test to detect transient elastic stress waves (or AE) produced during application of external stress (mechanical, thermal or pressure). The location of the source is located by triangulation or area (zonal) location methods.</p>	<p>Remote and continuous monitoring of the entire article under test in real time is possible.</p> <p>Can detect growing of active imperfections or discontinuities.</p> <p>Can detect discontinuities and defects that may be inaccessible to other NDT methods, and determine their location.</p> <p>Can be used for proof testing of new or in-service composite material components.</p> <p>Can be used for periodic or continuous (in situ) health monitoring.</p>	<p>The part or article under test must be stressed by an external stimulus.</p> <p>Inactive (nonpropagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.</p> <p>Nonrelevant noise must be filtered out.</p> <p>Transducers must be placed on the part or article under test.</p> <p>Usually requires other NDT methods to characterize detected imperfections or discontinuities.</p>	<p>The AE technique monitors transient elastic stress waves generated by various local processes that occur in a short time period in a structure under stress. The lack of sensed AE signals can be an indication of a composite structure having structural integrity. Alternatively, if increasing AE activity is detected, that can be an indication of damage occurring in the structure and of a potential loss of structural integrity. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring acoustic emission events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).</p>

TABLE 5 Summary of Acoustic Emission

Applications	How It Works	Advantages	Limitations	What Is Seen and Reported?
<p>Global monitoring of composite structures to detect and locate active sources.</p> <p>Evaluation of the structural integrity of finished composite components such as pipes, tubes, tanks, and pressure vessels.</p> <p>Quality control of production and fabrication processes (for example, during lay-up winding, or curing).</p> <p>Proof-testing after fabrication. Also can be used as an alternative method to periodic hydrostatic proof testing.</p> <p>Periodic monitoring of regions of interest or concern during service.</p> <p>Continuous, real-time monitoring of structures (health monitoring).</p> <p>Evaluation of adhesive bonding.</p> <p>Monitoring crack growth prior to failure.</p> <p>Leak detection.</p>	<p>AE transducers are coupled to the article under test to detect transient elastic stress waves (or AE) produced during application of external stress (mechanical, thermal or pressure). The location of the source is located by triangulation or area (zonal) location methods.</p>	<p>Remote and continuous monitoring of the entire article under test in real time is possible.</p> <p>Can detect growing of active imperfections or discontinuities.</p> <p>Can detect discontinuities and defects that may be inaccessible to other NDT methods, and determine their location.</p> <p>Can be used for proof testing of new or in-service composite material components.</p> <p>Can be used for periodic or continuous (in situ) health monitoring.</p>	<p>The part or article under test must be stressed by an external stimulus, such as mechanical load, pressure, or temperature.</p> <p>Inactive (nonpropagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.</p> <p>Nonrelevant noise must be filtered out.</p> <p>Transducers must be placed on the part or article under test.</p> <p>Usually requires other NDT methods to characterize detected imperfections or discontinuities.</p>	<p>The AE technique monitors transient elastic stress waves generated by various local processes that occur in a short time period in a structure under stress. The lack of sensed AE signals can be an indication of a composite structure having structural integrity. Alternatively, if increasing AE activity is detected, that can be an indication of damage occurring in the structure and of a potential loss of structural integrity. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring AE events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).</p>

7.2.1 Specially designed sensors (transducers) are used to detect transient elastic stress waves (AE) in a material produced as a result of applied external stress (tension, compression, torsion, internal pressure, or thermal). The sensors are coupled to the article under test with a suitable couplant (for example, grease), or by means of an epoxy cement or other adhesive. The output from the sensor is amplified and filtered to eliminate unwanted frequencies. The conditioned AE signal is then digitized and

segmented into discrete AE waveform packets through a process of threshold detection. Digital signal processing converts the transient waveform packets into extracted time and frequency features which describe the transient waveform's shape, size and frequency content. In sophisticated approaches, these features are sometimes analyzed together using artificial intelligence, pattern recognition and/or neural network techniques to distinguish true AE sources from noise. When multiple sensors in an array detect the same AE transient, location determination can be accomplished using arrival time analysis (triangulation) techniques. When multiple events are located close together they form an event cluster indicating continuing activity which is indicative of an active growing source. In addition to AE activity generated by growing imperfections or discontinuities, activity can also originate from preexisting imperfections or discontinuities that are not growing (for example, delamination surfaces rubbing together during depressurization of a pressure vessel).

7.3 Significance and Use

7.3.1 ~~AE~~ Acoustic emission is a term used to describe transient elastic stress waves produced in solids as a result of the application of stress. The applied stress may include mechanical forces (tension, compression or torsion), internal pressure, or thermal gradients (can often be accomplished by use of a hot-air gun). The applied stress may be short to long, random, or cyclic. The applied stress may be controlled by the examiner, or may already exist as part of the process. In either case the applied stress is measured along with the AE activity.

7.3.2 The resulting AE stress waves are produced by the rapid release of energy within the material from a localized source. The AE signal from composites often consists of both continuous AE (qualitative description of a sustained signal level produced by rapidly occurring ~~acoustic emission~~ AE events) and burst AE (qualitative description of discrete signals of varying duration that are usually of higher amplitude than continuous AE).

7.3.3 The AE technique records transient elastic stress waves produced by applied stress or resulting stress relaxation of the composite material or component. The stress waves are produced as either burst or continuous AE. AE activity, intensity, and severity correlated with applied stress yield information on the degradation within the article under test. Lack of AE activity is an indication of a sound structure, while more activity is an indication that the structure is degraded. The source is located by triangulation or zone location methods.

7.3.4 In fiber-reinforced composites, AE is generated by release of stored elastic energy during processes such as cracking of the matrix, or fracture or splitting of fibers. Irreversible viscoelastic processes such as crazing of amorphous matrices or plastic (irreversible) deformation of either the matrix or fiber are not detectable under normal measurement conditions with commercial AE systems.

7.3.5 Interfacial sources of AE in fiber-reinforced composites include debonding of the matrix from the fibers, subsequent fiber pull-out (rubbing), and interlaminar debonding.

7.3.6 AE can also be produced by other acoustic sources in the composite not directly related to the matrix or fiber. These sources include leakage of gas or liquid through a crack, orifice, seal break or other opening (for example, in composite-overwrapped pressure vessels); and by movement or loosening of parts (thread failure in assembled composite piping systems, for example).

7.3.7 Most AE signals that are useful in NDT have frequencies that are above the audible range. Ordinarily they are between 20 kHz and 1 MHz, depending on application. The rate and amplitude of acoustic emission signals are noted and correlated to structure or composite article characteristics. Lower and higher frequencies are filtered out to avoid interferences from unwanted sources of noise such as machine vibrations or electrical equipment generated noise.

NOTE 1—When detecting leaks using low frequencies generally lower than 100 kHz, it is possible for the leak to excite mechanical resonances within the article under test that may enhance the acoustic signal used to detect leakage.

7.3.8 In addition to immediate evaluation of the emissions detected during application of the stimulus, a permanent record of the number and location of emitting sources and the relative amount of AE detected from each source provides a basis for comparison with sources detected during the examination and during subsequent stimulation.

7.3.9 The basic functions of an AE monitoring system are to detect, locate, and possibly classify emission sources. Other NDT ~~methods; for example, visual, ultrasonics, methods~~ (for example, visual testing, ultrasonic testing, and eddy current testing) should be used to further evaluate the damage detected in an AE-located region.

NOTE 2—Determining the significance of damage with respect to residual strength or remaining life in a composite sample is presently not possible at the same level as is done with a crack in a metallic sample, for example, where fracture mechanics can be used to determine the significance of damage.

7.3.10 *Felicity Ratio*—The Felicity ratio is the numerical value of the applied stress at which ~~“significant AE”~~ “significant AE” begins divided by the applied stress during the previous cycle. The term ~~“significant AE”~~ “significant AE” has no quantitative definition at this time, and is open to interpretation by the AE practitioner. However, Practice E1067 suggests three guidelines for determining the onset of significant AE:

7.3.10.1 More than 5 bursts during a 10 % increase in applied stress.

7.3.10.2 More than 20 counts during a 10 % increase in applied stress.

7.3.10.3 Increasing AE at constant applied stress.

7.3.11 *Effect of Variables on the Felicity Ratio*—Rate of application and removal of stress, time at peak applied stress, AE system sensitivity, time between load cycles, stress state during loading, AE source mechanism, test environment, and the applied

stress relative to the ultimate strength of the article under test (stress ratio) can all affect the Felicity ratio. Composite materials and components which have rate dependent properties, such as fiber-reinforced composites with plastic matrices, will be affected to a greater extent.

7.3.12 *Kaiser Effect*—If a composite material or component is loaded to a given stress level and then unloaded, usually no AE will be observed upon immediate reloading until the previous load has been exceeded. This is known as the Kaiser effect. The Kaiser effect is said to hold when the Felicity ratio is ≥ 1.0 , and violated when the Felicity ratio is ≤ 1.0 . Therefore, the Kaiser effect holds when no new AE sources are operating, or when there are no reversible AE sources present during subsequent load cycling. Alternatively, when the Kaiser effect is violated, then either or both of these cases have occurred.

7.3.13 *Advantages and Applications*—AE is used to evaluate the structural integrity of composite pipes, tubes, tanks, pressure vessels, and other finished composite parts. Remote and real time surveillance of structures is possible. Inaccessible imperfections or discontinuities can be detected, and their location determined. In addition to imperfection or discontinuity or defect detection, AE can be used to detect leaks (see Practice E1211) and as an alternative to periodic hydrostatic proof testing (see Practice E1419). AE can also be used in quality control evaluation of production processes on a sampled or 100 % inspection basis, in-process examination during a period of applied stress in a fabrication process (for example, lay-up, ~~lay-up~~, winding, pressing, curing, etc.) proof-testing after fabrication, monitoring regions of interest or concern, and re-examination after intervals in service. AE is particularly useful for measuring adhesive bond integrity, and monitoring the growth of a crack in order to give a warning of impending failure. Compared to other common NDT methods, some of the advantages AE are as follows:

7.3.13.1 AE is a global monitoring technique, capable of detecting and locating imperfections or discontinuities a distance away from the sensors without the need to scan the sensors.

7.3.13.2 Can perform continuous monitoring on a complete composite article in real time.

7.3.13.3 Is very sensitive to detecting the growth of active imperfections or discontinuities compared to other NDT techniques; however, usually requires these other methods to characterize these imperfections or discontinuities.

7.3.13.4 Can detect discontinuities and defects that may be inaccessible to other NDT methods.

7.3.13.5 Can be used for proof testing of new or in-service composite pressure vessels.

7.3.14 *Limitations and Interferences*—Some of the disadvantages AE are as follows:

7.3.14.1 The part or article under test must be stressed.

7.3.14.2 With the exception of friction-generated AE (for example, delamination surfaces rubbing together), AE-inactive (nonpropagating) imperfections or discontinuities cannot be detected and structurally insignificant imperfections or discontinuities may produce AE. Therefore, the significance of a detected AE source cannot be assessed unambiguously.

7.3.14.3 Nonrelevant noise must be filtered out.

7.3.14.4 Transducers must be placed on the part or article under test.

7.4 *Use of Referenced Documents*

7.4.1 *Applications:*

7.4.1.1 *Testing of Composite Pipe, Fittings, Tanks and Small Parts:*

(1) Consult Practice E1067 for AE examination of new and in-service fiberglass-reinforced plastic (FRP) tanks and vessels to determine structural integrity. Practice E1067 is limited to tanks and vessels with fiber loadings greater than 15 % by weight, and that are designed to operate at an internal pressure no greater than 0.44 MPa (65 psia) above the static pressure due to the internal contents, or at vacuum service differential pressures levels between 0 and 0.06 MPa (0 and 9 psi).

(2) Consult Practice E1118 for AE examination of new and in-service reinforced thermosetting resin pipe (RTRP) to determine structural integrity. Practice E1118 is limited to lined and unlined pipe, fittings, joints, and piping systems up to and including 0.6 m (24 in.) in diameter, fabricated with fiberglass or carbon fiber reinforcement at fiber loadings greater than 15 % by weight, and is applicable to tests below pressures of 35 MPa absolute (5000 psia).

(3) Consult Guide E1932 for techniques for conducting AE examination on small parts.

7.4.1.2 *Testing of Pressure Vessels:*

(1) Consult ~~CGA Pamphlet C6~~ Compressed Gas Association (CGA) Pamphlet C6.4 for training of personnel conducting AE on pressure vessels.

(2) Consult Practice E569 for guidelines for AE examination and monitoring of structures such as pressure vessels that are stressed by mechanical or thermal means.

(3) Consult Test Method E1419 for guidelines for AE examination of noncryogenic seamless pressure vessels (tubes) of the type used for distribution or storage of industrial gases at pressures greater than encountered in service, as an alternative to periodic hydrostatic proof examination.

(4) Consult Test Method E2076 for measurement of AE during simulation of bending loads.

(5) Consult Test Method E2191 for guidelines for AE of new and in-service filament-wound composite pressure vessels at pressures equal to or greater than what is encountered in service, as an alternative to ~~Compressed Gas Association (CGA)-mandated~~ CGA-mandated three-year visual examination-testing.

NOTE 3—Slow-fill pressurization must proceed at flow rates that do not produce background noise from flow of the pressurizing medium. During proof testing of composite pressure vessels, AE energy from a particular AE event reaching the AE sensor will vary depending on the liquid level in the vessel. Furthermore, AE wave propagation characteristics will be affected by whether the vessel has a metal or rubber liner, for example.

NOTE 4—In general, fast-fill pressurization can be used if hold periods are used. In this case, AE data are recorded only during hold periods. While this hold period technique may be suitable for characterization of glass or aramid-reinforced composites, the same technique may not be suitable for carbon and graphite-reinforced composites.

NOTE 5—For composites made by certain fabrication routes (for example, filament-winding), the composite surface may not be as smooth as is normally the case. To have a relatively uniform coupling from article to article, the best amount of couplant to use may have to be determined experimentally by applying different amounts and ascertaining which amount gives the most uniform AE signal from pencil lead breaks, for example.

7.4.1.3 *Leak Testing*—Consult Practice E1211 for description of a passive method utilizing (1) surface-mounted AE sensors, or (2) sensors attached by means of acoustic waveguides that allow detection and location of the steady state source of gas and liquid leaking out of a pressurized system. Application examples to illustrate the use of AE to detect leaks in a relief valve, ball valve, and a transfer line are also given in Appendix X1 of Practice E1211.

7.4.2 *AE Acoustic Emission Equipment and Instrumentation:*

7.4.2.1 Consult Guide E650 for guidelines about mounting piezoelectric AE sensors.

7.4.2.2 Consult Practice E750 for required tests and measurements on AE equipment components and units, determination of instrument bandwidth, frequency response, gain, noise level, threshold level, dynamic range, signal overload point, dead time, and counter accuracy.

7.4.2.3 Consult Appendix X1 of Practice E750 for a discussion of AE electronic components or units including sensors, preamplifiers, filters, power amplifiers, line drive amplifiers, threshold and counting instrumentation, and signal cables. Also, most modern AE systems use computers to control collection, storage, display, and data analysis. Features of computer-based system include waveform collection as well as a wide selection of measurement parameters relating to the AE signal.

NOTE 6—AE signals from composites are typically of high amplitude, so sensor sensitivity is usually not an issue except in cases where the sensors are spaced too far apart or if the threshold is set too high. The use of non-resonant wideband (versus resonant sensors) is useful in detecting signals over a range of frequencies and is relevant when wave propagation theory is being used to understand the AE signal and to more accurately locate the AE source. Otherwise, both resonant and non-resonant sensors can be used as long as they are spaced appropriately on the composite material or component to maintain sensitivity to AE sources distributed across the article under test. Typical AE signals generated in composites are of higher amplitude near the source compared to the AE generated in metals. In contrast to metals, the higher frequencies in the AE signal are absorbed by the composite after relatively short propagation distances. Thus, often lower frequency sensors and filters are used for composites. Due to the fact that AE sources typically occur throughout composites when they are stressed, it is not unusual for AE sources to occur in the composite directly below sensors. This situation can result in a signal of very high amplitude. Such cases are not likely in metal samples as it is unlikely that a sensor will be directly over a crack tip. Due to the amplitude of the composite AE signals, in some cases it is necessary to use a preamplifier with only 20 dB of gain to avoid saturation of the signal. Most commercial AE preamplifiers saturate at 10 to 20 volts peak-to-peak voltage output. For these reasons, preamplifiers with a 20 to 40 dB gain, 10 volt peak-to-peak output voltage, and an 80–100 dB dynamic range are common.

7.4.2.4 Consult Appendix X2 of Practice E750 for an explanation of suggested measurements (for example, preamplifier input impedance, wave shaping, gain measurements).

7.4.2.5 Consult Appendix X3 of Practice E750 about the electrical circuit configuration for measurement of input impedance.

7.4.2.6 Consult Appendix X4 of Practice E750 about acoustic and electrical noise sources.

7.4.2.7 Consult Appendix A1 of Practice E1067 or Appendix A1 of Practice E1118 for instrumentation performance requirements for sensors, signal cable, couplant, preamplifier, filters, power-signal cable, main amplifier, and the main processor.

7.4.2.8 Consult Appendix A2 of Practice E1067 or Appendix A1 of Practice E1118 for baseline calibration of AE equipment, including low-amplitude threshold, high-amplitude threshold, and count value instrument calibration.

7.4.2.9 Consult Appendix A3 of Practice E1067 for sensor placement guidelines for atmospheric, atmospheric-pressure, and atmospheric-vacuum tanks.

7.4.2.10 Consult Appendix A1 of Practice E1419 for specifications for AE components; namely, sensors, signal cable, couplant, preamplifier, power-signal cable, power supply, and signal processor used as an alternative to periodic hydrostatic proof testing.

7.4.2.11 Consult MIL-HDBK-732A for useful applications details on test installation and test fixturing (Section 4); couplants and waveguides (Section 5); type, location, and application of sensors (Section 6); cables (Section 7); preamplifiers (Section 8); secondary amplifiers and filters (Section 9); time domains of burst and continuous AE (Section 10); AE sources in composites (Sections 11–14); wave propagation characteristics (Section 15); source or imperfection or discontinuity location (Section 16); Kaiser effect/Felicity ratio (Section 17); factors of significance in AE data (Section 18); in-situ calibration of AE tests (Section 19); extraneous AE (Section 20); and control checks on AE testing (Section 21).

7.4.3 *AE Acoustic Emission Calibration and Standardization:*

7.4.3.1 Consult Practice E569 for performing a location sensitivity check (includes a zone location sensitivity check and a source location algorithm sensitivity check).

7.4.3.2 Consult Guide E976 for performing sensor checks or system performance checks using a pencil lead break.

7.5 *Geometric and Size Considerations*

7.5.1 Wave propagation signal losses are more considerable in composites than in metals. There are three primary causes of amplitude attenuation of AE signals in composites during AE wave propagation: (1) geometric spreading (same as in metals, but metals don't do not typically have sensors directly over AE sources; thus this can be quite large), (2) material absorption (much higher in composites than in metals), and iii) dispersion (different propagation velocities of different frequencies). In addition, depending on the geometry and size of the article under test, reflections can also alter the expected attenuation.

7.5.2 In larger composite articles, ~~there may be significant manpower economies using sensors with integrated preamplifiers to~~ may preclude the need to connect separate preamplifiers.

7.5.3 Since composites are in general anisotropic and of varying thicknesses, the signal (wave) propagation losses may vary in different parts of the composite.

7.6 Safety and Hazards

7.6.1 *Pressure Vessels*—When conducting AE examination of pressure vessels and ~~RTRP; reinforced thermosetting resin pipe (RTRP)~~, the following safety guidelines shall be followed:

7.6.1.1 When testing in-service pressure vessels, all safety requirements unique to the examination location shall be ~~met~~. Protective clothing and equipment that is normally used in the area in which the examination is conducted shall be worn.

7.6.1.2 The test temperature should not be below the ductile-brittle transition temperature (β -relaxation) of the semicrystalline matrix, or above the glass-rubber transition temperature (α -relaxation or glass transition temperature) of the amorphous matrix used in the pressure vessel composite overwrap.

7.6.1.3 Precautions shall be taken to protect against the consequences of catastrophic failure when pressure testing, for example, flying debris and impact of escaping liquid. Pressurizing under pneumatic conditions is not recommended except when normal service loads include either a superposed gas pressure or gas pressure only. Care shall be taken to avoid overstressing the lower section of the vessel when liquid test loads are used to simulate operating gas pressures.

7.6.1.4 Pneumatic testing is extremely dangerous. Special safety precautions shall be taken when pneumatic testing is ~~required; for example, safety valves, etc.~~ required (safety valves, etc).

7.7 Calibration and Standardization

7.7.1 ~~Periodic~~ Periodically perform calibration and verification of pressure transducers, AE sensors, preamplifiers (if applicable), signal processors (particularly the signal processor time reference), and AE electronic waveform ~~generator~~ generator. Equipment should be adjusted so that it conforms to equipment manufacturer's specifications. Instruments used for calibration must have current accuracy certification that is traceable to the National Institute for Standards and Technology (NIST) or equivalent national or regional (multinational) standards institute.

7.7.2 Routine electronic checks must be performed any time there is concern about signal processor performance. A waveform generator should be used in making evaluations.

7.7.3 Routine sensor checks must be performed at any time there is concern about sensor performance. Peak amplitude and electronic noise level should be recorded. Sensors can be stimulated by a mechanical device such as a pencil lead break or piezoelectric transducer. The object is to induce stress waves into the article under test at a specified distance from each sensor. Induced stress waves stimulate a sensor in a manner similar to emission from an imperfection or discontinuity. Sensors ~~that should be replaced if they have peak amplitudes or electronic noise greater than the average, or sensitivities lower than the average of the group of sensors being used~~ should be replaced.

7.7.4 A system verification must be performed immediately before and immediately after each examination. A system verification uses a mechanical device such as a pencil lead break or piezoelectric transducer to induce stress waves into the article under test. The induced stress wave must be nondestructive. System verification validates the sensitivity of each system channel (including the couplant and test fixture).

7.8 Physical Reference Standards

7.8.1 Not Applicable.

8. Computed Tomography (X-ray Method)

8.1 Referenced Documents

8.1.1 ASTM Standards:²

E1441 Guide for Computed Tomography (CT) Imaging

E1570 Practice for Computed Tomographic (CT) Examination

~~E1670~~E1672 Guide for Computed Tomography (CT) System Selection

E1695 Test Method for Measurement of Computed Tomography (CT) System Performance

E1935 Test Method for Calibrating and Measuring CT Density

8.2 General Procedure

8.2.1 ~~CT~~ Computer Tomography is a radiographic inspection method that uses a computer to reconstruct an image of a cross-sectional plane (slice) through the article under test. CT consists of making penetrating radiation measurements of the X-ray opacity of the article under test along many paths to compute a cross-sectional CT-mass attenuation density image called a tomogram. The resulting cross-sectional image is a quantitative map of the linear X-ray mass attenuation coefficient at each point in the plane. The linear mass attenuation coefficient characterizes the local instantaneous rate at which X-rays are attenuated during the scan, by scatter or absorption, from the incident radiation as it propagates through the article under test.

8.3 Significance and Use

8.3.1 CT is usually performed after two dimensional X-ray imaging.