



Designation: D6712 – 17

# Standard Specification for Ultra-High-Molecular-Weight Polyethylene (UHMW-PE) Solid Plastic Shapes<sup>1</sup>

This standard is issued under the fixed designation D6712; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## INTRODUCTION

This specification is intended to be a means of defining Ultra-High-Molecular-Weight<sup>2</sup> Polyethylene (UHMW-PE) solid plastic shapes for commercial use.

### 1. Scope\*

1.1 This specification covers requirements and test methods for the material and properties of solid plastic shapes manufactured from UHMW-PE.

1.2 The properties included in this specification are those required for the compositions covered and are derived from molded samples or fabricated from sheet, rod and profiles. Requirements necessary to identify particular characteristics important to specialized applications are described by using the classification system given in Section 4.

1.3 This specification allows for the use of recycled plastics (as defined in Guide D5033).

1.4 The values are stated in SI units and are to be regarded as the standard in all property tables. For reference purposes, English units are also included in Table S-UHMW-PE and Table A and are not necessarily exact equivalents.

1.5 The following precautionary caveat pertains only to the test method portions of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory requirements prior to use.*

NOTE 1—There is no known ISO equivalent to this standard.

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials.

Current edition approved March 1, 2017. Published March 2017. Originally approved in 2001. Last previous edition approved in 2009 as D6712 - 01(2009). DOI: 10.1520/D6712-17.

<sup>2</sup> Ultra High Molecular Weight refers to a polyethylene resin meeting the requirements of Specification D4020.

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>3</sup>

D618 Practice for Conditioning Plastics for Testing

D638 Test Method for Tensile Properties of Plastics

D883 Terminology Relating to Plastics

D1600 Terminology for Abbreviated Terms Relating to Plastics

D3892 Practice for Packaging/Packing of Plastics

D4000 Classification System for Specifying Plastic Materials

D4020 Specification for Ultra-High-Molecular-Weight Polyethylene Molding and Extrusion Materials

D5033 Guide for Development of ASTM Standards Relating to Recycling and Use of Recycled Plastics (Withdrawn 2007)<sup>4</sup>

#### 2.2 ISO Standard:

ISO 11542-2 Ultra-High-Molecular Weight Polyethylene (PE-UHMW) Moulding Materials—Part 2: Preparation of Test Specimens and Determination of Properties

### 3. Terminology

#### 3.1 Definitions:

3.1.1 For definitions of other technical terms pertaining to plastics used in this specification, see Terminology D883, D1600, or Guide D5033.

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *additive, n*—any material added to the polymer such as processing aids, stabilizers, and colorants.

<sup>3</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>4</sup> The last approved version of this historical standard is referenced on www.astm.org.

\*A Summary of Changes section appears at the end of this standard

3.2.2 *recycled-plastic shape, n*—a product made from up to 100 % post-consumer material.

3.2.3 *regrind (plastic), n*—a product or scrap such as edge trim that have been reclaimed by shredding and granulating for use in-house.

3.2.4 *rod, n*—an extruded solid cylindrical shape with a minimum diameter of 1/16 in.

3.2.5 *sheet, n*—flat stock greater than 10 mils thickness.

3.2.6 *solid plastic shape, n*—a product of various geometries made up of UHMW-PE, such as sheet, rod, and so forth.

TABLE S-UHMW-PE Physical Property Requirements for Ultra High Molecular Weight Polyethylene Solid Plastic Shapes

Description	Type	Class	Description	Grade	Applicable Specification Callout	Description	Izod impact, Test Method for D4020, min, kJ/m <sup>2</sup> (ft-lbs/in. <sup>2</sup> )	Elongational Stress, Test Method for ISO 11542-2 (Annex 1), min, Mpa	Tensile Elongation, Test Method for D638, % at break, min
UHMW-PE	01	1	unfilled	1	ASTM D4020	General purpose	37 (18)	>0.20	200
				2	see Table A	Recycled	...	...	...
		0	as specified	1	see Table A	General purpose	...	...	...
				2	see Table A	Recycled	...	...	...
Other UHMW-PE	00	0	...	0	...	...	...	...	

4. Classification and Material

4.1 Product shape and size as defined in the applicable purchase order.

4.2 This standard covers product as listed in Table S-UHMW-PE.

4.2.1 The type of a UHMW-PE product is categorized by grade and type depending on resin and additives present, as defined in Table S-UHMW-PE.

4.2.2 Every type of UHMW-PE solid plastic shape are categorized into one of two grades as follows:

4.2.2.1 *Grade 1: General Purpose (Virgin) UHMW-PE*—UHMW-PE solid plastic shapes are made using only 100 % virgin UHMW polyethylene resin which meets the requirements of Specification D4020. Virgin product shall not contain materials of unknown origin or composition.

NOTE 2—If appropriate, the resin can contain additives, such as processing aids, stabilizers, and colorants.

4.2.2.2 *Grade 2: Recycled/Regrind UHMW-PE*—UHMW-PE solid plastic shapes are made using any amount up to 100 percent of recycled, or regrind UHMW-PE plastic, or both.

TABLE A Additional Requirements for UHMW-PE Solid Plastic Shapes

NOTE 1—The values listed in Table A are minimum values.

Designation Order Number	Property	0	1	9
1	Izod impact, Test Method for D4020, min kJ/m <sup>2</sup> (ft-lbs/in. <sup>2</sup> )	Unspecified	30 (14)	Specify value
2	Elongational stress, Test Method for ISO 11542-2 (Annex 1), min, MPa	Unspecified	>0.20	Specify value
3	Elongation at break, Test Method for D638, %, min	Unspecified	200	Specify value
4	To be determined	...	...	...

4.3 Property Tables:

4.3.1 Table S-UHMW-PE is to be used to describe UHMW-PE solid plastic shapes.

4.3.2 To facilitate the incorporation of future UHMW-PE or special UHMW-PE formulations not covered by Table A, the

“as specified” category (00) for grade is shown on the table with the basic properties to be obtained from Table S-UHMW-PE, as they apply.

4.4 Callout Designation—A one-line system shall be used to specify polyethylene materials covered by this specification.

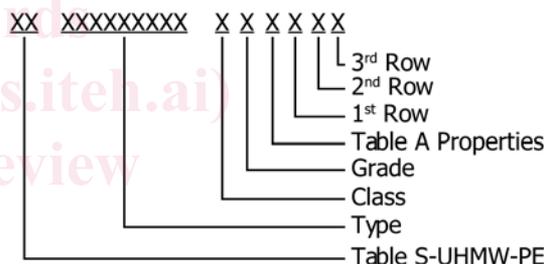


FIG. 1 Callout Designation Layout

4.4.1 The system uses pre-defined cells to refer to specific aspects of this specification as illustrated below in Examples 1–3:

4.4.2 *Example 1*—Product made from virgin Type UHMW-PE resin.

CELL CALLOUT: S-UHMW-PE0111

where:

S-UHMW-PE01 = product made from general purpose resin per Table S-UHMW-PE,  
 1 = unfilled class, and  
 1 = general purpose.

4.4.3 *Example 2*—Product made using virgin resin, or regrind/recycled UHMW-PE, or both, with an Izod impact 30 kJ/m<sup>2</sup> (14 ft-lb/m<sup>2</sup>), minimum and elongation at break more than 200 %.

CELL CALLOUT: S-UHMW-PE0112A101

where:

S-UHMW-PE01 = product made from general purpose resin per Table S-UHMW-PE,  
 1 = unfilled class,