



Designation: D5276 – 98 (Reapproved 2017)

## Standard Test Method for Drop Test of Loaded Containers by Free Fall<sup>1</sup>

This standard is issued under the fixed designation D5276; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers procedures for the drop testing of loaded boxes, cylindrical containers, and bags and sacks by the free-fall method.

1.2 For containers not exceeding 110 lb (50 kg), this test method fulfills the requirements of ISO Standards 2206:1987 and 2248:1985. These ISO standards may describe procedures that do not meet the requirements for this test method.

1.3 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>2</sup>

**D585 Practice for Sampling and Accepting a Single Lot of Paper, Paperboard, Fiberboard, and Related Product (Withdrawn 2010)**<sup>3</sup>

**D644 Test Method for Moisture Content of Paper and Paperboard by Oven Drying (Withdrawn 2010)**<sup>3</sup>

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D10 on Packaging and is the direct responsibility of Subcommittee D10.21 on Shipping Containers and Systems - Application of Performance Test Methods.

Current edition approved Sept. 1, 2017. Published September 2017. Originally approved in 1992. Last previous edition approved in 2009 as D5276 – 98 (2009). DOI: 10.1520/D5276-98R17.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The last approved version of this historical standard is referenced on [www.astm.org](http://www.astm.org).

**D880 Test Method for Impact Testing for Shipping Containers and Systems**

**D996 Terminology of Packaging and Distribution Environments**

**D2463 Test Method for Drop Impact Resistance of Blow-Molded Thermoplastic Containers**

**D4003 Test Methods for Programmable Horizontal Impact Test for Shipping Containers and Systems**

**D4169 Practice for Performance Testing of Shipping Containers and Systems**

**D4332 Practice for Conditioning Containers, Packages, or Packaging Components for Testing**

**D6055 Test Methods for Mechanical Handling of Unitized Loads and Large Shipping Cases and Crates**

**D6179 Test Methods for Rough Handling of Unitized Loads and Large Shipping Cases and Crates**

**E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process**

**E680 Test Method for Drop Weight Impact Sensitivity of Solid-Phase Hazardous Materials**

#### 2.2 ISO Standards:<sup>4</sup>

**ISO 2206 Packaging—Complete Filled Transport Packages, Identification of Parts When Testing**

**ISO 2248 Packaging—Complete Filled Transport Packages, Vertical Impact Test by Dropping**

#### 2.3 Code of Federal Regulations:

**Title 49 —Transportation (49 CFR)**<sup>5</sup>

### 3. Terminology

3.1 *Definitions*—General terms for packaging and distribution environments are found in Terminology **D996**.

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *cylinder*—for the purposes of this test method, a cylinder includes substantially cylindrical containers such as barrels, drums, kegs, and pails (fiber, metal, plastic, or wood, or combinations thereof).

<sup>4</sup> Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

<sup>5</sup> Available from U.S. Government Printing Office Superintendent of Documents, 732 N. Capitol St., NW, Mail Stop: SDE, Washington, DC 20401, <http://www.access.gpo.gov>.

3.2.2 *member*—a face, corner, or edge of a rectangular container; a chime, end, or sidewall of a cylindrical container; or a face, edge, corner, or butt of a bag or sack.

#### 4. Significance and Use

4.1 This test method is intended for use in evaluating the capability of a container to withstand the sudden shock resulting from a free fall, or to evaluate the capability of a container and its inner packing to protect its contents during the sudden shock resulting from a free fall. This test method may also be used to compare the performance of different package designs. This test method may also permit observation of the progressive failure of a container and the damage to its contents.

4.2 This test method is particularly suitable for containers that are normally handled manually during some part of their distribution cycle. Containers of such bulk or mass that they cannot be handled manually may be tested more satisfactorily in accordance with Test Method **D880**, Test Methods **D6055**, Test Methods **D6179**, or Test Methods **D4003**. See Practice **D4169** for additional guidance.

#### 5. Apparatus

5.1 *Free-Fall Drop Test Equipment*, conforming to the following requirements:

5.1.1 It shall permit the container to be placed, prior to release, in a position that will ensure correct orientation, within 2 degrees upon impact, for flat-face drops or flat drops on ends or sidewalls of cylindrical containers, and within 5° upon impact for other drops, such as edge drops and corner drops for rectangular containers, bags, and sacks and diagonal drops on chimes on cylindrical containers.

5.1.2 It shall permit accurate control of the drop from specified heights.

5.1.3 It shall utilize lifting devices that will not damage the test container.

5.1.4 It shall provide a release mechanism that does not impart vertical, rotational, or sideways forces to the test container. If drop leaves are used, the apparatus shall provide a spring or other mechanism so that the leaves do not interfere with a free, unobstructed fall.

5.1.5 It shall provide an impact surface, horizontal and flat, massive enough to be immovable and rigid enough to be nondeformable under the test conditions.

5.1.5.1 The impact surface shall be of concrete, stone, or steel. If the dropping surface is a steel plate, it must be at least ½ in. (13 mm) thick and must be anchored firmly to the mass.

NOTE 1—Grout (a thin mortar used to fill crevices) is recommended over the entire surface of the mass below the plate to ensure positive contact.

5.1.5.2 The impact surface shall be integral with a mass at least 50 times that of the heaviest container to be tested. Neither the depth nor width of the mass shall be less than half the length.

5.1.5.3 For drop testing of containers not exceeding 110 lb (50 kg), the impact surface shall be flat, such that no two points on the surface differ in level by more than 5/64 in. (2 mm).

5.1.5.4 The impact surface shall be rigid, such that it will not be deformed by more than 0.0039 in. (0.1 mm) when an area of 0.1550 in.<sup>2</sup> (100 mm<sup>2</sup>) is loaded statically with 22.05 lb (10 kg) anywhere on the surface.

5.1.5.5 The impact surface shall be sufficiently large to ensure that the containers being tested fall entirely upon the surface.

5.1.6 A rupture hazard may be used for determining the rupture resistance of cylindrical containers or bags. Unless otherwise specified, the rupture hazard should consist of a 4 by 4-in. (102 by 102-mm) timber, of oak or other wood of equivalent hardness, approximately 4 ft (1.2 m) long, having the edges rounded to a radius of not more than ¼ in. (6.35 mm).

5.1.6.1 For testing of 49 CFR—DOT 21C fiber drums, a 2 by 6-in. (51 by 152-mm) timber, with a 6-in. (152-mm) vertical dimension, shall be used. The drum shall be dropped at right angles to the timber. The drop height shall be measured from the top of the timber.

5.1.7 For very large containers, it may be necessary to use a hoist, sling, and tripping devices, or a solenoid-operated drop test mechanism and suspension devices, such as those described in **Appendix XI**.

5.1.8 *Conditioning Apparatus*—Adequate facilities shall be provided for conditioning test specimens at the proper humidity and temperature prior to testing, in accordance with the specification covering the containers to be tested.

5.1.8.1 *Conditioning*—Depending on the purpose of the tests, containers may be conditioned prior to the drop test by either a different physical test, water immersion, exposure to water spray, or exposure to standard or other fixed air temperature or humidity conditions. It is recommended that special atmospheres for conditioning be selected from those given in Practice **D4332**. Unless otherwise specified, fiber-board or paperboard containers shall be conditioned in accordance with the preconditioning and standard conditioning atmospheres specified in Practice **D4332** (see also Practice **D4169** for additional guidance).

5.1.8.2 Where the moisture content of fiberboard containers is determined, it should be determined in accordance with Test Method **D644**.

#### 6. Sampling

6.1 The test specimens and number of samples shall be chosen to permit an adequate determination of representative performance. Practice **E122** is recommended. Unless otherwise specified, Practice **D585** shall be used for acceptance testing of fiberboard containers.

6.2 In the absence of any sampling plan, at least three representative specimens should be selected for performance evaluation.

#### 7. Test Specimens

7.1 When the protective capability of a container is to be evaluated, it is preferable to pack the container with the actual contents for which it was designed (**Note 2**). When the capability of a container to withstand rough handling is to be evaluated, pack the container with either the actual contents or

a load simulating the contents. Regardless of which procedure is used, close the container in the same manner that will be used in preparing it for shipment.

**NOTE 2**—Where the use of actual contents is not feasible because of excessive cost or danger, a dummy load simulating the contents with respect to dimensions, center of gravity, moment of inertia, density, flow characteristics, etc. may be used. Accelerometers or other indicating mechanisms may be installed.

7.2 Close and seal the container in the normal manner. Dry and age sufficiently so that any adhesive, protective coatings, sealing tape, and so forth will have reached their final normal condition.

## 8. Procedure

8.1 Identify members as specified in **Annex A1**, by marking, at a minimum, Faces 1, 2, and 5 of rectangular containers; Positions 1, 3, 5, and 7 of cylindrical containers; and Faces 1, 4, and 5 of sacks and bags.

8.2 Unless otherwise specified, establish failure criteria prior to the commencement of testing. (See Practice **D4169**, Acceptance Criteria.)

8.3 Test containers that have been conditioned in the conditioned atmosphere or immediately upon removal from that atmosphere.

8.4 Conduct drop test procedures by dropping the container on either one member or several different members in a prescribed sequence (cyclical testing).

8.4.1 When the container is to be dropped flat on a face, position it so that, upon impact, there is no more than a 2° angle between the plane of this face and the impact surface.

8.4.2 When a rectangular container or bag is to be dropped on an edge, position it so that, upon impact, this edge makes no more than a 2° angle with the impact surface, and the plane containing this edge and the center of gravity of the container makes no more than a 5° angle with the vertical.

8.4.3 When a rectangular container or bag is to be dropped on a corner, position it so that, upon impact, the line containing this corner and the center of gravity of the container makes no more than a 5° angle with the vertical.

8.4.4 When a cylindrical container is to be dropped on either a chime or a circumferential edge, position it so that, upon impact, a plane containing this edge and the center of gravity of the container makes no more than a 5° angle with the vertical plane perpendicular to the drop surface.

8.4.5 When determining the rupture resistance of cylindrical containers or bags, place a rupture hazard (see **5.1.6**) on the target surface, and position it so that, unless otherwise specified, the center of the cylinder sidewall or face edge or butt of the bag impacts across the hazard.

8.4.6 Before each drop of a bag or sack, distribute the contents uniformly throughout the bag or sack.

8.5 *Height of Drop*—Determine the height of the drop by measuring from the bottom surface, edge, or corner of the container to the impact surface.

## 9. Report

9.1 Report the following information:

9.1.1 Reference to this test method, including a statement to the effect that all tests were conducted in full compliance with the requirements of this test method, or noting any variations and their details.

9.1.2 Dimensions of the container under testing; complete structural specifications; kinds of materials; description and specifications for blocking and cushioning, if used; spacing, size, and type of fasteners; method of closing and strapping, if any; drying and aging time, if any; and tare and gross masses.

9.1.3 Description of the contents of the container under testing and, if not tested with the actual contents intended to be shipped, description of these actual contents.

9.1.4 Number of specimens tested per sample.

9.1.5 Method of conditioning the container, if any; moisture content of the wood, plywood, or fiberboard, if determined; and results of any supplementary tests of the materials from which the container is made.

9.1.6 Description of apparatus and special instrumentation, if used.

9.1.7 Whether a 4 by 4 timber was used as a hazard. Where a hazard other than that specified in **5.1.6** is used, a description of the hazard used.

9.1.8 Details of the failure criteria used.

9.1.9 Member(s) tested (see **Annex A1**).

9.1.10 Description of the prescribed test sequence, if used.

9.1.11 Drop height(s).

9.1.12 Size of the increment, if a variable height drop test procedure is used.

9.1.13 Number of drops (at each incremental height, if applicable).

9.1.14 Detailed record of the test results for each container, including damage to the container and contents, together with any other observation that may assist in interpreting the results correctly or aid in improving the design of the container or method of packaging, blocking, or bracing.

9.1.15 Where a mean failure height is determined by dropping, a statement of this mean and the estimated standard deviation and level of confidence.

9.1.16 Name and address of the testing agency, date, and signature of a responsible representative of the testing agency.

## 10. Precision and Bias

10.1 *Precision*<sup>6</sup>:

10.1.1 A precision statement is not applicable when the drop test is conducted at a specified drop height to determine conformance with established acceptance criteria.

10.1.2 When the drop test is conducted to determine the drop height to failure, the observed precision is a combination of the precision of the test method (including apparatus, operators, etc.) and the precision of the packaged product being tested. Experience has shown that the observed precision is highly dependent on the particular packaged item being tested. Research Report D10–1004 describes an interlaboratory test program of three packaged items, establishing drop heights to failure. The mean drop heights to failure for the three types of

<sup>6</sup> Supporting data are available from ASTM Headquarters. Request RR:D10-1004.

packaging were 39, 42.6, and 47.7 in. (991, 1083, and 1212 mm). The repeatability (within laboratory) standard deviation ranged from 3 to 10 in. (75 to 250 mm) for these items. The pooled reproducibility (between laboratory) standard deviation was 2.25 in. (57 mm). The research report suggests that tests of some items produce data that are not distributed normally; log-normal, Weibull, or other distributions may be applicable.

10.2 *Bias*—No justifiable statement can be made on the bias of this test method since a true value cannot be established by an accepted referee test method.

11. Keywords

11.1 bags; boxes; cylindrical containers; drop test; drums; free fall; packaging; sacks

ANNEXES

(Mandatory Information)

A1. IDENTIFICATION OF MEMBERS

A1.1 *Rectangular Containers*—The procedure for identification of the members (faces, edges, and corners) of rectangular containers shall be as follows (see Fig. A1.1):

A1.1.1 Facing one end of the box with the manufacturer’s joint, where applicable, on the observer’s right, designate the top of the box as 1, the right side as 2, the bottom as 3, the left side as 4, the near end as 5, and the far end as 6.

A1.1.2 Identify the edges by the numbers of the two faces that form that edge; for example, 1-2 identifies the edge formed by the top and right side, and 2-5 identifies the edge formed by the right side and near end. (The 2-5 edge is the edge having a vertical manufacturer’s joint, and the 2-3 edge is the edge having a horizontal manufacturer’s joint in fiberboard containers.)

A1.1.3 Identify the corners by the numbers of the three faces that meet to form that corner; for example, 1-2-6 identifies the corner at which the top, right side, and far end meet.

A1.2 *Cylindrical Containers*—The procedure for identification of the members (tops, bottoms, sidewalls, and chimes) of cylindrical containers shall be as follows (see Fig. A1.2):

A1.2.1 The ends of two perpendicular diameters on the upper surface of the cylindrical container shall be designated as 1, 3, 5, and 7; and the other ends of lines parallel to the cylinder axis passing through these points respectively shall be designated as 2, 4, 6, and 8. If the package has one or more side seam joints, one of the joints should occupy the position of 5-6.

A1.2.2 Identify diagonal drops on chimes by designating the drop point by number, that is, drop on 1. Where it is desirable to drop on a midpoint between two locations on the chime, such a point can be designated using two numbers, that is, drop on 1-3.

A1.2.3 Identify flat drops on sidewalls by designating the drop point by two numbers, that is, drop on 3-4. Where it is desirable to drop on a midpoint between two locations on the sidewall, such a point can be designated using four numbers, that is, drop on 1-3-2-4.

A1.2.4 Identify flat drops on ends using the four numbers of that end, that is, 1-3-5-7 or 2-4-6-8.

A1.3 *Sacks and Bags*—The procedure for identification of the members (faces, sides, tops, and bottoms) of bags and sacks shall be as follows (see Fig. A1.3):

A1.3.1 Facing the front of the bag with the top up, designate the front of the bag as 1, the right side edge as 2, the rear side

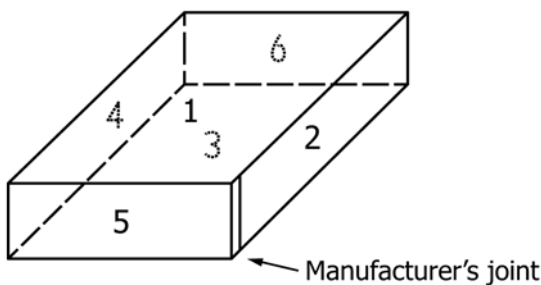


FIG. A1.1 Members of Rectangular Containers

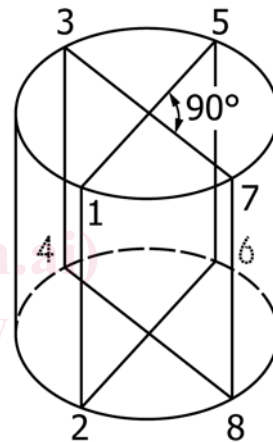


FIG. A1.2 Members of Cylindrical Containers