



Standard Test Methods and Practices for Emulsified Asphalts¹

This standard is issued under the fixed designation D244; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 These test methods and practices, given under the headings titled Composition, Consistency, Stability, and Examination of Residue, cover the examination of asphalt emulsions composed principally of a semisolid or liquid asphaltic base, water, and an emulsifying agent. The test methods cover the following tests and practices:

Test	Sections
Composition:	
Water Content	4 – 10
Residue and Oil Distillate by Distillation	See Test Method D6997
Residue by Evaporation	See Test Method D6934
Particle Charge of Cationic Emulsified Asphalts	See Practice D7402
Consistency:	
Viscosity (Saybolt Furol)	See Test Method D7496
Stability:	
Demulsibility	See Test Method D6936
Settlement	See Test Method D6930
Cement Mixing	See Test Method D6935
Sieve Test	See Test Method D6933
Aggregate Coating	See Practice D6998
Miscibility with Water	See Practice D6999
Freezing	See Practice D6929
Coating Ability and Water Resistance	11 – 18
Storage Stability of Asphalt Emulsion	See Test Method D6930
Examination of Residue	19 – 26
Identification Test for Rapid Setting Cationic Emulsified Asphalt	27 – 34
Identification of Cationic Slow Set Emulsions	See Practice D7402
Field Coating Test on Emulsified Asphalts	35 – 40

Emulsified Asphalt/Job Aggregate Coating Test	41 – 46
Density of Emulsified Asphalt	See Test Method D6937
Residue by Low-Temperature Vacuum Distillation	See Test Method D7403

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

- 2.1 *ASTM Standards*:²
- C778 Specification for Standard Sand
 - D5 Test Method for Penetration of Bituminous Materials
 - D70 Test Method for Density of Semi-Solid Bituminous Materials (Pycnometer Method)
 - D86 Test Method for Distillation of Petroleum Products and Liquid Fuels at Atmospheric Pressure
 - D113 Test Method for Ductility of Bituminous Materials (Withdrawn 2016)³
 - D128 Test Methods for Analysis of Lubricating Grease
 - D139 Test Method for Float Test for Bituminous Materials
 - D140 Practice for Sampling Bituminous Materials
 - D977 Specification for Emulsified Asphalt
 - D2042 Test Method for Solubility of Asphalt Materials in Trichloroethylene

¹ These test methods and practices are under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and are the direct responsibility of Subcommittee D04.42 on Emulsified Asphalt Test.

Current edition approved Oct. 1, 2017. Published October 2017. Originally approved in 1926. Last previous edition approved in 2009 as D244 – 09. DOI: 10.1520/D0244-09R17.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

[D2397 Specification for Cationic Emulsified Asphalt](#)
[D3289 Test Method for Density of Semi-Solid and Solid Asphalt Materials \(Nickel Crucible Method\)](#)
[D6929 Practice to Evaluate the Effect of Freezing on Emulsified Asphalts](#)
[D6930 Test Method for Settlement and Storage Stability of Emulsified Asphalts](#)
[D6933 Test Method for Oversized Particles in Emulsified Asphalts \(Sieve Test\)](#)
[D6934 Test Method for Residue by Evaporation of Emulsified Asphalt](#)
[D6935 Test Method for Determining Cement Mixing of Emulsified Asphalt](#)
[D6936 Test Method for Determining Demulsibility of Emulsified Asphalt](#)
[D6937 Test Method for Determining Density of Emulsified Asphalt](#)
[D6997 Test Method for Distillation of Emulsified Asphalt](#)
[D6998 Practice for Evaluating Aggregate Coating using Emulsified Asphalts](#)

[D6999 Practice for Miscibility of Emulsified Asphalts](#)
[D7402 Practice for Identifying Cationic Emulsified Asphalts](#)
[D7403 Test Method for Determination of Residue of Emulsified Asphalt by Low Temperature Vacuum Distillation](#)
[D7496 Test Method for Viscosity of Emulsified Asphalt by Saybolt Furol Viscometer](#)
[E1 Specification for ASTM Liquid-in-Glass Thermometers](#)
[E11 Specification for Woven Wire Test Sieve Cloth and Test Sieves](#)
[E145 Specification for Gravity-Convection and Forced-Ventilation Ovens](#)

3. Sample Conditioning for Testing

3.1 All emulsions with viscosity requirements of 50 °C should be heated to 50 ± 3 °C in the original sample container in a 71 °C water bath or oven. The container should be vented to relieve pressure. After the sample reaches 50 ± 3 °C, stir the sample to achieve homogeneity.

COMPOSITION

WATER CONTENT

4. Scope

4.1 This test method covers the procedure for determining the water content of an emulsified asphalt by reflux distillation using a water trap.

5. Significance and Use

5.1 This test method measures the amount of water present in the emulsified asphalt, as distinguished from either bitumen or petroleum solvent.

6. Apparatus and Materials

6.1 *Metal Still*—The metal still (Fig. 1(a)) shall be a vertical cylindrical vessel, preferably of copper, having a faced flange at the top to which the head is tightly attached by means of a clamp. The head shall be made of metal, preferably brass or copper, and shall be provided with a tubulation 25.4 mm (1 in.) in inside diameter.

6.2 *Glass Still*—The glass still (Fig. 1(b)) shall be a short-neck, round-bottom flask, made of well-annealed glass, and having an approximate capacity of 500 mL.

6.3 *Heat Source*—The heat source used with the metal still shall be a ring gas burner of 100-mm (4-in.) inside diameter or an electric mantle heater. The heat source for the glass still shall be either an ordinary gas burner or an electric heater.

6.4 *Condenser*—The condenser shall be a water-cooled reflux glass-tube type, having a jacket not less than 400 mm in length, with an inner tube 9.5 to 12.7 mm in outside diameter. The end of the condenser shall be ground to an angle of $30 \pm 5^\circ$ from the vertical axis of the condenser.

6.5 *Trap*—The trap shall be made of annealed glass constructed in accordance with Fig. 1(c) and shall be graduated in 0.10-mL divisions from 0 to 2 mL, and in 0.20-mL divisions from 2 to 25 mL.

6.6 *Solvent*—Xylol or other petroleum distillate conforming to the following distillation requirements: 98 % distills between 120 and 250 °C. This distillation shall be conducted in accordance with Test Method D86.

7. Sample

7.1 Obtain a representative sample of the material for test using standard procedures as specified in Practice D140.


NOTE 1—The difficulties in obtaining representative samples for this determination are unusually great, so that the importance of sampling cannot be too strongly emphasized.

8. Procedure

8.1 When the material to be tested contains less than 25 % water, place 100 ± 0.1 g of sample in the still. When the material contains more than 25 % water, use a 50 ± 0.1 -g sample. Thoroughly mix the sample to be tested with 200 mL of solvent by swirling, taking proper care to avoid any loss of material.

8.2 Connect the still, trap, and condenser by means of tight-fitting corks as shown in Fig. 1(a) or (b). Adjust the end of the condenser in the trap to a position which will allow the end to be submerged to a depth of not more than 1 mm below the surface of the liquid in the trap after distillation conditions have been established. When using the metal still, insert a heavy paper gasket, moistened with the solvent, between the lid and flange before attaching the clamp.

8.3 When the ring burner is used with the metal still, place it about 76.2 mm above the bottom of the still at the beginning of the distillation, and gradually lower it as the distillation proceeds. Regulate the heat so that the condensate falls from the end of the condenser at a rate of from 2 to 5 drops per second. Continue the distillation at the specified rate until no water is visible on any part of the apparatus and a constant volume of water is obtained in the trap. Remove any persistent

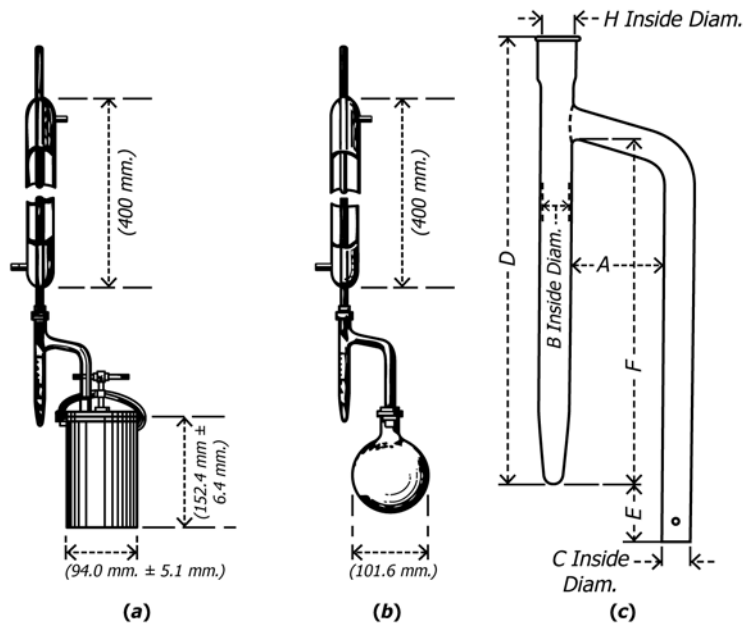

A = 45 to 55 mm
 B = 14 to 16 mm
 C = 12 to 16 mm
 D = 235 to 255 mm

E = 25 to 38 mm
 F = 186 to 194 mm
 H = 18 to 19 mm

FIG. 1 Apparatus for Determining Water Content

ring of condensed water in the condenser tube by increasing the rate of distillation for a few minutes.

9. Calculation and Report

9.1 Calculate the water content as follows:

$$\text{Water content, \%} = (A/B) \times 100 \quad (1)$$

where:

- A = volume of water in trap, mL, and
- B = original weight of sample, g.

9.2 Report the result as "... water weight percent, ASTM D244."

10. Precision and Bias

10.1 The following criteria should be used for judging the acceptability of results (95 % probability):

10.1.1 Duplicate results by the same operator should not be considered suspect unless they differ by more than the following amount:

Water Content, weight % 30 to 50	Repeatability, weight % 0.8
-------------------------------------	--------------------------------

10.1.2 The results submitted by each of two laboratories should not be considered suspect unless they differ by more than the following amount:

Water Content, weight % 30 to 50	Reproducibility, weight % 2.0
-------------------------------------	----------------------------------

COATING ABILITY AND WATER RESISTANCE

11. Scope

11.1 This test method is intended to aid in the identification of asphalt emulsions suitable for mixing with coarse-graded calcareous aggregates. It can be applied to other aggregates. (See Note 2.)

12. Significance and Use

12.1 This test method covers the determination of the ability of an asphalt emulsion to (1) coat an aggregate thoroughly, (2) withstand a mixing action while remaining as a film on the aggregate, and (3) resist the washing action of water after completion of the mixing.

13. Apparatus

13.1 *Mixing Pan*—A white-enamelled kitchen saucepan with handle, of approximately 3-L capacity.

13.2 *Mixing Blade*—A putty knife with a 31.8 by 88.9-mm steel blade with rounded corners. A 254.0-mm kitchen mixing spoon may be used as an alternative.

13.3 *Sieves*—Standard 19.0-mm and 4.75-mm sieves conforming to Specification E11.

13.4 *Constant-Head Water-Spraying Apparatus*—An apparatus for applying tap water in a spray under a constant head of

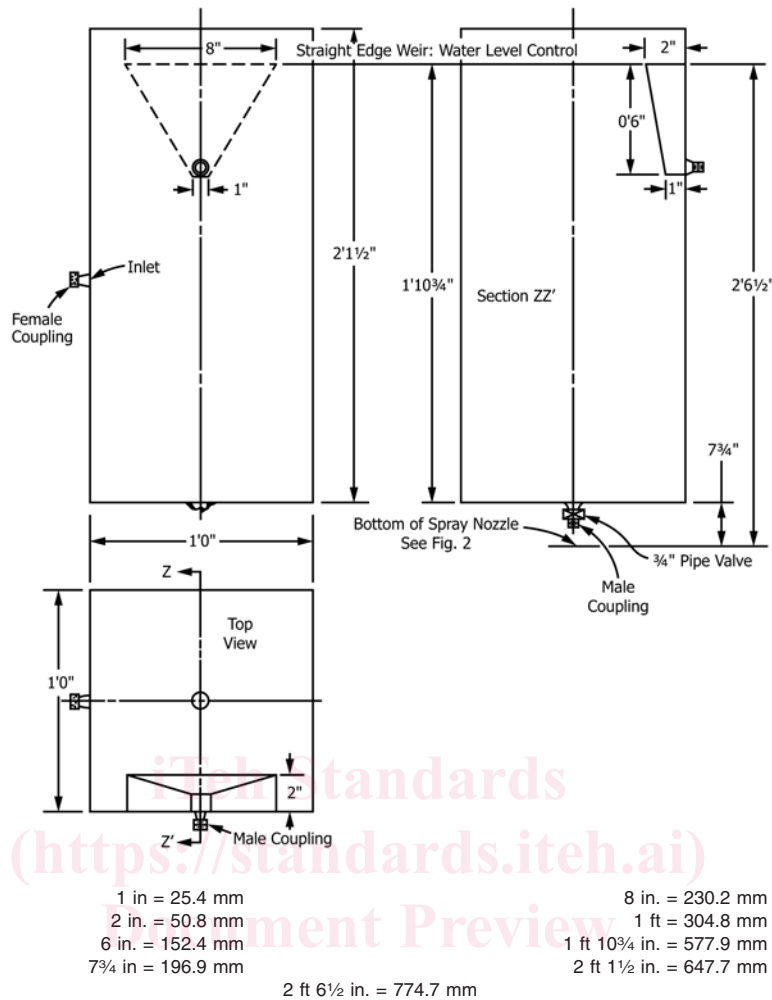


FIG. 2 Constant-Head Flow Tank

774.7 mm (Figs. 2 and 3). The water shall issue from the apparatus in a low-velocity spray.

13.5 *Thermometer*—An ASTM low softening point thermometer 15F (or 15C), having a range from -2 to 80 °C and conforming to the requirements in Specification E1.

13.6 *Balance*, capable of weighing 1000 g to within ± 0.1 g.

13.7 *Pipet*, of 10-mL capacity.

14. Materials

14.1 *Aggregate*—Standard reference aggregate⁴ shall be a laboratory-washed and air-dried limestone aggregate graded to pass the 19.0-mm sieve and be retained on the 4.75-mm sieve.

NOTE 2—Aggregates other than limestone may be used, provided calcium carbonate is omitted throughout the test method. Laboratory washing and air drying of such aggregates shall also be omitted.

⁴ Limestone from the Monon Stone Co. of Monon, IN, has been found suitable as reference aggregate.

14.2 *Calcium Carbonate*—Chemically pure, precipitated calcium carbonate (CaCO₃) shall be used as a dust to be mixed with the standard reference aggregate.

14.3 *Water*—Tap water of not over 250 ppm CaCO₃ hardness for spraying over the sample.

15. Sample

15.1 The sample shall be representative of the asphalt emulsion to be tested.

16. Procedure for Tests with Dry Aggregate

16.1 Carry out the test at 23.9 ± 5.5 °C.

16.2 Weigh 461 g of the air-dried, graded reference aggregate in the mixing pan.

16.3 Weigh 4.0 g of CaCO₃ dust in the mixing pan and mix with the 461 g of aggregate for approximately 1 min by means of a mixing blade to obtain a uniform film of dust on the aggregate particles.