



Designation: **C1565 – 09 C1565 – 17**

Standard Test Method for Determination of Pack-Set Index of Portland Cement and Blended Hydraulic Cements¹

This standard is issued under the fixed designation C1565; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This test method covers the determination of the pack-set index, which provides an indication of the mechanical force needed to overcome the consolidation of portland cement and blended hydraulic cements.

1.2 The pack-set index number provides a numerical value useful for manufacturers who desire to measure and control the effect that vibration-induced consolidation has upon the manufactured cement.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard. Values stated in SI units shall be obtained by measurement in SI units or by appropriate conversion, using the rules of Conversion and rounding given in Standard **IEEE/ASTM SI 10**, of measurements made in other units.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use. (WARNING—Fresh hydraulic-cementitious mixtures are caustic and may cause chemical burns to skin and tissue upon prolonged exposure.)*²

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*³

C1005 Specification for Reference Masses and Devices for Determining Mass and Volume for Use in the Physical Testing of Hydraulic Cements

IEEE/ASTM SI 10 International System of Units (SI) The Modernized Metric System

3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

3.1.1 *pack set, n*—a condition of hydraulic cement, exhibited in varying degrees, following silo storage or transport in bulk railcars or trucks, that causes the cement to resist flowing until considerable mechanical effort has been applied.

3.1.2 *pack-set index, n*—the numerical indication of the degree of pack set a particular cement exhibits when subjected to the procedures of this test method.

3.1.3 *peak voltage, n*— as pertaining to this method only, the energy in volts applied to consolidate the sample, which results in the maximum pack-set index for a particular cement and the apparatus used for the measurement.

4. Summary of Test Method

4.1 Portland or blended hydraulic cement is placed into a flask and then consolidated on a vibrating table by a vibration force controlled by time and volts. The consolidated bed is measured for relative strength by turning the flask to a horizontal position

¹ This test method is under the jurisdiction of ASTM Committee **C01** on Cement and is the direct responsibility of Subcommittee **C01.20** on Additions. Current edition approved June 1, 2009; Dec. 1, 2017. Published July 2009; December 2017. Originally approved in 2003. Last previous edition approved in 2004 as **C1565 – 04**; **C1565 – 09**. DOI: 10.1520/C1565-09.1520/C1565-17.

² Section on Safety, Manual of Cement Testing, *Annual Book of ASTM Standards*, Vol 04.01.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

and rotating in 180° increments until the bed collapses from the bottom of the flask. The number of half turns is a relative indication of the force required to overcome the consolidation and is designated the pack-set index, or P.S.I.

5. Significance and Use

5.1 This method is intended to help manufacturers determine the relative pack-set tendency of their cement(s). The test establishes a pack-set index which, when properly correlated with field performance, is useful in predicting or preventing field unloading difficulties.

5.2 The test is an aid to routine control during cement production and is not suitable for specification purposes.

5.3 In general, field performance of cement flowability is satisfactory when the pack-set index as determined on freshly ground cement averages 0 to 15 and is unsatisfactory when the index exceeds 25. Any prediction of field performance of cement flowability measuring 16 to 25 is tenable. These are general ranges and the field performance of individual cements may not necessarily fall within these ranges. Additional conditions, after the cement has left the control of the manufacturing facility, can affect the apparent pack set index as well.

5.4 Any attempt to apply the critical range of pack-set index numbers based on freshly ground cement to job cement without special treatment of the sample would be problematic. The test is a “GO-NO GO” type of test and should not be used for specification purposes.

5.5 The pack-set index of field cement can be evaluated in terms of the pack-set index ranges of that cement as determined when freshly-ground. This comparison can aid the manufacturer in producing cement that offers the best field performance for pack-set properties.

5.6 Silo storage of cement may result in a greater amount of consolidation than this method is designed to induce, and the resulting forces required to overcome that consolidation are not measured by this test method.

5.7 Pack set is not to be confused with “warehouse set” which results from surface hydration of the cement from adsorbed moisture.

6. Interferences

6.1 Results obtained from the pack-set test are dependent on sample exposure (See [Note 1](#)).

NOTE 1—Fresh cement has a greater pack-set tendency. Cement stored in silos for only a day or two will test similar to fresh cement. Cement stored in full silos, where aeration is negligible, may develop lower pack-set indices upon further aging. Even samples in sealed containers may vary.

6.2 Pack-set index determination can be affected by sample temperature (See [Note 2](#)).

NOTE 2—Cement with a temperature noticeably hotter than room temperature may produce a different pack-set index number than that same cement cooled to room temperature. Cooling of hot cement samples must be accomplished with minimum aeration to avoid moisture and CO₂ adsorption.

6.3 The testing room humidity can significantly influence the determined pack-set index.

6.4 Keep the apparatus level during the testing procedure.

6.5 The vibration energy transferred to the sample is affected by the support given the apparatus (See [Note 3](#)). The determination of pack-set index for unknown samples shall be accomplished on the same physical support that the peak voltage for the test was determined on.

NOTE 3—Apparatus which is not setting firmly on the counter or table may not deliver repeatable results.

6.6 Vibration energy delivered by the table is related to the proper handling and adjustment of the table. See Section 7 for details.

6.7 Vibration energy delivered by the table is related to the frequency of the source voltage. This variation, if present, will result in a poor repeatability and require more frequent determination of the peak voltage.

7. Apparatus

7.1 *Erlenmeyer Flask*, 250 mL capacity, regular wall thickness, fitted with a number 14 (large diameter 32 mm and small diameter 25 mm) cork stopper. Flasks are not interchangeable. Each flask and cork combination must have the peak voltage determined prior to use in the test method (See [Note 4](#)).

7.2 *Reference Masses and Devices for Determining Mass* shall conform to the requirements of Specification [C1005](#) as appropriate for the size of the sample, the mass of which is to be determined, with a sensitivity of no less than 0.1 g and a readability of 0.1 g or less.

NOTE 4—There are enough differences between Erlenmeyer flasks of the same rated capacity to cause significant difference in the pack-set index. It is recommended that several flasks which deliver similar pack-set index numbers for the same cement be kept as spares.

7.3 *Vibrating Table*, (see [Fig. 1](#)), capable of generating electromagnetic vibrations at the frequency of 60 Hz, having a wooden or phenolic resin top with dowel pins installed equidistant from each other on the circumference of the circle centered on the table,

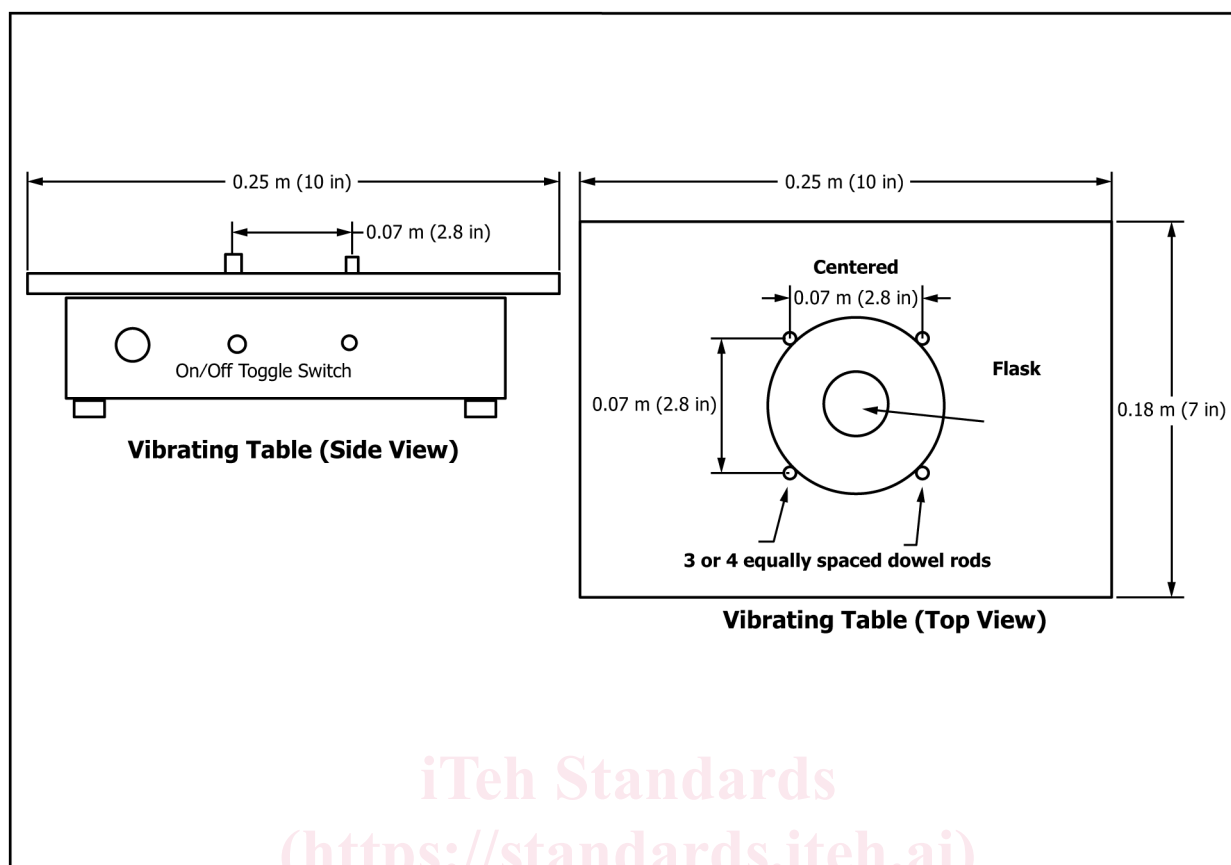


FIG. 1 Vibrating Table

with a radius slightly greater than the largest radius of the flask (to restrain the flask movement on the table).⁴ A device that is capable of stopping any lateral movement of the flask during vibration is required (See [Note 5](#)). The air gap setting between the armatures of the vibrating table is critical to the generation of the proper vibrational amplitude and must be adjusted according to the manufacturer’s instructions. Manufacturer’s recommendations and precautions for proper operation must be followed to assure the accurate determination of the pack set index.

NOTE 5—Three or four dowel pins of 6 to 10 mm diameter and 25 to 30 mm long will be sufficient to restrain the flask. Interconnecting rubber bands or rubber cam-locks can be used to restrain the flask to prevent lateral movement of the flask during vibration.

7.4 *Roto-Tester*; (see [Fig. 2](#)), a device on which the Erlenmeyer flask can be mounted in a horizontal position against a vertical, flat, rotating plate that contains frictional hold-down cams to prevent the flask from falling, and capable of smoothly rotating the flask and table while in that horizontal position, in 180° increments at the rate of approximately 40 one-half rotations per minute with a short partial second pause between half-rotations. The device shall be equipped with a counter capable of recording the number of one-half rotations of the table.⁵

7.5 *Voltmeter*; capable of measuring and displaying the voltage delivered to the vibrating table to the nearest 0.5 VAC.

7.6 *Variable-voltage Transformer*; inductance-type, capable of supplying the vibrating table with voltage within the range of 0 v to 100 % of the design voltage of the vibrating table.

7.7 *Automatic Timer*; capable of controlling the “ON” time of the variable-voltage transformer and the vibrating table to $15 \pm \frac{1}{2}$ s.

8. Preparation of Apparatus—Determination of Peak Voltage

8.1 Determine the peak voltage applied to the vibrating table to achieve the maximum pack-set index number for a sample.

8.1.1 Turn the vibrating table ON, and using the voltage adjustment of the variable-transformer, set the voltage so that little or no compaction takes place in the cement sample during the 15 s vibration. Increment the voltage by 2v until the compaction achieved result is a pack-set index value greater than zero. Continue incrementing the voltage by 2v until a pack-set index is

⁴ The vibrating table is available from suppliers of the pack set apparatus. A list of suppliers can be obtained from ASTM.

⁵ The roto-tester is available from suppliers of the pack set apparatus. A list of suppliers can be obtained from ASTM.