



Designation: E2580 – 17

Standard Practice for Ultrasonic Testing of Flat Panel Composites and Sandwich Core Materials Used in Aerospace Applications¹

This standard is issued under the fixed designation E2580; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This practice establishes two procedures for ultrasonic testing (UT) of flat panel composites and flat sandwich core panels (parallel surfaces). Typical as-fabricated lay-ups include uniaxial, cross ply and angle ply laminates; as well as honeycomb sandwich core materials. These procedures can be used throughout the life cycle of the materials; product and process design optimization, on line process control, after manufacture inspection, and in service inspection. Contact methods such as angle-beam techniques using shear waves, or surface-beam techniques using Lamb waves, are not discussed.

1.2 Ultrasonic testing is a common subsurface method for detection of laminar oriented discontinuities. Two techniques can be considered based on panel surface accessibility; pulse echo for one sided and through transmission (bubblers/squirters) for two sided. As used in this practice, both require the use of a pulsed straight-beam ultrasonic longitudinal wave followed by observing indications of either the reflected (pulse-echo) or received (through transmission) wave. The general types of anomalies detected by both techniques include foreign materials, delamination, disbond/un-bond, fiber debonding, inclusions, porosity, and voids.

1.3 This practice provides two ultrasonic test procedures. Each has its own merits and requirements for inspection and shall be selected as agreed upon in a contractual document.

1.3.1 *Test Procedure A, Pulse Echo (non-contacting and contacting)*, is at a minimum a single transducer transmitting and receiving a longitudinal wave in the range of 0.5 to 20 MHz (see Fig. 1). This procedure requires access to only one side of the specimen. This procedure can be conducted by automated or manual means. Automated and manual test results may be imaged or recorded.

1.3.2 *Test Procedure B, Through Transmission*, is a combination of two transducers. One transmits a longitudinal wave

and the other receives the longitudinal wave in the range of 0.5 MHz to 20 MHz (see Fig. 2). This procedure requires access to both sides of the specimen. This procedure is automated and the examination results are recorded.

1.4 This practice does not specify accept-reject criteria.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[E2580 Terminology of Structural Sandwich Constructions \(Withdrawn 2016\)](#)³

[D3878 Terminology for Composite Materials](#)

[D5687/D5687M Guide for Preparation of Flat Composite Panels with Processing Guidelines for Specimen Preparation](#)

[E543 Specification for Agencies Performing Nondestructive Testing](#)

[E1309 Guide for Identification of Fiber-Reinforced Polymer-Matrix Composite Materials in Databases \(Withdrawn 2015\)](#)³

[E1316 Terminology for Nondestructive Examinations](#)

[E1434 Guide for Recording Mechanical Test Data of Fiber-Reinforced Composite Materials in Databases \(Withdrawn 2015\)](#)³


¹ This practice is under the jurisdiction of ASTM Committee E07 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.06 on Ultrasonic Method.

Current edition approved Nov. 1, 2017. Published December 2017. Originally approved in 2007. Last previous edition approved in 2012 as E2580 - 12. DOI: 10.1520/E2580-17.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

*A Summary of Changes section appears at the end of this standard

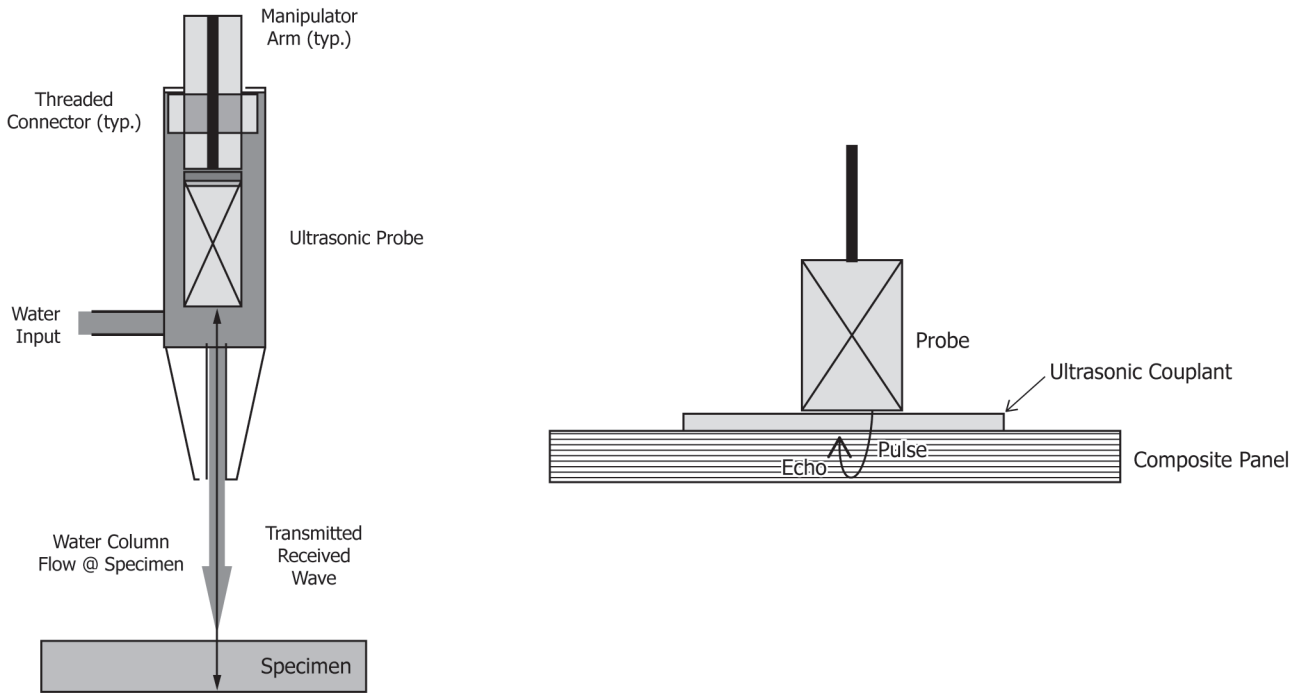

Automated

Manual

FIG. 1 Test Procedure A, Pulse Echo Apparatus Set-up

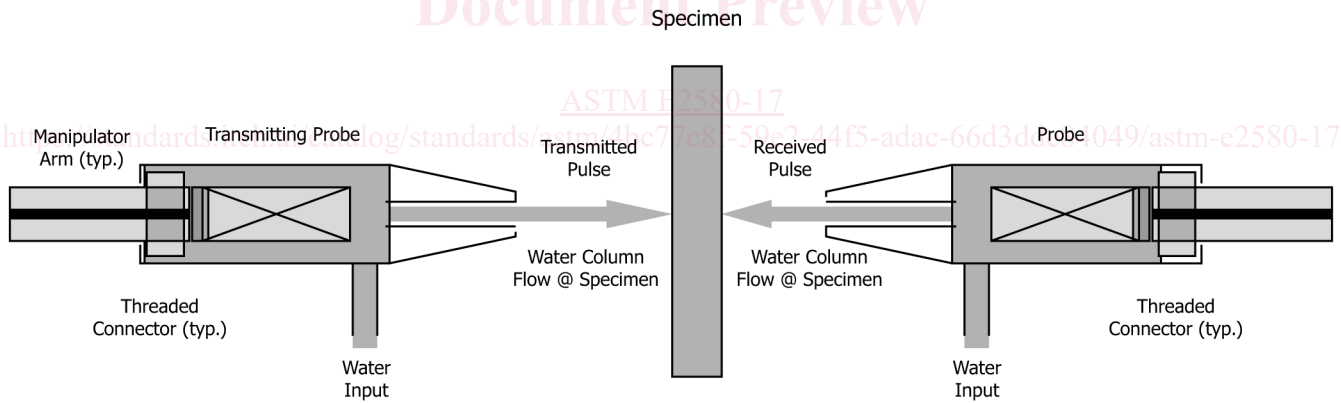


FIG. 2 Test Procedure B, Through Transmission Apparatus Set-up

E1471 Guide for Identification of Fibers, Fillers, and Core Materials in Computerized Material Property Databases (Withdrawn 2015)³

2.2 SAE Standards:⁴

ARP 5605 Solid Composite Laminate NDI Reference Standards, Issued 2001-09

ARP 5606 Composite Honeycomb NDI Reference Standards, Issued 2001-09

2.3 AIA Standard:⁵

NAS-410 NAS Certification & Qualification of Nondestructive Test Personnel

2.4 ASNT Standards:⁶

SNT-TC-1A Recommended Practice for Personnel Qualification and Certification in Nondestructive Testing

⁵ Available from Aerospace Industries Association of America, Inc. (AIA), 1000 Wilson Blvd., Suite 1700, Arlington, VA 22209-3928, <http://www.aia-aerospace.org>.

⁶ Available from American Society for Nondestructive Testing (ASNT), P.O. Box 28518, 1711 Arlingate Ln., Columbus, OH 43228-0518, <http://www.asnt.org>.

⁴ Available from Society of Automotive Engineers (SAE), 400 Commonwealth Dr., Warrendale, PA 15096-0001, <http://www.sae.org>.

ANSI/ASNT CP-189 Standard for Qualification and Certification or Nondestructive Testing Personnel

2.5 *ISO Standard*.⁷

ISO 9712 NDT—Qualification and Certification of NDT Personnel in the Applicable Product Sector “Aerospace”

3. Terminology

3.1 *Definitions*—Terminology in accordance with Terminologies **C274**, **E1316**, and **D3878** shall be used where applicable.

3.2 *Definitions of Terms Specific to This Standard*:

3.2.1 *flat panel composite, n*—any fiber reinforced composite lay-up consisting of laminate (plies) with one or more orientations with respect to some reference direction that are consolidated by press or autoclave to yield a two-dimensionally flat article of finite thickness.

3.2.2 *sandwich core material, n*—a structural panel made up of two relatively thin outer skins of composite laminate or other material, such as metal or wood, separated by and bonded to a relatively thick lightweight inner core such as honeycomb, open and close cell foam, wave formed material, bonded composite tubes, or naturally occurring material such as balsa wood.

4. Summary of Practice

4.1 This practice describes two procedures for detecting anomalies in flat panel composite and flat sandwich core panels using ultrasonic longitudinal waves coupled by either contact (Procedure A) or bubbler/squitter (Procedure B). Equipment, reference blocks, examination and evaluation procedures, and documentation are described in detail.

5. Significance and Use

5.1 This practice is intended primarily for the testing of flat panel composites and sandwich core panels to an acceptance criteria most typically specified in a purchase order or other contractual document.

5.2 *Basis of Application*—There are areas in this practice that require agreement between the cognizant engineering organization and the supplier, or specific direction from the cognizant engineering organization.

6. Basis of Application

6.1 The following items are subject to contractual agreement between the parties using or referencing this standard.

6.2 *Personnel Qualification*—If specified in the Contractual agreement, personnel performing examinations to this standard shall be qualified in accordance with a nationally or internationally recognized NDT personnel qualification practice or standard such as ANSI/ASNT-CP-189, SNT-TC-1A, NAS-410, or similar document and certified by the employer or certifying agency, as applicable. The practice or standard used and its

applicable revision shall be identified in the contractual agreement between the using parties.

6.3 *Qualification of Nondestructive Agencies*—If specified in the contractual agreement, NDT agencies shall be qualified and evaluated as described in Specification **E543**. The applicable edition of Specification **E543** shall be specified in the contractual agreement.

6.4 *Surface Preparation*—The pre-examination surface preparation criteria shall be in accordance with 8.4, unless otherwise specified.

6.5 *Timing of Examination*—The timing of examination shall be in accordance with 8.2 and 8.3, unless otherwise specified.

6.6 *Extent of Examination*—The extent of examination shall be in accordance with 8.5 unless otherwise specified.

6.7 *Reporting Criteria/Acceptance Criteria*—Reporting criteria for the examination results shall be in accordance with 14.1 unless otherwise specified. Since acceptance criteria (for example, for reference radiographs) are not specified in this standard, they shall be specified in the contractual agreement.

6.8 *Reexamination of Repaired/Reworked Items*—Reexamination of repaired/reworked items is not addressed in this standard and if required shall be specified in the contractual agreement.

7. Equipment and Materials

7.1 *Equipment*

7.1.1 *Operation*—Test equipment shall be capable of providing uniform, repeatable, and controlled operation.

7.1.2 *Electronic Equipment*—The electronic equipment should be capable of producing and processing electronic signals at frequencies in the range of search unit frequencies being used.

7.1.3 *Search Unit(s)*—The search unit(s) selected should be compatible with the electronic equipment being used and with the material to be inspected. The search unit should match the intended squitter(s) or contact. Only straight-beam (longitudinal) search units, with flat or focused acoustic lenses, should be used.

7.1.4 *Alarm*—The alarm or threshold level should be adjustable to allow triggering at any commonly required level of indication amplitude. Alarms are not required on systems that record amplitude recordings.

7.1.5 *Alarm Gate Synchronization*—In the pulse echo mode ensure that the alarm gate tracks the inspection area. The gate should lock on the first interface pulse from the test piece rather than on the initial pulse from the system. In the through transmission mode the alarm gate should be wide enough to cover any negative or positive movement (left to right) in the horizontal plane.

7.1.6 *Manipulating Equipment* should be provided to adequately support the search tube(s) and allow angular adjustment in two mutually perpendicular planes. The search unit manipulator shall be capable of providing the adjustments necessary to properly position the search unit during testing. The scanning and indexing apparatus should have sufficient

⁷ Available from International Organization for Standardization (ISO), ISO Central Secretariat, BIBC II, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <http://www.iso.org>.